



# Cu<sub>2</sub>O Photocathode for Low Bias Photoelectrochemical Water Splitting Enabled by NiFe-Layered Double Hydroxide Co-Catalyst

Huan Qi, Jonathan Wolfe, Denis Fichou, Zhong Chen

## ► To cite this version:

Huan Qi, Jonathan Wolfe, Denis Fichou, Zhong Chen. Cu<sub>2</sub>O Photocathode for Low Bias Photoelectrochemical Water Splitting Enabled by NiFe-Layered Double Hydroxide Co-Catalyst. Scientific Reports, 2016, 6, pp.30882. 10.1038/srep30882 . hal-01360210

**HAL Id: hal-01360210**

**<https://hal.sorbonne-universite.fr/hal-01360210>**

Submitted on 5 Sep 2016

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution 4.0 International License

# SCIENTIFIC REPORTS

OPEN

## $\text{Cu}_2\text{O}$ Photocathode for Low Bias Photoelectrochemical Water Splitting Enabled by NiFe-Layered Double Hydroxide Co-Catalyst

Received: 16 May 2016

Accepted: 11 July 2016

Published: 04 August 2016

Huan Qi<sup>1,\*</sup>, Jonathan Wolfe<sup>2,\*</sup>, Denis Fichou<sup>3,4,5</sup> & Zhong Chen<sup>1</sup>

Layered double hydroxides (LDHs) are bimetallic hydroxides that currently attract considerable attention as co-catalysts in photoelectrochemical (PEC) systems in view of water splitting under solar light. A wide spectrum of LDHs can be easily prepared on demand by tuning their chemical composition and structural morphology. We describe here the electrochemical growth of NiFe-LDH overlayers on  $\text{Cu}_2\text{O}$  electrodes and study their PEC behavior. By using the modified  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  electrodes we observe a remarkable seven-fold increase of the photocurrent intensity under an applied voltage as low as  $-0.2\text{V}$  vs Ag/AgCl. The origin of such a pronounced effect is the improved electron transfer towards the electrolyte brought by the NiFe-LDH overlayer due to an appropriate energy level alignment. Long-term photostability tests reveal that  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  photocathodes show no photocurrent loss after 40 hours of operation under light at  $-0.2\text{V}$  vs Ag/AgCl low bias condition. These improved performances make  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  a suitable photocathode material for low voltage  $\text{H}_2$  production. Indeed, after 8 hours of  $\text{H}_2$  production under  $-0.2\text{V}$  vs Ag/AgCl the PEC cell delivers a 78% faradaic efficiency. This unprecedented use of  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  as an efficient photocathode opens new perspectives in view of low bias or self-biased PEC water splitting under sunlight illumination.

The accelerated depletion of fossil fuel reserves combined with increasing demand of energy across the world has triggered a tremendous effort toward alternative energy sources and various technologies are currently being explored. Among those, photoelectrochemical (PEC) water splitting under solar light irradiation has shown their potential by the successful integration of abundant energy source and high efficient catalysts. In order to realize high efficiency PEC systems in view of water splitting, a number of photocatalysts have been investigated including the widespread  $\text{TiO}_2$ <sup>1–3</sup>,  $\text{ZnO}$ <sup>4–7</sup>,  $\text{WO}_3$ <sup>8–11</sup>,  $\text{Fe}_2\text{O}_3$ <sup>12</sup>, as well as more innovative catalysts such as  $\text{Cu}_2\text{O}$ <sup>13–15</sup>, and  $\text{BiVO}_4$ <sup>16</sup>.

$\text{Cu}_2\text{O}$  is a promising photocathode material due to its suitable band gap (1.9–2.2 eV) and high absorption coefficient in the visible region<sup>17–20</sup>. Its conduction band is located above the reduction potential of water, making it suitable for mediating  $\text{H}_2$  production with little or no external bias in a PEC cell. Among different methods, electrodeposition has proven to be the most convenient and reliable to prepare nanostructured  $\text{Cu}_2\text{O}$ <sup>17,21</sup>. Recent studies show that the  $\text{Cu}_2\text{O}$  morphology and orientation can be controlled by judiciously tuning the deposition parameters such as the electrolyte pH, temperature, applied potential and current density<sup>17,21</sup>. The morphology and crystal structure determine the material performances through their role in light absorption and charge transport.

Although  $\text{Cu}_2\text{O}$  possesses an intrinsic potential as a photocathode, the reported photocurrents remain well below the theoretical values, in particular under low external biases. These poor performances arise essentially from structural defects at the semiconductor-electrolyte interface. It has been reported that at low external

<sup>1</sup>School of Materials Science Engineering, Nanyang Technological University, Singapore 639798, Singapore.

<sup>2</sup>Interdisciplinary Graduate School, Nanyang Technological University, Singapore 639798, Singapore. <sup>3</sup>School of Physical and Mathematical Sciences, Nanyang Technological University, 637371, Singapore. <sup>4</sup>CNRS, UMR 8232, Institut Parisien de Chimie Moléculaire, Paris, France. <sup>5</sup>Sorbonne Universités, UPMC Univ Paris 06, UMR 8232, Institut Parisien de Chimie Moléculaire, F-75005, Paris, France. \*These authors contributed equally to this work. Correspondence and requests for materials should be addressed to D.F. (email: denis.fichou@upmc.fr) or Z.C. (email: aszchen@ntu.edu.sg)

voltages, Cu<sub>2</sub>O does not transfer electrons efficiently towards the electrolyte due to an inappropriate band bending<sup>22</sup>. In order to improve the photocurrent of Cu<sub>2</sub>O electrodes, various approaches have been recently developed. For example Cu<sub>2</sub>O can be combined with another catalyst such as TiO<sub>2</sub><sup>23</sup>, or by depositing a protective layer on its surface such as Cu<sub>2</sub>S<sup>13,14</sup>, RuO<sub>2</sub><sup>24</sup>, or polyoxometallates<sup>25</sup>.

Layered double hydroxides (LDHs) attract a growing attention as co-catalysts due to several advantages. LDHs constitute a group of two-dimensional materials of general formula  $[M_{1-x}^{2+}M_x^{3+}(\text{OH})_2][A_{x/n}]\cdot m\text{H}_2\text{O}$  in which a fraction of a divalent metal cation  $M^{2+}$  coordinated octahedrally by hydroxy groups is replaced isomorphously by a trivalent metal cation  $M^{3+}$ <sup>26,27</sup>. The variety in chemical composition and structural morphology of LDH materials make them suitable for a wide range of applications as electrocatalysts<sup>28–32</sup>. In particular, LDHs can act as efficient photocatalysts for improving the charge separation of photogenerated electrons and holes<sup>33</sup>. Moreover, the hierarchical morphology of LDHs provides convenient charge transfer at the electrolyte interface in PEC systems. Several types of LDHs such as CoNi<sup>33</sup>, or ZnCo<sup>34</sup>, have been widely investigated to enhance PEC water splitting.

We describe here the fabrication of Cu<sub>2</sub>O/NiFe-LDH via a facile two-step electrodeposition method and the use of NiFe-LDH to enhance the performances of Cu<sub>2</sub>O photocathodes. The NiFe-LDH layers grow as nanoplatelets that are uniformly anchored onto the Cu<sub>2</sub>O surface. Our Cu<sub>2</sub>O/NiFe-LDH exhibits greatly improved photocurrent intensities particularly at low applied voltages. Moreover we demonstrate that modified Cu<sub>2</sub>O/NiFe-LDH photocathodes allow more efficient H<sub>2</sub> production at low applied voltages. The Cu<sub>2</sub>O/NiFe-LDH photocathodes reveal to be highly stable with no degradation under low bias after 40 hours of illumination, making Cu<sub>2</sub>O/NiFe-LDH an excellent photoelectrode for low bias PEC water splitting.

## Results and Discussion


**Morphology of Cu<sub>2</sub>O/NiFe-LDH materials.** Images recorded by field-emission scanning electron microscopy (FESEM) show that electrodeposited Cu<sub>2</sub>O consists of compact and highly homogeneous layers made of cubic particles having ~400 nm in size (Fig. 1a) and thicknesses of ~1 μm after 1,500 s of deposition time (Fig. 1b). NiFe-LDH overlayers are then grown on the Cu<sub>2</sub>O samples using different deposition times (Fig. 1b,c). After 60 seconds, the NiFe-LDH material adopts a uniform nanoflake morphology (Fig. 1d) with individual flakes of size ~5 nm (Figure S1). After 300 s it self-assembles into sponge-like structures (Fig. 1f). AFM images show that after deposition of NiFe-LDH, the surface roughness is greatly increased (Table S1 and Figure S2) and may thus increase substantially the number of photons absorbed by the photocathode. Besides, the XRD pattern of NiFe-LDH after 150 s exhibits typical (003), (006), and (104) reflection peaks, while Cu<sub>2</sub>O shows the known dominant (111) reflection (Figure S3)<sup>35,36</sup>. For NiFe-LDH (20 s) XRD does not reveal any visible peaks, while EDX images confirm the existence and uniformity of Ni and Fe elements in the Cu<sub>2</sub>O layer (Figure S4).

**PEC measurement. Linear sweep voltammetry.** The PEC properties of Cu<sub>2</sub>O with and without NiFe-LDH were investigated under chopped light by linear sweep voltammetry (LSV) (Fig. 2a and Figure S5a). Before deposition of NiFe-LDH the photocurrent density is 1.27 mA.cm<sup>-2</sup> under -0.6 V vs Ag/AgCl. For deposition times shorter than 20 s the photocurrent of bare Cu<sub>2</sub>O does not improve significantly (Figure S6). After deposition of NiFe-LDH for 20 s, the photocurrent density exhibits a twofold increase to reach 2.42 mA.cm<sup>-2</sup>. An even more important relative photocurrent increase is observed in the low bias range from 0.0 V to -0.3 V vs Ag/AgCl. For example, Cu<sub>2</sub>O/NiFe-LDH (20 s) under -0.2 V vs Ag/AgCl, that is more than seven times that of bare Cu<sub>2</sub>O (-0.05 mA.cm<sup>-2</sup>, Fig. 2b). It shows that the introduction of the NiFe-LDH layer induces a more efficient separation of photogenerated charges on one side and an effective electron injection into the electrolyte on the other side. Prolonged deposition of NiFe (more than 20 s) results in less or no improvement in photocurrent (Figure S5a) due to a too strong light absorption by NiFe-LDH that reduces charge carriers generation by Cu<sub>2</sub>O.

Furthermore, although bare Cu<sub>2</sub>O generates a *positive* photocurrent when illuminated under *positive* low voltages (Fig. 2c), the Cu<sub>2</sub>O/NiFe-LDH electrodes generates a *negative* photocurrent under *negative* voltages (Fig. 2d and Figure S5c,d). For example, under -0.1 V vs Ag/AgCl, Cu<sub>2</sub>O electrode produces a very weak *positive* photocurrent (< +0.01 mA.cm<sup>-2</sup>) while Cu<sub>2</sub>O/NiFe-LDH (20 s) generates a *negative* photocurrent (-0.3 mA.cm<sup>-2</sup>). Note that for reversed voltages (that is negative for bare Cu<sub>2</sub>O and positive for Cu<sub>2</sub>O/NiFe-LDH) both types of electrodes do not produce any significant photocurrent. Whereas, this photocurrent reversal is another evidence of the profound modification brought by the NiFe-LDH (20 s) overlay on the PEC behaviour of Cu<sub>2</sub>O electrodes.

The Mott-Schottky plots comparison of Cu<sub>2</sub>O photocathode with and without NiFe-LDH (20 s) reveals the greatly increased number of charge carriers that has reached the interface is induced by NiFe-LDH cocatalyst (Figure S7). This unveils the function of NiFe-LDH as an efficient cocatalyst that improves the charge separation of Cu<sub>2</sub>O photocathode. Furthermore, in order to eliminate the possibilities that this photocurrent enhancement is induced by the metal valence state changes in NiFe-LDH, we have investigated the cyclic voltammetry behaviour of NiFe-LDH (Figure S8). Results indicate that at the low bias condition (less than -0.2 V vs Ag/AgCl), there is no reduction/oxidation behaviour on NiFe-LDH. This excludes the likelihoods of metal valence state changes-induced photocurrent enhancement of Cu<sub>2</sub>O/NiFe-LDH photocathode in low bias condition. The photoresponse of pure NiFe-LDH (300 s) has also been explored (Figure S9). Results show that NiFe-LDH itself generates very limited charge carrier upon illumination. This excludes the possibilities that the photocurrent enhancement of Cu<sub>2</sub>O/NiFe-LDH photocathode is induced by the increased number of photon-generated charge carriers induced by NiFe-LDH.

Another point worth notice is that the difference in photocurrent of Cu<sub>2</sub>O photocathode and Cu<sub>2</sub>O/NiFe-LDH photocathode becomes smaller with increased bias voltage. This is because the increased high applied voltage is able to efficiently separate the majority of photon-generated charge carriers. The effects of NiFe-LDH become less pronounced. As there is no difference for the total number of charge carriers as Cu<sub>2</sub>O is the only photon absorber (Figure S9). Thus, the maximum photocurrent of both electrodes have very little difference.

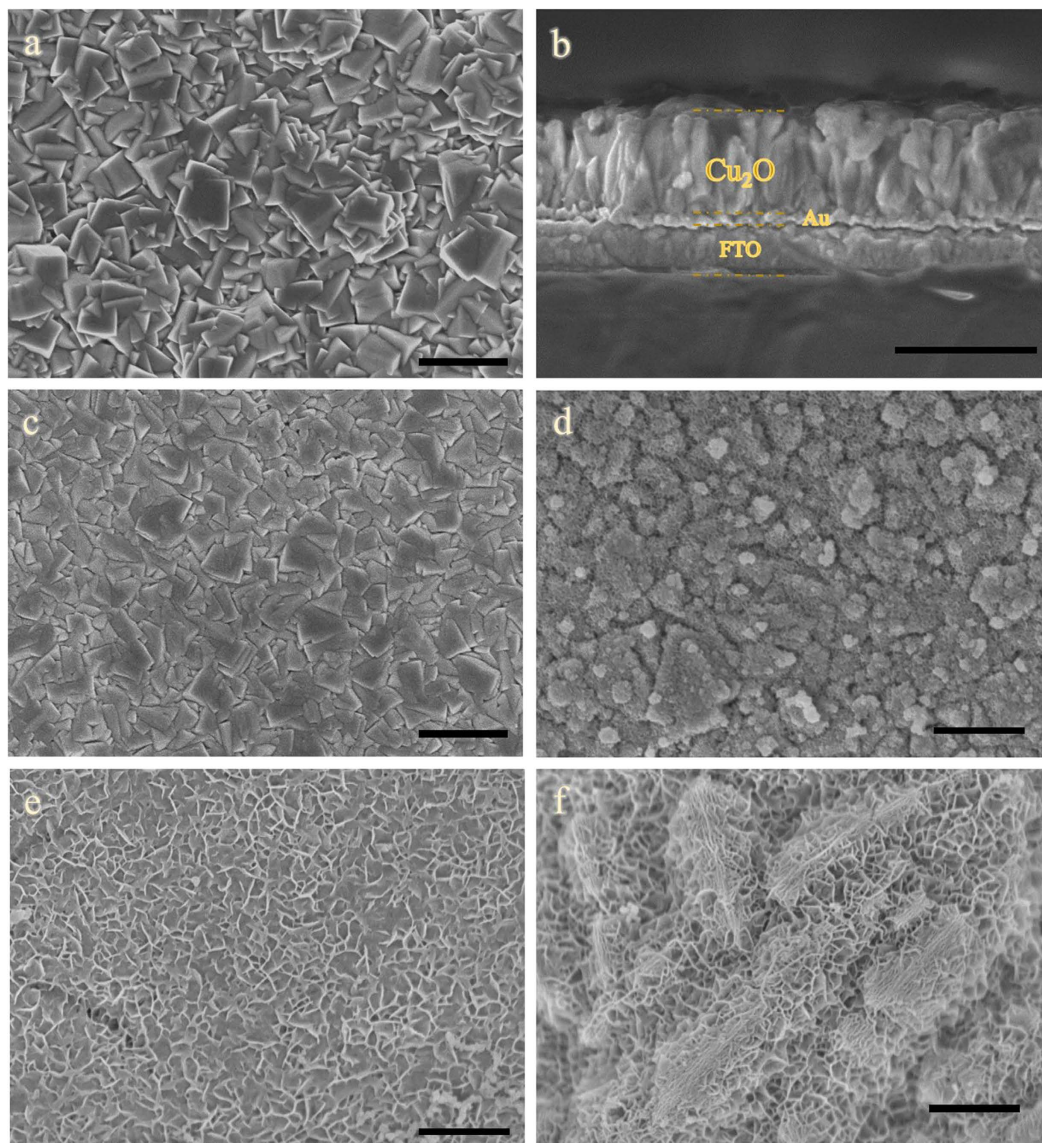


**Figure 1.** FESEM images of (a) bare  $\text{Cu}_2\text{O}$ ; (b) cross-sectional image of bare  $\text{Cu}_2\text{O}$ ; (c)  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  (20 s); (d)  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  (60 s); (e)  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  (90 s) and (f)  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  (300 s). Scale bars: 1  $\mu\text{m}$ .

**Electrochemical impedance spectroscopy.** Electrochemical impedance spectroscopy (EIS) provides information about the interfacial property of the synthesized photocathode, which further reveals the efficient charge separation effect and improved electron injection property brought by NiFe-LDH layer (Fig. 3). The semi-circular diameter of the measured EIS stands for the charge carrier transfer resistance ( $R_{ct}$ ) that controls the electron transfer kinetics at the electrode/electrolyte interface<sup>37</sup>. The resistance of  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  in the dark is much larger than that under illumination, indicating a higher number of charge carriers at the electrode interface. (Figure S10). In addition, as compared with bare  $\text{Cu}_2\text{O}$ , the radius of the semicircle of  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  is smaller under all the conditions (Fig. 3a,b and Figure S11).

An interesting observation is that by increasing the applied bias from  $-0.02\text{ V}$  to  $-0.12\text{ V}$  vs  $\text{Ag}/\text{AgCl}$ , the interface resistance increases for bare  $\text{Cu}_2\text{O}$  but decreases for the  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  samples. This phenomenon arises from the difference between the electrode/electrolyte interfaces with either  $\text{Cu}_2\text{O}$  or NiFe-LDH. Under illumination over the voltage range  $-0.02/-0.12\text{ V}$  vs  $\text{Ag}/\text{AgCl}$ , the surface of bare  $\text{Cu}_2\text{O}$  is predominantly charged with holes essentially because of the blockage of the electron transfer path from  $\text{Cu}_2\text{O}$  to the electrolyte (see Fig. 4a). At more negative voltages, the number of holes decreases, thus resulting in a resistance increase of bare  $\text{Cu}_2\text{O}$ . This is evidenced by the larger semi-circle diameter in the EIS (Fig. 3a). In contrast, deposition of a NiFe-LDH overlayer induces an appropriate energy level alignment with respect to the electrolyte redox levels so that electrons are efficiently transported towards the surface where they reduce water into  $\text{H}_2$  (Fig. 4b and Figure S12b). Electrons become predominant and the NiFe-LDH surface is negatively charged. The number of electrons increases with increasing negative voltage, as confirmed by the smaller semi-circle diameter in Fig. 3b. This demonstrates the key role of NiFe-LDH in introducing appropriate energy levels at the interface and the subsequent higher electron injection rate into the electrolyte.



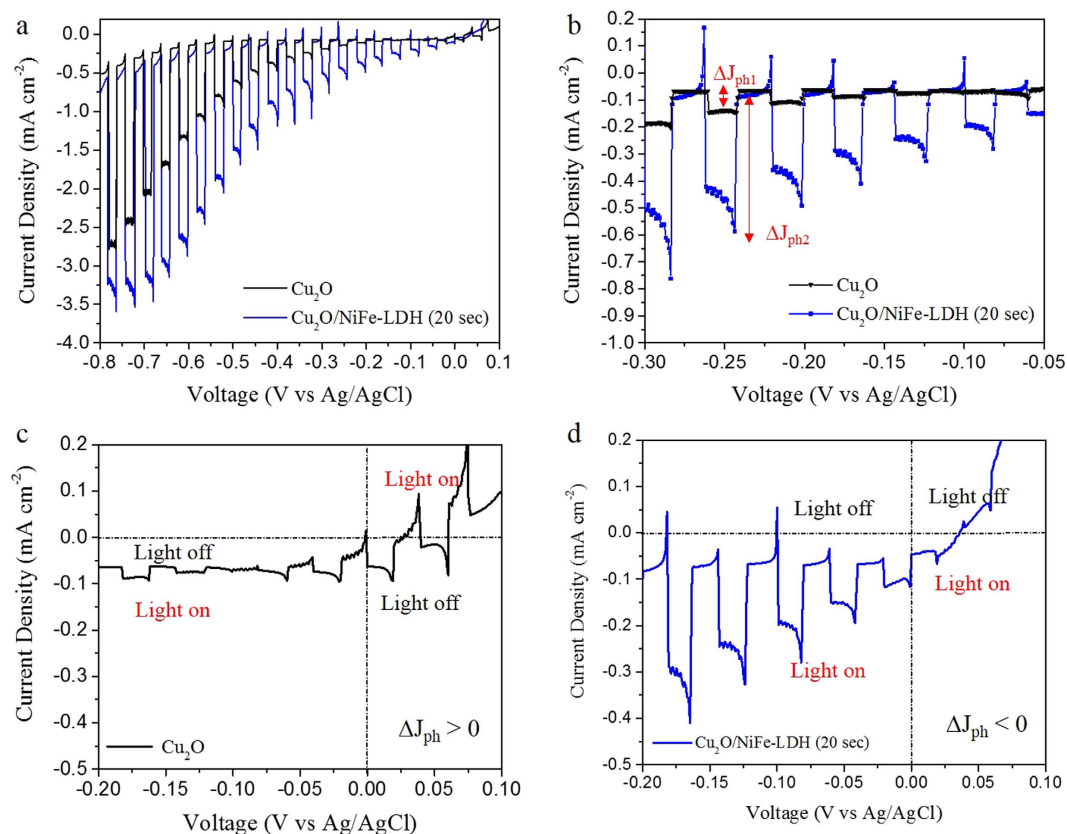


**Figure 2.** Linear sweep voltammetry under light-chopped illumination of bare  $\text{Cu}_2\text{O}$  and  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  (20 s) electrodes in the voltage ranges (a)  $+0.1/-0.8$  V and (b)  $-0.3/-0.05$  V vs Ag/AgCl.  $\Delta J_{\text{ph}}$  denotes the photocurrent density after subtraction of the dark current. At  $-0.25$  V vs Ag/AgCl, the  $\Delta J_{\text{ph}}$  value for bare  $\text{Cu}_2\text{O}$  is  $\Delta J_{\text{ph1}} = 0.07 \text{ mA}\cdot\text{cm}^{-2}$  while for  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  it is  $\Delta J_{\text{ph2}} = 0.49 \text{ mA}\cdot\text{cm}^{-2}$ . (c,d) Zoom-in of the photoresponse of  $\text{Cu}_2\text{O}$  and  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  electrodes in the  $-0.2/+0.1$  V vs Ag/AgCl low voltage range.


Overall, the inefficient surface charge separation efficiencies and insufficient electron transfer in the electrolyte of bare  $\text{Cu}_2\text{O}$  induces an overwhelming number of photogenerated electrons in the bulk. On the contrary, after coating by NiFe-LDH, electrons are able to transfer from electrode to electrolyte under very low external bias (Fig. 4). This results in a reduced number of electrons in the  $\text{Cu}_2\text{O}$  layer, driving electrons from the counter-electrode to the  $\text{Cu}_2\text{O}$  photocathode. As a result, the sample with and without NiFe-LDH have different electron flow directions for a given bias (Fig. 4 and Figure S12). This superior property makes  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  an excellent candidate for photocathode in low or non-bias PEC systems.

**Photostability.** In order to evaluate the potential of  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  photocathodes for  $\text{H}_2$  production, we tested their long-term stability under illumination at low voltages. It is well-known that  $\text{Cu}_2\text{O}$  suffers from poor stability under illumination. The photogenerated electrons reduce  $\text{Cu}_2\text{O}$  into Cu and photogenerated holes oxidize  $\text{Cu}_2\text{O}$  into  $\text{CuO}$ . When oxidized, the illuminated area rapidly turning black. Various attempts have been made to solve this problem<sup>38–41</sup>, but the stability of  $\text{Cu}_2\text{O}$  under low bias is rarely mentioned because of too low photocurrents. However, in the presence of the NiFe-LDH co-catalyst, the photostability of  $\text{Cu}_2\text{O}$  under low bias can be explored. Observations indicate that  $\text{Cu}_2\text{O}$  instability is mostly caused by the highly negative applied voltage, under which electrons that accumulate at the photocathode reduce  $\text{Cu}_2\text{O}$  into metallic copper (Figure S13). The testing conditions in the literature are usually under  $\sim 0$  V vs RHE<sup>17</sup>, under which environment  $\text{Cu}_2\text{O}$  tends to be reduced to a most stable state – metallic Cu. Whereas, our testing condition is  $-0.2$  V vs Ag/AgCl under pH 6.5, which fell exactly in its stable condition range. This is supported by the fact that  $\text{Cu}_2\text{O}$  samples under  $-0.2$  V vs Ag/AgCl is also surprisingly stable after 40 hours of continuous illumination (Fig. 5). The stability tests of  $\text{Cu}_2\text{O}$  with and without NiFe-LDH under  $-0.6$  V vs Ag/AgCl show that NiFe-LDH also lengthens the stability of  $\text{Cu}_2\text{O}$  under relatively high voltage (Figure S14). Whereas, the purpose of this study to improve  $\text{Cu}_2\text{O}$  photocathode's performance under its stable condition (green shadowed area in Figure S13) instead of spend numerous efforts in improving its stability under extreme conditions such as under strong negative bias.

**$\text{H}_2$  production.**  $\text{H}_2$  evolution tests using  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  (20 s) photocathodes have been conducted in a 25% methanol solution as a sacrificial reagent under visible light irradiation according to literature<sup>42</sup>. The faradaic efficiency is calculated according to  $\rho = n_{\text{H}_2}/(Q/2F)$ , where  $n_{\text{H}_2}$  is the amount of hydrogen generated,  $Q$  is the total amount of charge passed through the cell (C), and  $F$  is the faraday constant. As shown in Fig. 6, under low bias

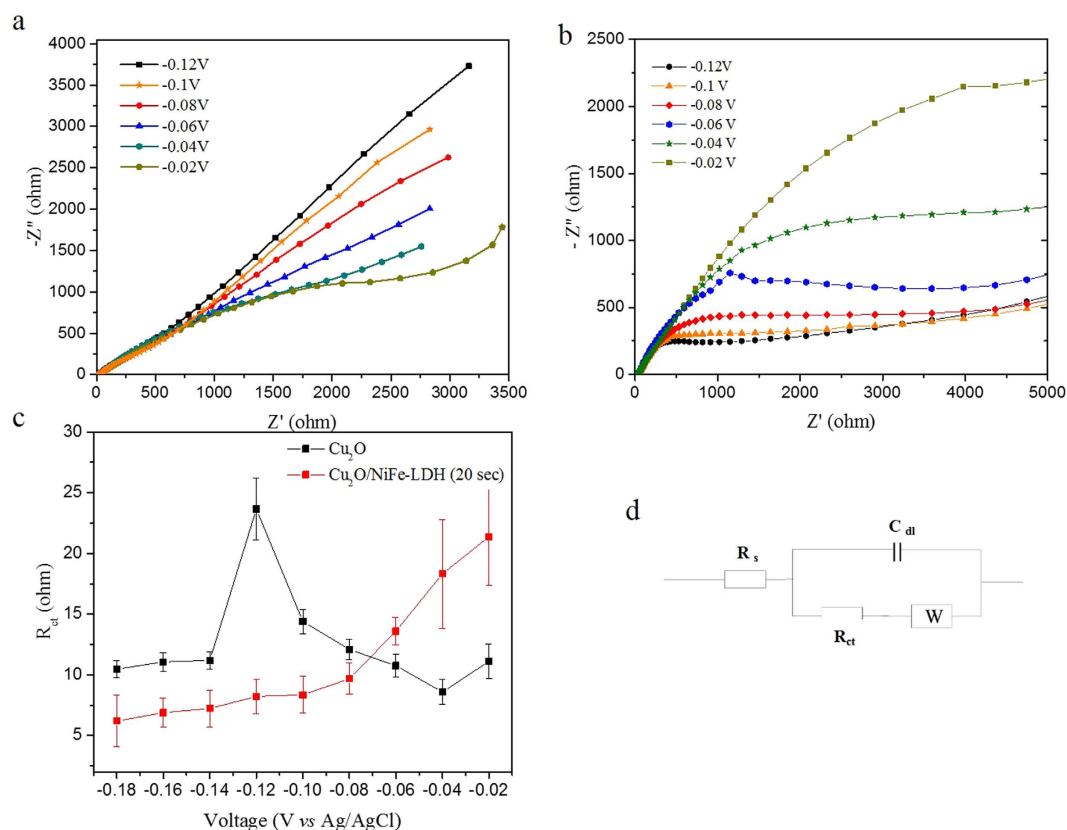


**Figure 3.** Electrochemical impedance spectroscopy of (a)  $\text{Cu}_2\text{O}$  and (b)  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  (20s) electrodes under different external biases. (c) Voltage dependence of the resistance  $R_{ct}$  of  $\text{Cu}_2\text{O}$  and  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  electrodes using the equivalent circuit shown in (d).

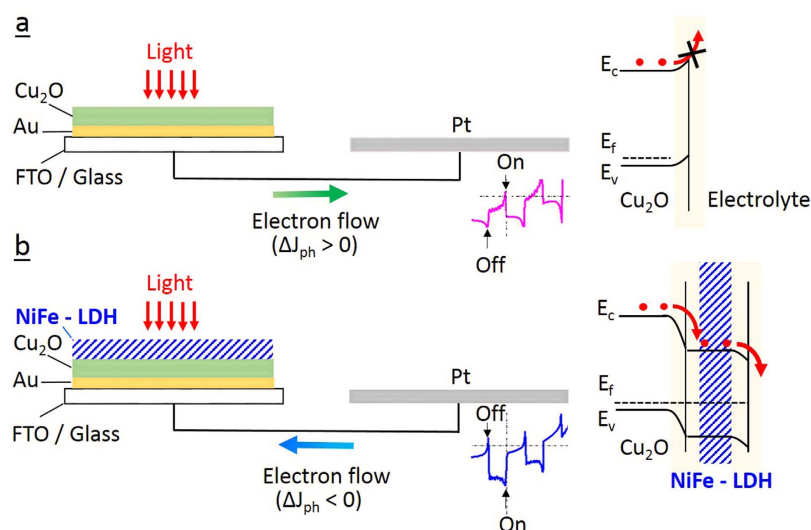


**Figure 4.** Schematics of photogenerated electron transfer occurring in a PEC system using (a) bare  $\text{Cu}_2\text{O}$  and (b) modified  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  (20s) electrodes. The reversal of the electron flow at low voltages is indicated as well as the corresponding band diagrams (red dots denote electrons).

−0.2 V vs Ag/AgCl, the initial faradaic efficiency is 61%, and it increases with time up to 78% before decreasing slowly after 800 minutes of illumination. There is no significant decrease in the performance during the first 12 hours. Over the following 10 hours the efficiency slightly decreases to 59%. When a higher bias of −0.8 V vs Ag/AgCl is applied, it shows good  $\text{H}_2$  evolution in the first 40 minutes. However, after 60 minutes  $\text{H}_2$  stops evolving and a progressive decrease of the faradaic efficiency takes place to become less than 5% after 1,000 minutes of illumination.

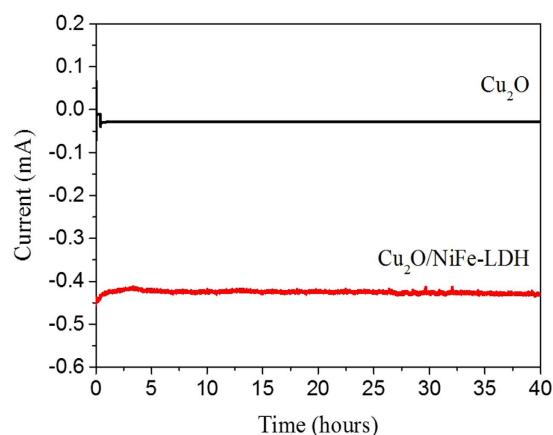

**Figure 5.** Long-term photostability of bare  $\text{Cu}_2\text{O}$  (black curve) and  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  (20 s) (red curve) electrodes under white light illumination and  $-0.2\text{ V}$  vs  $\text{Ag}/\text{AgCl}$  external voltage.

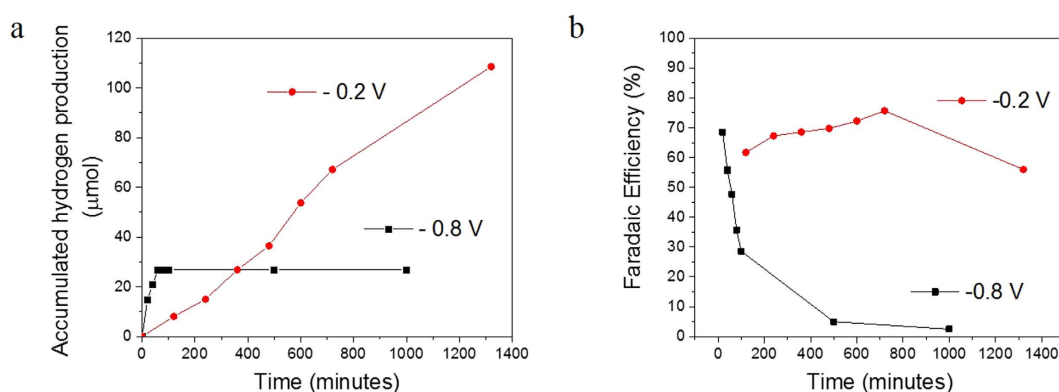

**Figure 6.** (a) Hydrogen production and (b) faradaic efficiency of a PEC system using  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  (20 s) as the working electrode under applied voltages of  $-0.2\text{ V}$  vs  $\text{Ag}/\text{AgCl}$  (red curves) and  $-0.8\text{ V}$  vs  $\text{Ag}/\text{AgCl}$  (black curves).

## Conclusions

The growth of an ultrathin NiFe-LDH co-catalyst on  $\text{Cu}_2\text{O}$  electrodes by electrodeposition induces a remarkable seven-fold increase of the photocurrent density under low applied voltages (typically  $0.49\text{ mA}\cdot\text{cm}^{-2}$  at  $-0.25\text{ V}$  vs  $\text{Ag}/\text{AgCl}$ , as compared to  $0.07\text{ mA}\cdot\text{cm}^{-2}$  for bare  $\text{Cu}_2\text{O}$ ). Electrochemical impedance spectroscopy reveals that NiFe-LDH (20 s) considerably reduces the  $\text{Cu}_2\text{O}$  surface resistance thus allowing photogenerated electrons to be efficiently transported and injected into the electrolyte. Both results are induced by the appropriate band alignment induced by NiFe-LDH. When coated with NiFe-LDH (20 s) as a co-catalyst, the  $\text{Cu}_2\text{O}$  photocathodes generate negative photocurrents with an excellent stability over 40 hours of continuous visible illumination under an external bias of  $-0.2\text{ V}$  vs  $\text{Ag}/\text{AgCl}$ . In  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  (20 s) photocathodes, the combination of high photocurrents and long-term stability under low voltage allow hydrogen evolution. After 8 hours of continuous illumination,  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  photocathodes exhibit a 78% Faradaic efficiency under  $-0.2\text{ V}$  vs  $\text{Ag}/\text{AgCl}$ , while the efficiency drops down to only 5% under  $-0.8\text{ V}$  vs  $\text{Ag}/\text{AgCl}$ . These results demonstrate that modified  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  photoelectrodes are well-adapted to low-biased or self-biased PEC systems in view of artificial photosynthesis.

## Methods

**Preparation of  $\text{Cu}_2\text{O}$  photocathodes.** Prior to the deposition, 50 nm Au was deposited on FTO glasses via e-beam deposition to ensure the conductivity and reproducibility of the samples. Electrodeposition of  $\text{Cu}_2\text{O}$  was carried out in a basic solution of lactate-stabilized copper sulfate consisting in  $0.2\text{ M}$   $\text{CuSO}_4$  (Sigma Aldrich) and  $3\text{ M}$  lactic acid (Fisher Scientific) solution in deionized water. Afterward,  $1\text{ M}$  NaOH was added to adjust the solution pH to 12. The basic environment ensures that deposited  $\text{Cu}_2\text{O}$  is of p-type conduction. During deposition, the temperature was kept constant at  $40^\circ\text{C}$  using a hot plate. The  $\text{Cu}_2\text{O}$  thin films were deposited at a constant current density of  $-1\text{ mA}\cdot\text{cm}^{-2}$  vs  $\text{Ag}/\text{AgCl}$  reference electrode using a three-electrode system (galvanostatic mode, Gamry Instruments, Inc.)

**Electrodeposition of the NiFe-LDH co-catalyst.** Electrodeposition of NiFe-LDH is realized using  $\text{Cu}_2\text{O}$  as the working electrode, together with a Pt counter-electrode and Ag/AgCl as the reference electrode. The solution for electrodeposition of NiFe-LDH consists in a mixture of 0.2 M  $[\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}]$  and 0.1 M  $[\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}]$  in 50 ml of deionized water. A constant potential of  $-1.0\text{ V}$  vs Ag/AgCl is applied during various periods of time in the range 20–300 s, leading to different morphologies. For less than 60 s, NiFe-LDH does not reveal a clear nanoflake morphology, although photocurrent is already improved as compared with bare  $\text{Cu}_2\text{O}$ . A 150 s deposition time is required to obtain visible XRD peaks due to the intensity limit.

**Morphological characterizations.** The crystal phase of the synthesized photocathodes were studied using a Shimadzu thin film X-ray diffractometer with a Cu K $\alpha$  excitation ( $\lambda = 1.54\text{ \AA}$ ). Microscopic morphologies including lattice analysis of scraped particles were obtained using field emission scanning electron microscopy (FESEM, JEOL JSM-7600F) and high resolution transmission electron microscopy (HRTEM, JEOL-2100F) operating at 200 kV.

**Photoelectrochemical measurements.** All PEC measurements were conducted in a 0.5 M  $\text{Na}_2\text{SO}_4$  electrolyte using a three-electrode configuration with synthesized sample as the working electrodes, Pt and Ag/AgCl electrodes being used as the counter and reference electrodes, respectively. The inter-electrode spacing was  $\sim 1\text{ cm}$ . Photocurrents were recorded using a PCI4/300<sup>TM</sup> potentiostat equipped with PHE200<sup>TM</sup> software (Gamry Instruments, Inc.). The working electrodes were exposed to the AM 1.5 light from a solar simulator equipped with a 300 W Xe-lamp (HAL-320, Asahi Spectra Co., Ltd.). The incident light intensity was  $100\text{ mW}\cdot\text{cm}^{-2}$  and the sample illumination area  $0.28\text{ cm}^2$ . Linear sweep voltammetry (LSV) was carried out under both dark and illumination conditions with a scan rate of  $5\text{ mV}\cdot\text{s}^{-1}$  with chopped light irradiation (frequency = 0.2 Hz). Stability tests were conducted by chronoamperometry under a potential of  $-0.2\text{ V}$  vs Ag/AgCl in a 0.5 M  $\text{Na}_2\text{SO}_4$  solution. Mott-Schottky measurements were conducted using the same equipment and configuration with Mott-Schottky mode in 0.5 M  $\text{Na}_2\text{SO}_4$  electrolyte with a frequency of 300 Hz in the potential range of chemical stability. Cyclic voltammetry (CV) was carried out using the same equipment and configuration in 0.5 M  $\text{Na}_2\text{SO}_4$  electrolyte at the potential window 0.3 V to  $-0.4\text{ V}$  vs Ag/AgCl with scan rate of  $100\text{ mV}\cdot\text{s}^{-1}$ .

**Electrochemical impedance spectroscopy.** Electrochemical impedance spectroscopy (EIS) was conducted using the same equipment and configuration as for the PEC measurements, which is a PCI4/300<sup>TM</sup> potentiostat equipped with EIS300<sup>TM</sup> software (Gamry Instruments, Inc.). Potentiostatic mode was applied under white light illumination (AM1.5,  $100\text{ mW}\cdot\text{cm}^{-2}$ ) at an applied voltage of  $-0.2\text{ V}$  vs. Ag/AgCl. AC perturbations of amplitude 5 mV were superimposed with frequency in the range 0.01–100 kHz. Equivalent circuit modeling and curve fitting were performed using the Echem Analyst<sup>TM</sup> software (Gamry Instruments, Inc.)

**Hydrogen production.** The amount of hydrogen generated was measured using a well-sealed glass cell (100 ml) mounted with a quartz window. The  $\text{Cu}_2\text{O}$  and  $\text{Cu}_2\text{O}/\text{NiFe-LDH}$  working electrodes (sample illumination area =  $1\text{ cm}^2$ ) were exposed to the light of a solar simulator equipped with a 300 W Xe-lamp (HAL-320, Asahi Spectra Co., Ltd.), and the incident AM 1.5 light intensity was  $100\text{ mW}\cdot\text{cm}^{-2}$ . The working electrode, Pt counter-electrode and Ag/AgCl reference electrode were suspended in a solution (pH = 7) containing 30 ml of 0.1 M  $\text{Na}_2\text{SO}_4$  and 10 ml of methanol (25%). Prior to testing, the reactor was repeatedly vacuum-pumped and purged with argon to remove the residual air. Then, an external bias is applied on the working electrode and the lamp is turned on. The amount of generated  $\text{H}_2$  gas was quantitatively analyzed by a gas chromatograph (Shimadzu GC-2014; molecular sieve 5  $\text{\AA}$ , TCD detector, Ar carrier gas).

## References

- Fujishima, A. & Honda, K. Electrochemical Photolysis of Water at a Semiconductor Electrode. *Nature* **238**, 37–39 (1972).
- Robel, I., Subramanian, V., Kuno, M. & Kamat, P. V. Quantum dot solar cells. Harvesting light energy with CdSe nanocrystals molecularly linked to mesoscopic  $\text{TiO}_2$  films. *J Am Chem Soc* **128**, 2385–2393 (2006).
- Stergiopoulos, T., Arabatzi, I. M., Katsaros, G. & Falaras, P. Binary polyethylene oxide/titania solid-state redox electrolyte for highly efficient nanocrystalline  $\text{TiO}_2$  photoelectrochemical cells. *Nano Lett* **2**, 1259–1261 (2002).
- Yang, X. Y. *et al.* Nitrogen-Doped ZnO Nanowire Arrays for Photoelectrochemical Water Splitting. *Nano Lett* **9**, 2331–2336 (2009).
- Fichou, D. *et al.* Extension of the Photoresponse of Semiconducting Zinc-Oxide Electrodes by 3d-Impurities Absorbing in the Visible Region of the Solar Spectrum. *J Electroanal Chem* **188**, 167–187 (1985).
- Jakani, M. *et al.* Photoelectrochemical Properties of Zinc-Oxide Doped with 3d Elements. *J Solid State Chem* **56**, 269–277 (1985).
- Cao, L. L., Yuan, J., Chen, M. X. & Shanguan, W. F. Photocatalytic energy storage ability of  $\text{TiO}_2\text{-WO}_3$  composite prepared by wet-chemical technique. *J Environ Sci-China* **22**, 454–459 (2010).
- Wang, G. M. *et al.* Solar driven hydrogen releasing from urea and human urine. *Energ Environ Sci* **5**, 8215–8219 (2012).
- Qin, D. D. *et al.* Dense layers of vertically oriented  $\text{WO}_3$  crystals as anodes for photoelectrochemical water oxidation. *Chem Commun* **48**, 729–731 (2012).
- Qi, H. *et al.* Triple-layered nanostructured  $\text{WO}_3$  photoanodes with enhanced photocurrent generation and superior stability for photoelectrochemical solar energy conversion. *Nanoscale* **6**, 13457–13462 (2014).
- Liu, C. J. *et al.* In situ synthesis of  $\text{Bi}_2\text{S}_3$  sensitized  $\text{WO}_3$  nanoplate arrays with less interfacial defects and enhanced photoelectrochemical performance. *Sci Rep-Uk* **6** (2016).
- Cesar, I., Kay, A., Martinez, J. A. G. & Gratzel, M. Translucent thin film  $\text{Fe}_2\text{O}_3$  photoanodes for efficient water splitting by sunlight: Nanostructure-directing effect of Si-doping. *J Am Chem Soc* **128**, 4582–4583 (2006).
- McShane, C. M. & Choi, K. S. Photocurrent Enhancement of n-Type  $\text{Cu}_2\text{O}$  Electrodes Achieved by Controlling Dendritic Branching Growth. *J Am Chem Soc* **131**, 2561–2569 (2009).
- Minguez-Bacho, I., Courte, M., Fan, H. J. & Fichou, D. Conformal  $\text{Cu}_2\text{S}$ -coated  $\text{Cu}_2\text{O}$  nanostructures grown by ion exchange reaction and their photoelectrochemical properties. *Nanotechnology* **26**, 185401–185411 (2015).
- Kang, Z. *et al.* Electronic Structure Engineering of  $\text{Cu}_2\text{O}$  Film/ $\text{ZnO}$  Nanorods Array All-Oxide p-n Heterostructure for Enhanced Photoelectrochemical Property and Self-powered Biosensing Application. *Sci Rep-Uk* **5** (2015).
- Luo, W. J. *et al.* Solar hydrogen generation from seawater with a modified  $\text{BiVO}_4$  photoanode. *Energ Environ Sci* **4**, 4046–4051 (2011).



17. Paracchino, A., Laporte, V., Sivula, K., Gratzel, M. & Thimsen, E. Highly active oxide photocathode for photoelectrochemical water reduction. *Nat Mater* **10**, 456–461 (2011).
18. Yang, L. X. *et al.* High Efficient Photocatalytic Degradation of p-Nitrophenol on a Unique Cu<sub>2</sub>O/TiO<sub>2</sub> p-n Heterojunction Network Catalyst. *Environ Sci Technol* **44**, 7641–7646 (2010).
19. Wu, L. L., Tsui, L. K., Swami, N. & Zangari, G. Photoelectrochemical Stability of Electrodeposited Cu<sub>2</sub>O Films. *J Phys Chem C* **114**, 11551–11556 (2010).
20. Paracchino, A., Brauer, J. C., Moser, J. E., Thimsen, E. & Graetzel, M. Synthesis and Characterization of High-Photoactivity Electrodeposited Cu<sub>2</sub>O Solar Absorber by Photoelectrochemistry and Ultrafast Spectroscopy. *J Phys Chem C* **116**, 7341–7350 (2012).
21. Zhang, Z. H. & Wang, P. Highly stable copper oxide composite as an effective photocathode for water splitting via a facile electrochemical synthesis strategy. *J Mater Chem* **22**, 2456–2464 (2012).
22. Wijesundera, R. P., Solar Cells - Thin-Film Technologies, L. A. Kosyachenko (Ed.), 2011, ISBN: 978-953-307-570-9.
23. Wang, M. Y. *et al.* p-n Heterojunction photoelectrodes composed of Cu<sub>2</sub>O-loaded TiO<sub>2</sub> nanotube arrays with enhanced photoelectrochemical and photoelectrocatalytic activities. *Energy Environ Sci* **6**, 1211–1220 (2013).
24. Tilley, S. D., Schreier, M., Azevedo, J., Stefik, M. & Graetzel, M. Ruthenium Oxide Hydrogen Evolution Catalysis on Composite Cuprous Oxide Water-Splitting Photocathodes. *Adv Funct Mater* **24**, 303–311 (2014).
25. Zhang, Y. Z. *et al.* Photovoltaic performance enhancement of Cu<sub>2</sub>O photocathodes by electrostatic adsorption of polyoxometalate on Cu<sub>2</sub>O crystal faces. *Rsc Adv* **4**, 1362–1365 (2014).
26. Sideris, P. J., Nielsen, U. G., Gan, Z. H. & Grey, C. P. Mg/Al ordering in layered double hydroxides revealed by multinuclear NMR spectroscopy. *Science* **321**, 113–117 (2008).
27. Fan, G. L., Li, F., Evans, D. G. & Duan, X. Catalytic applications of layered double hydroxides: recent advances and perspectives. *Chem Soc Rev* **43**, 7040–7066 (2014).
28. Liu, J. P., Li, Y. Y., Huang, X. T., Li, G. Y. & Li, Z. K. Layered double hydroxide nano- and microstructures grown directly on metal substrates and their calcined products for application as Li-ion battery electrodes. *Adv Funct Mater* **18**, 1448–1458 (2008).
29. Lu, Z. *et al.* Three-dimensional NiFe layered double hydroxide film for high-efficiency oxygen evolution reaction. *Chem Commun* **50**, 6479–6482 (2014).
30. Gong, M. *et al.* An Advanced Ni-Fe Layered Double Hydroxide Electrocatalyst for Water Oxidation. *J Am Chem Soc* **135**, 8452–8455 (2013).
31. Li, X. D., Yang, W. S., Li, F., Evans, D. G. & Duan, X. Stoichiometric synthesis of pure NiFe<sub>2</sub>O<sub>4</sub> spinel from layered double hydroxide precursors for use as the anode material in lithium-ion batteries. *J Phys Chem Solids* **67**, 1286–1290 (2006).
32. Zheng, S. F. *et al.* An Inexpensive Co-Intercalated Layered Double Hydroxide Composite with Electron Donor-Acceptor Character for Photoelectrochemical Water Splitting. *Sci Rep-Uk* **5** (2015).
33. Shao, M. F., Ning, F. Y., Wei, M., Evans, D. G. & Duan, X. Hierarchical Nanowire Arrays Based on ZnO Core-Layered Double Hydroxide Shell for Largely Enhanced Photoelectrochemical Water Splitting. *Adv Funct Mater* **24**, 580–586 (2014).
34. Xu, D., Rui, Y., Li, Y., Zhang, Q. & Wang, H. Zn-Co layered double hydroxide modified hematite photoanode for enhanced photoelectrochemical water splitting. *Appl Surf Sci* **358**, 436–442 (2015).
35. Newman, S. P., Jones, W., O'Connor, P. & Stamiros, D. N. Synthesis of the 3R(2) polytype of a hydrotalcite-like mineral. *J Mater Chem* **12**, 153–155 (2002).
36. Hansen, H. C. B., Koch, C. B. & Taylor, R. M. Synthesis and Characterization of Cobalt(II)-Iron(III) Hydroxide Carbonate, a Layered Double Hydroxide Belonging to the Pyroaurite Group. *J Solid State Chem* **113**, 46–53 (1994).
37. Zang, J. F. *et al.* Well-aligned cone-shaped nanostructure of polypyrrole/RuO<sub>2</sub> and its electrochemical supercapacitor. *J Phys Chem C* **112**, 14843–14847 (2008).
38. Juodkazyte, J. *et al.* Study on copper oxide stability in photoelectrochemical cell composed of nanostructured TiO<sub>2</sub> and Cu<sub>2</sub>O electrodes. *Electrochim Acta* **137**, 363–371 (2014).
39. Paracchino, A. *et al.* Ultrathin films on copper(I) oxide water splitting photocathodes: a study on performance and stability. *Energy Environ Sci* **5**, 8673–8681 (2012).
40. Morales-Guio, C. G. *et al.* Photoelectrochemical Hydrogen Production in Alkaline Solutions Using Cu<sub>2</sub>O Coated with Earth-Abundant Hydrogen Evolution Catalysts. *Angew Chem Int Edit* **54**, 664–667 (2015).
41. Zhao, Y. X. *et al.* Hierarchical branched Cu<sub>2</sub>O nanowires with enhanced photocatalytic activity and stability for H<sub>2</sub> production. *Nanoscale* **6**, 195–198 (2014).
42. Wick, R. & Tilley, S. D. Photovoltaic and Photoelectrochemical Solar Energy Conversion with Cu<sub>2</sub>O. *J Phys Chem C* **119**, 26243–26257 (2015).

## Acknowledgements

The authors wish to thank the support from the Ministry of Education in Singapore under the AcRF Tier2 grant (MOE2014-T2-1-132) and from the National Research Foundation (NRF) Singapore through its Campus for Research Excellence and Technological Enterprise (CREATE) program.

## Author Contributions

H.Q. and J.W. conceived, designed and performed the experiments. H.Q., J.W., D.F. and Z.C. analyzed the data. H.Q. and D.F. co-wrote the paper. Z.C. provides guidance and revises the manuscript. All authors discussed the results and reviewed the manuscript.

## Additional Information

**Supplementary information** accompanies this paper at <http://www.nature.com/srep>

**Competing financial interests:** The authors declare no competing financial interests.

**How to cite this article:** Qi, H. *et al.* Cu<sub>2</sub>O Photocathode for Low Bias Photoelectrochemical Water Splitting Enabled by NiFe-Layered Double Hydroxide Co-Catalyst. *Sci. Rep.* **6**, 30882; doi: 10.1038/srep30882 (2016).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>