



HAL
open science

Method for determining the polymer content in non soluble polydiacetylene films – application to pentacosadiynoic acid

Sylvie Spagnoli, Emrick Briand, Ian Vickridge, Jean-Louis Fave, Michel Schott

► To cite this version:

Sylvie Spagnoli, Emrick Briand, Ian Vickridge, Jean-Louis Fave, Michel Schott. Method for determining the polymer content in non soluble polydiacetylene films – application to pentacosadiynoic acid. *Langmuir*, 2017, 33 (6), pp.1419-1426. 10.1021/acs.langmuir.6b03147 . hal-01449784

HAL Id: hal-01449784

<https://hal.sorbonne-universite.fr/hal-01449784>

Submitted on 30 Jan 2017

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

1
2
3
4 Method for determining the polymer content in non
5
6
7
8 soluble polydiacetylene films – application to
9
10
11
12
13 pentacosadiynoic acid.
14
15
16
17

18 *Sylvie Spagnoli^{*,†,‡}, Emrick Briand^{§,1}, Ian Vickridge^{§,1}, Jean-Louis Fave^{§,1}, Michel Schott^{§,1}*
19

20
21 [†]Université Grenoble Alpes, LIPHY, F-38000 Grenoble, France
22

23
24 [‡]CNRS, UMR5588, LIPHY, F-38000 Grenoble, France
25
26

27
28 [§]Sorbonne Universités, UPMC Univ Paris 06, UMR7588, INSP, F-75005 Paris, France
29
30

31 ¹CNRS, UMR7588, Institut des NanoSciences de Paris (INSP), F-75005 Paris, France
32
33
34
35
36
37

38 KEYWORDS: Polydiacetylenes, Nuclear Reaction Analysis, Polymer content, incomplete
39
40 photopolymerization.
41
42
43

44 ABSTRACT: The absorptivities of polydiacetylenes (PDA) used in Langmuir films or vesicles for the
45
46 development of PDA sensors films or other applications such as in non linear optics or for field-effect
47
48 transistors are not known, so polymer contents cannot be deduced from experimental spectra. Here we
49
50 introduce a novel method, using Nuclear Reaction Analysis (NRA) that allows quantitative
51
52 determination of the polymer content X proportion of monomers that have been incorporated into PDA
53
54 chains. We apply it to pentacosadiynoic acid (PCDA) evaporated microcrystalline films. A calibration
55
56 curve giving X as a function of the area under an absorption spectrum normalized to the monomer areal
57
58
59
60

1 density is obtained for blue and red PCDA. The method is applicable to all kinds of films, and to other
2 PDA, provided films with known molecular areal density are available. An example of application to a
3 PCDA Langmuir film is given.
4
5
6
7

8 MAIN_TEXT

9 1 Introduction: motivation for this study.

10
11 The development of this method was initially motivated by the extensive current work on
12 possible biological or environmental sensors based on the color transition of polydiacetylenes
13 (PDA) in Langmuir films or vesicles, as discussed in several recent reviews [1-4]. Its application
14 to Langmuir films will be illustrated in § 3-4. But it should be stressed that the method is general,
15 applicable in principle to other types of films used in other types of studies or applications. For
16 instance, PDA films and in particular films of PCDA or similar molecules, have been used in
17 Field-Effect Transistors using Langmuir Blodgett (LB) films [5], or evaporated films [6] and
18 even monomolecular films [5]. The present results can be used to determine the actual polymer
19 content in such devices.
20
21
22
23
24
25
26
27
28
29
30
31
32
33

34
35 PDA chains, of monomer general formula $R'C\equiv C-C\equiv CR$ where R and R' are side groups
36 which may have widely different molecular formulas, can exist in at least two different
37 electronic structures conventionally named the Blue (B) and Red (R) forms. B-type chains have a
38 maximum absorption near $\lambda_{\max} \approx 640$ nm and are not fluorescent (with a quantum yield at room
39 temperature of the order of 10^{-5} [7]), while R-type chains have a λ_{\max} often near 540 nm, but it
40 may be as high as 580 nm [10] or as low as 520 nm [11], and they are fluorescent, albeit weakly
41 (quoted yield [10] 0.02), at room temperature [11-13].
42
43
44
45
46
47
48
49
50

51
52 A first order transition between B and R forms is observed in many crystalline DA and in
53 Langmuirs films or vesicles. This transition is called "color transition" and it is the basis of
54 sensor operation. This transition is often, but not always, irreversible. It can be triggered by
55 various means, such as temperature or pressure. It also sometimes occurs during polymerization.
56
57
58
59
60

1
2
3 In the case of sensor applications, it is triggered by the binding of the species to be detected
4 (molecule, ion, or a biological macromolecule) onto a selective group bound at the end of some
5
6 of the DA molecules forming the film. For instance, in the paper which, as far as we know,
7
8 initiated this type of research, an influenza virus was detected [14]. Note that the microscopic
9
10 mechanism by which the transition is produced remains under debate. It was initially thought
11
12 that the color change which results from a geometrical change of the PDA chain, was an order-
13
14 disorder transition. However, perfectly ordered red chains are now known [15] with a room
15
16 temperature absorption spectrum identical to that of red Langmuir films. So it seems more likely
17
18 that red chains are ordered but not planar, having a twist similar to that known in several red
19
20 PDA single crystals such as poly-THD [16, 17]. This is discussed in [18] following previous
21
22 similar proposals [19, 20], but the question is not completely settled.
23
24
25
26
27
28

29 The sensor can be used to simply verify the presence of an analyte or for quantitative
30
31 measurements. In film form, they are generally prepared as monolayer Langmuir films of the
32
33 monomer which are then transferred onto a suitable solid substrate by various methods [21, 22].
34
35 Photopolymerization can be carried out either in the Langmuir trough or after transfer, and can
36
37 easily be monitored spectroscopically, as can the color transition, since PDA of both B and R
38
39 forms strongly absorb in the visible (examples of spectra are given Figure 1). It is often observed
40
41 that the B-R transition occurs spontaneously at some stage during photopolymerization [23-25]
42
43 while for sensor use it is obviously required that the film still be in the blue phase, so for use as a
44
45 sensor irradiation must be stopped before onset of the color transition, at partial polymerization.
46
47 Moreover the question of the polymer content is usually not mentioned, and when it is, the
48
49 polymerization is assumed to stop at completion [26, 27]. Unfortunately, we have shown
50
51
52
53
54
55
56
57
58
59
60

1
2
3 previously that, at least in the case of poly4BCMU, the reaction practically stops around 50%
4
5 [28].
6
7

8 It would be useful to be able to deduce a film's polymer content at any stage of the
9 polymerization, for any polymer color, from an experimental absorption spectrum.
10 Unfortunately, the absorptivity of the PDA used in these applications is generally unknown (this
11 is so for the most used materials in sensors, pentacosadiynoic acid or tricosadiynoic acid and
12 their derivatives), so absorption spectra do not allow calculation of the polymer content X of the
13 film. X is the fraction of the total mass which is polymerized. This is also the ratio of number of
14 monomers that have been incorporated in a chain to the initial total number of monomer, since
15 the reaction occurs with no loss of atoms. Indeed, these PDAs are generally totally insoluble, so
16 the method that has been used to determine the absorptivities of the few soluble PDAs and which
17 requires calibration via a solution [28,29], cannot be used.
18
19
20
21
22
23
24
25
26
27
28
29
30

31 The motivation of the present work is therefore to develop a method, applicable to any PDA,
32 for determination of absolute absorptivity, so as to provide a simple method for deducing X in
33 any type of film from quantities easily read on an absorption spectrum, both in the B and R
34 forms. This method uses NRA (Nuclear Reaction Analysis see Supporting information F) in a
35 way that has never been used before. This method allows a quantitative measurement of the areal
36 density of one type of atoms (in our case Carbon) in a film. It is generally used for determination
37 of areal densities of other types of atoms such as oxygen in inorganic films for instance in
38 microelectronics.
39
40
41
42
43
44
45
46
47
48
49

50 The paper is organized as follows: in §2 the sample preparation and the different techniques
51 used are described. In §3.1 the principle of the NRA method and its implementation are
52 presented. In order to validate the method, it is applied in §3.2 to a soluble PDA, poly-4BCMU,
53
54
55
56
57
58
59
60

1
2
3 for which absorptivity has been determined previously [28, 29], showing that the method indeed
4 yields the correct absorptivities. Blue and red pentacosadiynoic acid (referred to below as PCDA,
5 an often used acronym in the literature) is then studied in §3.3, and in §3.4 means are given to
6 deduce a polymer content X from quantities read on an experimental absorption spectrum
7 obtained in the case of PCDA Langmuir films.
8
9

10 11 12 13 14 15 2 Materials and methods

16 17 18 2.1 Materials

19
20 4BCMU monomer was synthesized in the laboratory by the standard method [30] and purified
21 by column chromatography. 10-12 pentacosadiynoic acid was purchased from Aldrich and used
22 without further purification except removal of residual polymer by filtration of solutions used for
23 Langmuir films preparation. The molecular structure and the polymerization scheme are given in
24 Supporting Information A and B.
25
26
27
28
29
30

31 32 2.2 Sample preparation.

33
34 *Polycrystalline thin films:* (thickness from 30 to 250 nm) were prepared by vacuum
35 evaporation of the monomer from a quartz crucible on 15mm x15mm precleaned glass
36 substrates using a home-made evaporation chamber at a base pressure of $1.0 \pm 0.2 \cdot 10^{-7}$ Torr.
37 Glass was cleaned using the previously described protocol [28]. Deposited mass was measured
38 by a quartz microbalance (Maxtek, model TM-350). Since the quartz is not positioned exactly at
39 the same place as the substrates, the ratio of the deposition rates (tooling factor) was calculated
40 geometrically.
41
42
43
44
45
46
47
48
49

50
51 In each evaporation 4 films were simultaneously prepared. To make sure that they would be
52 identical, the sample holder was rotated around a central vertical axis (period ≈ 2 s). Similar
53 deposition rates of 14 ± 2 Å/s and substrate temperatures of 20°C were chosen in all cases. This
54
55
56
57
58
59
60

1
2
3 ensures the same balance between nucleation and growth of the crystallites, leading to the same
4 crystallite size range. An AFM image is shown in Supporting Information C. After preparation
5
6 the samples were kept at -20°C in the dark until use.
7
8
9

10 In each set of 4 films, one was kept unirradiated to serve as a reference for film thickness as
11 measured by Nuclear Reaction Analysis NRA (see below) and the others were
12 photopolymerized.
13
14
15

16
17 *Langmuir films:* Concentration of spreading solutions is typically 2×10^{-3} mol/L in
18 chloroform. A few microliters of the solution were deposited onto the air/liquid interface of a
19 Langmuir trough equipped with a double movable barrier for film compression. The surface
20 pressure was measured according to the Wilhelmy plate method. The plate was made of filter
21 paper and the measurement device was a microbalance from Riegler&Kirstein GmbH
22 (Germany). The subphase consisted of Milli-Q Millipore ultrapure water (18.2 M Ω ·cm). The
23 temperature was regulated at $\pm 0.5^\circ\text{C}$ using a circulating water bath. All isotherms were
24 performed at a constant compression speed of 9 $\text{\AA}^2/\text{mol}/\text{min}$. The typical duration of a
25 compression is about 40 min.
26
27
28
29
30
31
32
33
34
35
36
37

38
39 *Polymerization:* For evaporated films, photopolymerization was carried out either at 254 nm
40 (bandwidth 5 nm) in a Cary 5000 spectrometer for small polymer content, or in a home-made
41 irradiator using a high pressure Xe lamp (Oriel), a water filter to absorb unwanted IR light and a
42 45° dielectric mirror for unpolarized light (Melles Griot type KRF-2037-45-UNP) to
43 preferentially select the range 230-270 nm. The measured ratio of the polymerization efficiencies
44 of the two methods is about 60, with 1 hour in the Cary is approximately equivalent to 1 minute
45 in front of the Xe lamp. A low pressure Hg lamp (100W – Ulice optronique) essentially emitting
46 the 254 nm line was used for in situ polymerization of Langmuir films. The used wavelengths
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 are exclusively absorbed by the DA group, other parts of the molecules only absorb at
4
5 significantly shorter wavelengths.
6

7
8 *Removal of residual monomer:* At the end of the irradiation, films still contain between 30 and
9
10 90 % monomer, which has to be removed before the NRA experiment, without removing any
11
12 polymer. Two methods were tested: high temperature evaporation under vacuum or selective
13
14 dissolution at room temperature in an appropriate solvent. They gave identical results, but there
15
16 is a risk of incipient degradation of the polymer at high temperature which would affect the use
17
18 of red spectra for determination of polymer as described below. So all data presented here used
19
20 the dissolution method. Note that dissolution of residual monomer has been a standard method
21
22 for determining the polymer concentration in a partially polymerized samples (crystal, powdered
23
24 film) [31-35], and therefore the polymerization kinetics. Nevertheless, since the method has not
25
26 been specifically validated for PCDA, its validity was checked as detailed in Supporting
27
28 Information D.
29
30
31
32

33
34
35 Removal of some polymer (for instance relatively short oligomers if any are formed) could be
36
37 a problem with the dissolution method. But comparison with the results of removal by
38
39 evaporation, where no polymer is evaporated, showed this not to be the case. Also, the solvents
40
41 used for dissolution remained colorless.
42
43

44
45 For dissolution, a glass slide covered with a film was put in a Petri dish and solvent was
46
47 carefully added until the slide was covered under several millimeters of solvent. To determine
48
49 the optimum procedure leading to total dissolution of the monomer several groups of identical
50
51 samples were tested varying one parameter at a time: time of contact with the solvent and choice
52
53 of the solvent. Acetone is a good solvent of both monomers, but it does not wet 4BCMU well, so
54
55 capillary forces might degrade the film; therefore the following procedure was used. The slide is
56
57
58
59
60

1
2
3 first immersed in n-Hexane, a solvent of both monomers chosen for its low surface energy; about
4
5 twice as much acetone is then carefully added and the dish is repeatedly gently agitated for 1
6
7
8 hour at room temperature. It was checked that the same results were found after 10 minutes of
9
10 contact and this was taken as indicating that at 1 hour complete monomer dissolution is achieved.
11
12 More details are given in Supporting Information D.

13
14
15 Before dissolution of residual monomer all polymer chains were in the blue phase, whatever
16
17 the polymer content. After, they were all red (see Figure 1), in the process the polymer chains
18
19 undergo the blue to red phase transition. In fact in 4BCMU and PCDA the blue polymer phase is
20
21 a metastable one which transforms into the stable red one thanks to the free volume generated by
22
23 dissolution of the monomer. As we will see in §2.3 this conformational transition has no
24
25 influence on the NRA experiment, only the number of carbon atoms is determined and this
26
27 transition does not change this number. The aim of the method is to create a calibration curve
28
29 giving the polymer content versus an easy to read parameter on an absorption spectrum. Thanks
30
31 to this color transition occurring when the monomer is removed, with the same NRA experiment
32
33 two calibration curves can be obtained, one for the B conformation, the other for the R
34
35 conformation as described below in §3.1.

40 41 2.3 Techniques

42
43 *Absorption spectra:* All spectra of evaporated films were taken using a double beam Cary
44
45 5000 spectrometer, typically between 350 and 800 nm: polymer films are transparent beyond 800
46
47 nm, and glass would begin to absorb below 320 nm. Blue polymer absorption is very small
48
49 below 350 nm, and red polymers only show a weak residual absorption there. Since spectra are
50
51 broad a 2 nm resolution was chosen, but it was checked that higher resolution leads to identical
52
53
54
55
56
57
58
59
60

1
2
3 spectra (but with more noise). The final spectrum corresponds to the polymer content to be
4 measured by NRA.
5
6

7
8 For Langmuir films, absorption spectra are obtained in-situ using a bifurcated fiber made of 6
9 illumination fibers connected to a halogen light source (HL2000 Ocean Optics) around a read
10 fiber connected to a UV-Vis spectrometer (Avantes avaspec-2048x64). A mirror is placed in the
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Langmuir trough prior to deposition. The transmitted light is collected, after reflection on the
mirror, via the same optical fiber and analyzed by the spectrometer (see scheme in Supporting
Information E). The reference spectrum is taken on the compressed monomer just before
irradiation.

Nuclear Reaction Analysis (NRA): A general introduction to the method is provided in
Supporting Information F. Measurements were performed in a home-made dedicated vacuum
chamber, using dry pumping to avoid carbon contamination during the experiments, installed at
the Tandem van de Graaff accelerator ALTAIS of the Laboratoire d'Analyses par Réactions
Nucléaires at the University of Namur, Belgium. It delivered stable deuteron beams in the energy
range 850-970 keV used in the experiments. Films were mounted with their surface
perpendicular to the deuteron beam direction, on a sample holder containing typically 20 to 25
samples which could be studied in the same run. NRA is a method for counting carbon atoms,
irrespective of their chemical state. It is also insensitive to the organization and structure of the
studied material. In this way one obtains an areal density of carbon atoms $N_C(\text{cm}^{-2})$ and
molecules $N_m(\text{cm}^{-2})$ in a film. Once this is known, the absorption spectrum of the film can be
used to compute absolute absorptivities, or the area of the absorption spectrum, which is related
to the oscillator strength of the electronic transition corresponding to the absorption.

1
2
3 Here we use the $^{12}\text{C}(\text{d},\text{p}_0)^{13}\text{C}$ nuclear reaction, meaning that the reaction of a deuteron with a
4 ^{12}C nucleus generates a high energy proton which is counted by a suitable detector, and a stable
5 ^{13}C nucleus. Practically, absolute numbers are obtained by comparing the number of detected
6 events for a given deuteron fluence to that of a suitable reference containing a known areal
7 density of atoms, for the same fluence and in the same geometry. But carbon references are not
8 stable enough (they can lose carbon by radiation damage or gain carbon via contamination), so a
9 very stable ^{16}O reference is chosen, using the $^{16}\text{O}(\text{d},\text{p}_1)^{17}\text{O}$ reaction.

10 The cross sections of the two reactions have been determined; they depend on the incident
11 deuteron energy and the geometry used for detection [36]. Here we used the following
12 conditions: energy of the incident deuterons 854 keV for the ^{16}O reaction used for reference, and
13 968 keV for the ^{12}C reaction used for studying the film. These energies were chosen so that the
14 corresponding reaction cross section is only slowly varying in the vicinity of the chosen values,
15 so that small calibration errors of the accelerator energies are irrelevant. The ratio of cross
16 section of these carbon and oxygen nuclear reactions is in these conditions 5.56 [37].

17 Emitted protons (which have high energies) were detected at a 150° scattering angle. Other
18 particles are also emitted in that direction, for instance elastically backscattered deuterons, but
19 their energy is lower. All such particles, but not the protons, were stopped in a 13 microns Mylar
20 film placed in front of the detector. For each measurement, a complete energy spectrum of the
21 detected protons was recorded, and the peak corresponding to the reaction of interest was
22 selected and integrated. In all cases, background counts at the peak positions were negligible.

23 *Application to the present study:* to avoid heating the films, the deuteron beam current was
24 limited to 2-4 nA in a rectangular beam of cross section 2 mm x 2 mm. Usually, the total
25 deuteron fluence ranging from less than 1 to about 2 μC , was given in fractions of 0.2 or 0.5 μC
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 with a short waiting time in between. There are two reasons for fractionating the fluence: to limit
4 heating, and to allow evaluation of possible degradation, which may be corrected for it where
5 necessary by a linear regression of the data to zero dose. Note that, since the chemical nature of
6 the carbon atom is irrelevant in NRA, only degradation processes leading to evaporation of a
7 carbon-containing fragment are detected here. Other degradation processes, which indeed occur,
8 are unimportant. These precautions were unnecessary for the oxygen reference, for which a
9 fluence of 10 μC was usually chosen in a single step.
10
11
12
13
14
15
16
17
18
19

20 However, carbon contamination being omnipresent, it has to be taken into account.
21 Contamination was measured in two ways. First, carbon atoms were counted on a part of the
22 slide not covered with the material during evaporation. Second, counts on monomer films of
23 different thicknesses were compared. The mass measurement by the quartz balance is very
24 accurate, so since the raw counts are not exactly in the ratio of the thicknesses, it was assumed
25 that the difference came from contamination. Both methods gave reproducible and consistent
26 results, leading to a contribution from contamination to the measured NRA signal of ≈ 150
27 counts per μC . This was subtracted from all experimental counts.
28
29
30
31
32
33
34
35
36
37
38

39 *Uncertainties:* the nuclear reaction being a statistical process, there is a statistical uncertainty
40 on the count values recorded. In our experimental conditions, these were 1 to 2 %, except for
41 films of small thickness and low polymer content where it could reach 3 %. Since X is simply
42 the ratio of two counts obtained in identical conditions, the uncertainty on it has no other source.
43
44
45
46
47

48 However, other factors enter in the determination of N_{C} . There is a 1.5 % statistical uncertainty
49 on the areal density of ^{16}O atoms in the reference. There are also a number of non statistical
50 uncertainties which identically affect these two quantities. The factor 5.56 is only known to ± 3
51
52
53
54
55
56
57
58
59
60

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

% . The number of molecules per unit area (the so-called areal density) N is calculated as follow equation 1:

$$N = \frac{N_{c_cor}}{N_0} \cdot \frac{\sigma_0}{5.56} \cdot \frac{1}{n_c} N \quad (1)$$

N_{C_cor} is N_C corrected by removing the carbon contamination (150 counts/ μC) and multiplying by 1.011 to take into account the natural abundance of the ^{13}C isotope, since only ^{12}C is determined in the NRA measurements. N_O is the number density of oxygen atoms per unit area counted by NRA, σ_O the areal density of ^{16}O reference and n_C the number of C atoms in the molecule of interest.

3 Results and discussion

3.1 NRA method to determine the polymer content-calibration curve

The polymer content obtained by NRA X_{NRA} is the ratio N_p/N_m , where N_m and N_p are the molecular areal densities (number of molecules per unit area in the total thickness of the film) in a film before and after removal of the monomer. In the polymer we mean by "molecule" a repeat unit of the polymer chain which has the same molecular formula and therefore the same number of carbon atoms as the monomer molecule. Rather than performing the two NRA measurements on the same film (with the risk of unwanted degradation on handling, particularly during the dissolution step) we chose to proceed as follows: as mentioned before, four films are simultaneously prepared. They should be identical, and this was indeed checked in two ways: they give the same NRA results, and after UV irradiation for the same duration their absorption spectra are identical. Therefore, in each series of 4 films one was kept intact and its NRA result gives the areal density N_m valid for the four films. The three others were irradiated and their spectra recorded just after irradiation and before removal of residual monomer (a blue spectrum is obtained). The residual monomer was then removed leaving a red, pure polymer film and the

1
2
3 corresponding red spectrum was recorded. This film was then studied by NRA giving a
4
5 molecular (repeat unit) areal density $N_p(\text{cm}^{-2})$.
6
7

8
9 The next step is to determine a quantity, related to the polymer content, easily measurable on
10 such absorption spectra. The maximum of absorption or the second lower peak corresponding to
11 the vibron associated to the double bond stretch vibration could be chosen. However these
12 quantities may be affected by changes in absorption lineshape. Indeed, it is observed that the
13 halfwidth of the longer wavelength band increases with polymer content, so its height becomes
14 correspondingly smaller. So we shall consider a more global quantity: the area Σ under the
15 spectrum plotted in wavenumbers. This area is proportional to the oscillator strength, a quantity
16 characteristic of the electronic transition (it is well established that all the absorption in the
17 visible and near UV of blue as well as red PDA corresponds to a single excitonic transition [38-
18 39]), so it is a physically meaningful quantity independent of variations in spectral shape. This
19 would not be the case for a spectrum plotted in wavelengths. Considering that the majority of
20 published spectra are given between 400 and 800 nm this spectral interval was chosen here for
21 the determination of Σ . Finally the calibration curve is obtained plotting X_{NRA} as a function of
22 Σ/N_m , where Σ is normalized to the molecular areal density which is directly related to the
23 thickness of the sample.
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44

45 3.2 Validation of the NRA method on 4BCMU

46
47 The diacetylene (DA) chosen to test the NRA method is known as 4BCMU (of side group
48 formula $-(\text{CH}_2)_4\text{-OCONH-CH}_2\text{-COOC}_4\text{H}_9$ see Supporting Information A). The corresponding
49 PDA has been much studied (for reviews see [38-39]), partly because it is among the few soluble
50 PDAs [29]. Thanks to this property a method to determine the polymer content X_{abs} , knowing an
51 absorption spectrum has already been described in [28], where the peak absorptivity of blue
52
53
54
55
56
57
58
59
60

1
2
3 poly-4BCMU crystalline films has been determined: $\alpha_B = 2.62 \pm 0.13 \cdot 10^5 \text{ cm}^{-1}$ at room
4
5
6 temperature.

7
8 In §3.1 an alternative and independent method giving the polymer content X_{NRA} has been
9
10 described. This method is not based on the solubility of the PDA. In the present work twelve
11
12 4BCMU films, of thicknesses 100 to 250 nm, were prepared (plus 4 pure monomer reference
13
14 films) and photopolymerized. Irradiation durations were from 1.4 to 60 minutes, corresponding
15
16 to polymer contents X_{abs} from 0.08 to 0.42; as shown previously, 4BCMU photopolymerization
17
18 practically stops near $X_{\text{abs}} \approx 0.5$. Spectra up to the end of irradiation are typical blue ones (Figure
19
20
21 1).

22
23
24 The residual monomer was extracted as described above. The absorption spectra recorded after
25
26 extraction are typical red ones (Figure 1). We have prepared and polymerized, but not studied by
27
28 NRA, several films with thicknesses between 2.7 nm (one monolayer) [40] and 350 nm. For all
29
30 thicknesses absorption spectra are very similar so the conclusions drawn from the NRA will be
31
32 valid for films of all thicknesses.
33
34
35

36
37 Figure 1 shows that the maximum absorbance of the same film is much smaller in the red
38
39 phase than in the blue one. The ratio of red to blue absorbance is 1.8 so the maximum
40
41 absorptivity of red poly-4BCMU is $\alpha_R = 1.45 \cdot 10^5 \text{ cm}^{-1}$ at room temperature. However, the areas
42
43 Σ under the two spectra, calculated between 12500 and 25000 cm^{-1} , are almost equal, meaning
44
45 that the oscillator strengths of the two transitions are almost equal, but this does not imply that
46
47 the peak absorptivity will be the same, since the spectra have different shapes.
48
49
50

51
52 From the NRA results, X_{NRA} values for all samples could be calculated as the ratio of the
53
54 counting rate on the film to that on the corresponding reference monomer film. The statistical
55
56 uncertainties are from about 1 % at high polymer content to about 3.5 % for the smallest one.
57
58
59
60

1
2
3 The values of X_{NRA} obtained in this way are compared on Figure 2 to those calculated from the
4
5 absorption spectra using the value of α_{B} known with $\pm 5\%$ uncertainty and the carbon atom areal
6
7 densities measured by NRA with uncertainty $\pm 1\%$. They are equal within the experimental
8
9 uncertainties: as shown on Figure 2, the results are well fitted by a straight line of slope $1.01 \pm$
10
11 0.02 with intercept at zero. This validates the NRA method for determining polymer content.
12
13

14
15 A calibration curve can thus be obtained for 4BCMUs. Figure 3 shows Σ/N_{m} , Σ is normalized
16
17 by the surface density N_{m} , to obtain a curve useful whatever the thickness of the samples, versus
18
19 the polymer content. N_{m} varies from 14 to 32 10^{15} molecules/cm². Data have been fitted by a
20
21 straight line of slope $228 \pm 7 \cdot 10^{-15}$ cm/molecule with intercept at zero. Such a curve is not
22
23 necessary in the case of 4BCMUs because it is easier to use the peak absorptivity α , but in many
24
25 PDA α is not known because the polymer is not soluble [28]. A similar data treatment can be
26
27 done on red chains. The red and blue slopes are equal when the same frequencies range is used
28
29 [12500-25000 cm⁻¹]. Since the red spectrum doesn't decrease to zero at 12500 cm⁻¹, the slope is
30
31 slightly underestimated. If a larger range [12500-28500 cm⁻¹] is used, the new slope becomes:
32
33 $250 \pm 20 \cdot 10^{-15}$ cm/molecule. The NRA method can be used on insoluble PDA, and we shall use it
34
35 on one of the most studied PDA, 10-12 pentacosadiynoic acid (PCDA) in the next section.
36
37
38
39
40
41

42 3.3 Polymer content in PCDA thin films: calibration curve

43
44 The same procedure as described on 4BCMUs is performed on PCDA films. The blue and red
45
46 spectra of evaporated PCDA film are shown in Figure 1. Again, the value of Σ is obtained by
47
48 integration from 800 nm (12500 cm⁻¹) to 400 nm (25000 cm⁻¹). The values of the molecular areal
49
50 density of the samples vary between 5 and 16 10^{15} molecules/cm². The result Σ/N_{m} function of
51
52 X_{NRA} for blue chains is given Figure 4, the data are fitted by a line of slope $197 \pm 3 \cdot 10^{-15}$
53
54
55
56
57
58
59
60

1
2
3 cm/molecule and zero intercept. The slope is a little bit smaller than that obtained for 4BCMU
4
5 suggesting that the oscillator strength of the transition is slightly smaller.
6
7

8 It is now possible to determine the polymer content of B type chains for a given absorption
9
10 spectrum and obtain polymerization kinetics. Figure 5a shows a series of absorption spectra
11
12 recorded during photopolymerization of a 150 nm thick film in the same conditions as in [28],
13
14 and Figure 5b shows the time variation of the deduced polymer content, compared to the peak
15
16 absorption variation. An integration extending further in the UV would slightly increase the
17
18 difference.
19
20

21
22 Often one wants to know the polymer content at the end of an experiment where all chains are
23
24 in the red phase. The method described for the blue chains can be used exactly in the same way.
25
26 However, the red absorption spectrum does not fall to zero at 400 nm. To draw a calibration
27
28 curve for red chains we have chosen to calculate Σ between 12500 and 25000 cm^{-1} as for the
29
30 blue chains, since this is the range almost always used in the literature, so the calculated values
31
32 slightly underestimate the total area and oscillator strength. The result is given Figure 6. The
33
34 slope of the line obtained is $216 \pm 4 \cdot 10^{-15}$ cm/molecule, a little bit higher than that obtained in the
35
36 blue case. When the experimental absorption is the sum of both blue and red chain spectra an
37
38 approximate value of the total polymer content can be deduced using the average of the slopes of
39
40 the two calibration curves.
41
42
43
44

45 3.4 An example of application to PCDA Langmuir films.

46
47 The calibration curves have been obtained using evaporated thin films; these curves can be
48
49 used on other kind of PCDA samples provided that the absorption spectra have the same shape.
50
51 The photopolymerization of a trilayer of PCDA at 25mN/m corresponding to an area of 0.08
52
53 $\text{nm}^2/\text{molecule}$ and so an areal density $N_m = 1.25 \cdot 10^{15}$ molecules/ cm^2 , on pure water subphase has
54
55
56
57
58
59
60

1
2
3 been studied by absorption. These conditions are identical to those used by Lifshitz et al. [41] in
4 their determination of the crystal structure of a PCDA trilayer. Experimental details of our
5 experiment are given in Supporting Information E. An example is given Figure 5a, added in bold
6 for comparison to a series of PCDA microcrystalline film absorption spectra. From this spectrum
7 an X of 30% is deduced using the calibration obtained above. We note in passing that the
8 reactivity for photopolymerization is very similar on microcrystalline and Langmuir films (see
9 supporting information E Figure E3). From these two data points, the use of the color ratio and
10 the problem of the apparent concentration can be discussed.

11
12 To quantify the color transition, a quantity called the color ratio (CR) is generally used. It was
13 initially introduced by Charych [14,42] as equation 2:

$$14 \quad CR = \frac{B_0 - B_V}{B_0} \times 100 \quad (2)$$

15 where $B_0 = \frac{I_0(blue)}{I_0(blue) + I_0(red)}$ and $B_V = \frac{I_V(blue)}{I_V(blue) + I_V(red)}$, where $I_0(blue)$ and $I_V(blue)$ are the
16 absorbances at the absorption maximum of blue type polymer chains before and after a color
17 transition, with $I_0(red)$ and $I_V(red)$ for the red type polymer chains. It is an empirical quantity
18 introduced for its large dynamic range between 0 and 100%. This quantity has to be
19 experimentally calibrated (and it was in these papers). However it has sometimes been equated
20 by others to the relative concentration of red chains, which is not generally true except that it is
21 indeed 0 for a pure blue film and 1 for a pure red one. This is because the maximal absorbance of
22 the two types of chains may not be equal, and in fact they are not in PCDA (and 4BCMU) as
23 may be seen in Figure 1 and the blue absorbance at the wavelength of maximal red absorption is
24 not negligible; in fact it amounts to $\approx 40\%$ of the maximal blue absorption in the same spectrum.

25
26 As already shown [28] a strong slowing down of the photopolymerization rate (Figure 5b)
27 occurs, so that an apparent saturation of the reaction may not correspond to a complete
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 polymerization. It is indeed the case for PCDA crystal or Langmuir film (see Supporting
4 Information E). The discussions on the blue to red transition in sensors have to take into account
5
6 the fact that polymer films are potentially constituted of up to 40-50% of monomer.
7
8

9 10 4 Conclusion

11
12 This paper introduces a new method for quantifying the polymer content X in a PDA
13 film, using numbers directly given by its absorption spectrum (it should be noted that the peak
14 absorbance of a spectrum does not give a good quantitative measure of X , except possibly at
15 small X . In view of the current activity in PDA sensor development, we have therefore applied
16 the method to obtain a calibration curve for PCDA, a much studied material in the sensor
17 context, however the method is more general.
18
19

20
21 The method makes it possible to determine X at any stage of the polymerization. It has
22 often been reported in the literature that a spontaneous, unwanted (in fact detrimental), blue to
23 red color transition occurs [23, 27] during photopolymerization. The question of the polymer
24 content at which this transition occurs is never mentioned. The PCDA calibration (Σ/N_m as a
25 function of X) obtained with the novel method presented here our method allows determination
26 of X at the stage where this transition occurs. Such a calibration curve can be obtained for other
27 polydiacetylenes using NRA and used for other types of films. Calibration was obtained for both
28 blue and red PDA films. For each of the two materials studied here, 4BCMU and PCDA, the
29 blue and red results are very close despite the large difference in spectral shapes, indicating very
30 similar values of the total oscillator strengths of the excitonic transitions.
31
32

33
34 It had already been shown [28] that in evaporated films of 4BCMU, photopolymerization
35 does not go to completion. This had been explained by efficient quenching of a photoexcited
36 monomer via energy transfer to a neighboring existing chain. In the present work it is observed
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 that photopolymerization remains also incomplete in PCDA evaporated films, as shown in
4
5 Figure E3 in Supporting Information E. These photopolymerisation kinetics were obtained from
6
7 the polymer contents calculated using the calibration for PCDA obtained in the present work
8
9 (Figure 4). Since the quenching mechanism present in 4BCMU is in principle a general process,
10
11 we suggest that it also applies to explain the incomplete polymerization of PCDA. Moreover, a
12
13 similarly obtained polymerization kinetics of a Langmuir trilayer film is also shown in Figure E3
14
15 with the same saturation as for evaporated films, presumably due to the same mechanism.
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42

43 FIGURES
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

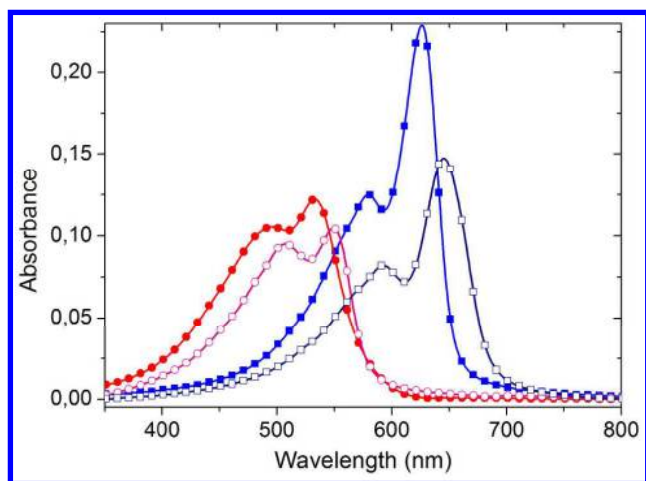


Figure 1: Absorption spectra for evaporated polycrystalline films of 4BCMUs and PCDA of the blue and red polymer chain type, with $N_m(4BCMUs)=14 \cdot 10^{15}$ molecules/cm² (~100nm) and $N_m(PCDA)=5.3 \cdot 10^{15}$ molecules/cm² (~35nm). Solid and open squares: blue 4BCMUs and PCDA respectively; solid and open circles: red 4BCMUs and PCDA respectively.

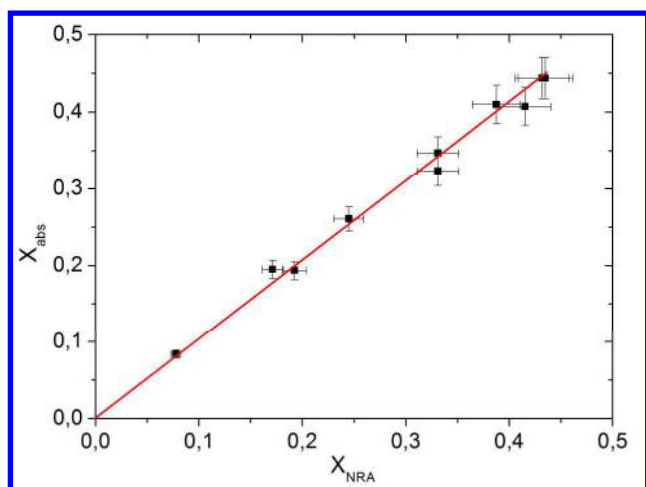


Figure 2: comparison of the polymer content determined using the absorption spectra: X_{abs} and using the NRA method: X_{NRA} in evaporated 4BCMUs polycrystalline films. Data are fitted with a straight line of slope 1.01 ± 0.02 with intercept at zero.

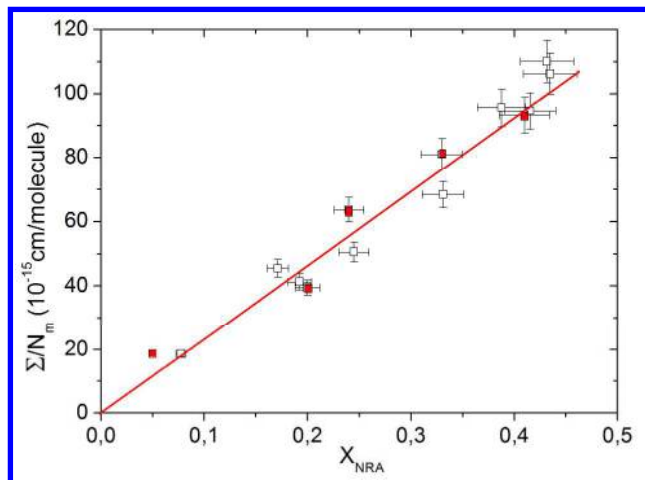


Figure 3: 4BCMU calibration curve using the NRA method: Σ/N_m as a function of X_{NRA} for the blue and red chains. When the same wavenumber range ($12500\text{-}25000\text{ cm}^{-1}$) is used to calculate Σ , similar data are obtained for blue (open squares) and red (solid squares) chains: slope 232 ± 9 10^{-15} cm/molecule and intercept zero.

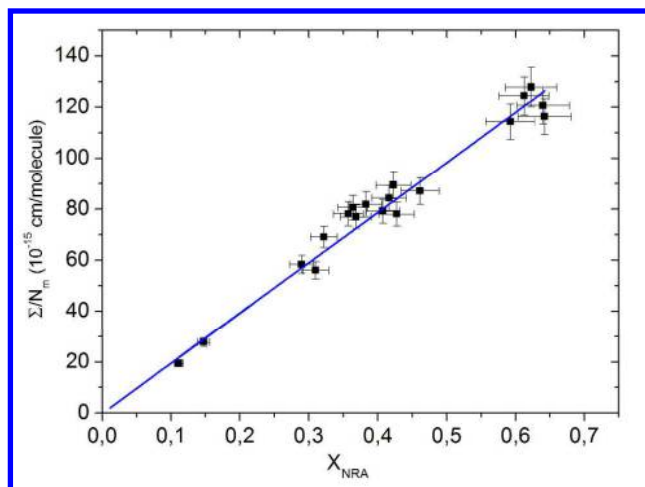


Figure 4: PCDA calibration curve using the NRA method: Σ/N_m function of X_{NRA} for the blue chains. Slope 197 ± 3 10^{-15} cm/molecule and intercept zero.

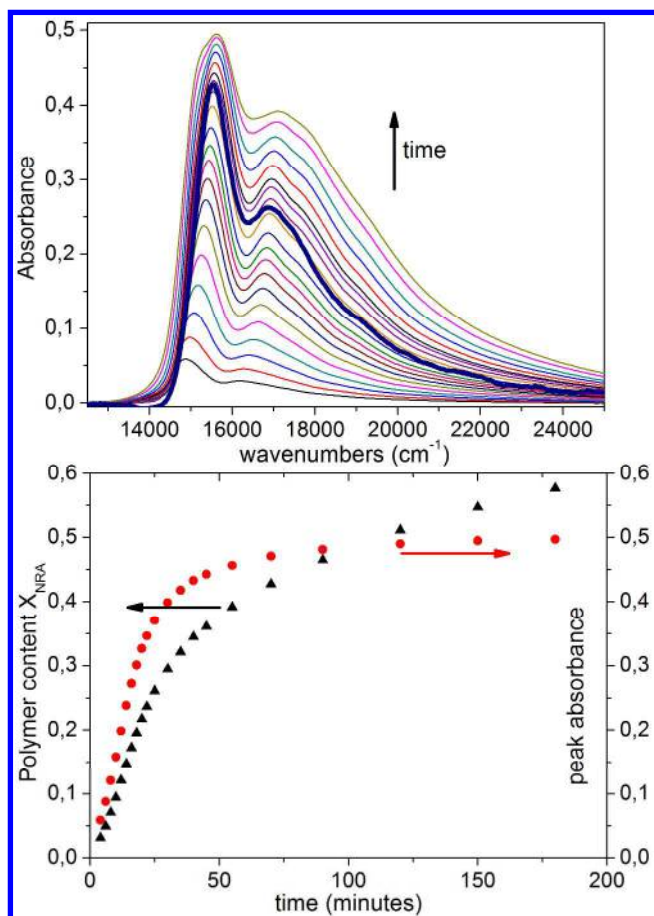


Figure 5: a) absorption spectra of microcrystalline PCDA film (150 nm) as a function of UV polymerization time. In bold the absorption spectrum of a trilayer Langmuir film of PCDA corresponding to a polymer content of 30% is added. This spectrum has been multiplied by a factor 20 b) PCDA microcrystalline film: polymerization kinetics using the peak absorption (closed circles) and the polymer content (closed triangles).

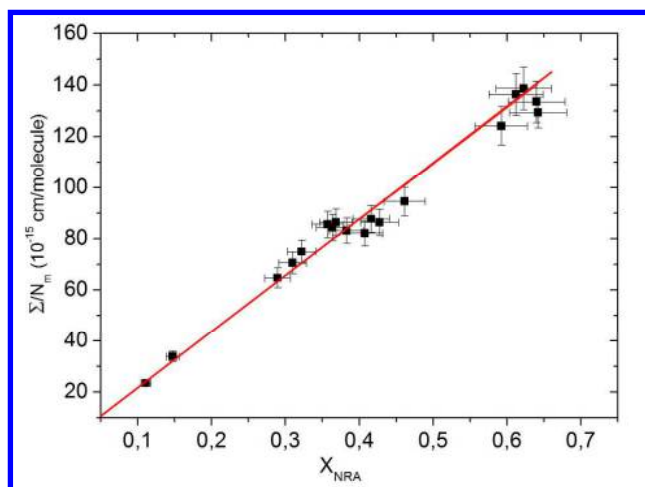


Figure 6: PCDA calibration curve using the NRA method: Σ/N_m as a function of X_{NRA} for the red chains. Slope $216 \pm 4 \cdot 10^{-15}$ cm/molecule and intercept zero.

AUTHOR INFORMATION

Corresponding Author

*Sylvie Spagnoli Sylvie.spagnoli@univ-grenoble-alpes.fr

Author Contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

ACKNOWLEDGMENT

The NRA experiments were performed within the SAFIR collaboration at the ALTAIS accelerator of the University of Namur. We are grateful to Pr. Guy Therwagne for access to this instrument and to Mr T. Tabarrant for expert technical assistance in its operation.

ASSOCIATED CONTENT

Supporting Information

A- Molecular structure of 4BCMU and PCDA

B- Scheme of topochemical polymerization of diacetylenes

C- AFM of PCDA microcrystalline films

D- Dissolution method to remove the monomer.

E- Isotherms and in situ absorption of PCDA Langmuir film.

F- Nuclear Reaction Analysis (NRA).

REFERENCES

- (1) Reppy, M. A.; Pindzola, B. A. Biosensing with polydiacetylene materials: structures, optical properties and applications. *Chem. Commun.* **2007**, 4317–4338.
- (2) Yoon, B; Lee, S; Kim, J-M. Recent conceptual and technological advances in polydiacetylene-based supramolecular chemosensors. *Chem. Soc. Rev.* **2009**, *38*, 1958–1968.
- (3) Chen, X.; Zhou, G.; Peng, X.; Yoon, J. Biosensors and chemosensors based on the optical responses of polydiacetylenes. *Chem. Soc. Rev.* **2012**, *41*, 4610-4630.
- (4) Jelinek, R; Ritenberg, M. Polydiacetylenes – recent molecular advances and applications *RSC Adv.* **2013**, *3*, 21192-21201.
- (5) Scott, J. C.; Samuel, J. D. J.; Hou, J. H.; Rettner, C. T.; Miller, R. D. Monolayer transistor using a highly ordered conjugated polymer as the channel. *Nano Letters* **2006**, *6*, 2916-2019.

1
2
3 (6) Nishide, J-I.; Nakagawa, Y.; Sasabe, H. Organic field-effect transistors using
4 polydiacetylene derivatives as an active layer. *Mol. Cryst. Liq. Cryst.* **2009**, *505*, 257-265.
5
6

7
8
9 (7) Yasuda, A.; Yoshizawa, M.; Kobayashi, T. Fluorescence spectrum of a blue-phase
10 polydiacetylene obtained by probe saturation spectroscopy. *Chem. Phys. Lett.* **1993**, *209*, 281-
11 286.
12
13
14

15
16
17 (8) Morrow, M. E.; White, K. M.; Eckhardt, C. J.; Sandman, D. J. Single crystal reflection and
18 Raman spectra of the polydiacetylene THD. *Chem. Phys. Lett.* **1987**, *140*, 263-269.
19
20
21

22 (9) Al Choueiry, A.; Barisien, T.; Holcman, J.; Legrand, L.; Schott, M.; Weiser, G.; Balog, M.;
23 Deschamps, J.; Dutremez, S. G.; Filhol, J.-S. Twisted polydiacetylene quantum wire: Influence
24 of conformation on excitons in polymeric quasi-one-dimensional systems. *Phys. Rev. B* **2010**, *81*,
25 125208.
26
27
28
29
30

31
32 (10) Olmsted III, J.; Strand, M. Fluorescence of Polymerized Diacetylene Bilayer Films. *J.*
33 *Phys. Chem.* **1983**, *87*, 4790-4792.
34
35
36

37
38 (11) Goettgens, B. M.; Tillmann, R. W. ; Radmacher, M.; Gaub, H. E. Molecular order in
39 polymerizable Langmuir-Blodgett films probed by microfluorescence and scanning force
40 microscopy. *Langmuir* **1992**, *8*, 1768-1774.
41
42
43
44

45
46 (12) Carpick, R. W.; Mayer, T. M.; Sasaki, D. Y.; Burns, A.R. Spectroscopic ellipsometry and
47 fluorescence study of thermochromism in an ultrathin poly(diacetylene) Film: reversibility and
48 transition kinetics. *Langmuir* **2000**, *16*, 4639-4647.
49
50
51

52
53 (13) Li, X. ; McCarroll, M.; Kohli, P. Modulating fluorescence resonance Energy Transfer in
54 Conjugated Liposomes. *Langmuir* **2006**, *22*, 8615-8617.
55
56
57
58
59
60

1
2
3 (14) Charych, D. H.; Nagy, J. O.; Spevak, W.; Bednarski, M. D. Direct colorimetric detection
4 of a receptor-ligand interaction by a polymerized bilayer assembly. *Science* **1993**, *261*, 585-588.
5
6

7
8 (15) Dubin, F.; Melet, R.; Barisien, T.; Grousson, R.; Legrand, L.; Schott, M.; Voliotis, V.
9 Macroscopic coherence of a single exciton state in an organic quantum wire. *Nature Physics*,
10 **2006**, *2*, 32-35.
11
12
13

14 (16) Enkelmann, V.; Schleier, G. Poly[1,2-bis(diphenylaminomethyl)-1-buten-3-ynylene].
15 *Acta Cryst. B.* **1980**, *36*, 1954-1956.
16
17
18

19 (17) Filhol, J.B.; Deschamps, J.; Dutremez, S. G.; Boury, B.; Barisien, T.; Legrand, L.; Schott,
20 M. Polymorphs and Colors of Polydiacetylenes: A First Principles Study. *J. Am. Chem. Soc.*
21 **2009**, *131*, 6976–6988.
22
23
24
25
26
27

28 (18) Schott, M. The colors of polydiacetylenes: a commentary, *J. Phys. Chem. B* **2006**, *110*,
29 15864-15868.
30
31
32
33

34 (19) Tanaka, H.; Gomez, M. A.; Tonelli, A. E.; Thakur, M. Thermo-chromic Phase Transition
35 of a Polydiacetylene, Poly(ETCD), Studied by High-Resolution Solid-state ¹³C NMR.
36 *Macromolecules*, **1989**, *22*, 1208-1215.
37
38
39
40
41
42

43 (20) Cholli, A. L.; Sandman, D. J. Structural investigation of polydiacetylenes: A variable
44 temperature solid state ¹³C CP/MAS NMR study. *Bull. Mat. Sci.* **1999**, *22*, 691-695.
45
46
47
48

49 (21) Charych, D.; Cheng, Q.; Reichert, A.; Kuziemko, G.; Stroh, M.; Nagy, J. O.; Spevak, W.;
50 Steven, R. C. A 'litmus test' for molecular recognition using artificial membranes. *Chem*
51 *and Bio.* **1996**, *3*, 113-120.
52
53
54
55
56
57
58
59
60

1
2
3 (22) Ma, B.; Fan, Y.; Zhang, L.; Kong, X.; Li, Y.; Li, J. Direct colorimetric study on the
4 interaction of Escherichia coli with mannose in polydiacetylene Langmuir / Blodgett films. *Coll.*
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

(22) Ma, B.; Fan, Y.; Zhang, L.; Kong, X.; Li, Y.; Li, J. Direct colorimetric study on the interaction of Escherichia coli with mannose in polydiacetylene Langmuir / Blodgett films. *Coll. and Surf. B.* **2002**, *27*, 209-213.

(23) Tachibana, H. ; Yamanaka, Y. ; Sakai, H.; Abe, M.; Matsumoto, M. In situ AFM study on the morphological change of the Langmuir-Blodgett film of cadmium 10,12-Pentacosadiynoate during polymerization. *Langmuir*, **2000**, *16*, 2975-2977.

(24) Britt, D. W.; Hofmann, U. G.; Mobius, D.; Hell, S. W. Influence of substrate properties on the topochemical polymerization of diacetylene monolayers. *Langmuir* **2001**, *17*, 3757-3765.

(25) Fugimori, A.; Ishitsuka, M.; Nakahara, H.; Ito, E.; Hara, M.; Kanai, K.; Ouchi, Y.; Seki, K. Formation of the newly greenish organized molecular film of long-chain diynoic acid derivatives by photopolymerization and its structural study using near-edge X-ray absorption fine structure (NEXAFS) spectroscopy. *J. Phys. Chem. B* **2004**, *108*, 13153-13162.

(26) Kim, T.; Ye, Q.; Sun, L.; Chan, K. C.; Crooks, R. M. Polymeric self-assembled monolayers. 5. synthesis and characterization of ω -functionalized, self-assembled diacetylenic and polydiacetylenic monolayers. *Langmuir*, **1996**, *12*, 6065-6073.

(27) Lifshitz, Y.; Upcher, A.; Shusterman, O.; Horovitz, B.; Berman, A.; Golan, Y. Phase transition kinetics in Langmuir and spin-coated polydiacetylene films. *Phys. Chem. Chem. Phys.*, **2010**, *12*, 713-722.

(28) Spagnoli, S.; Fave, J.-L.; Schott, M. Photopolymerization of thin polycrystalline diacetylene films and quenching of the precursor excited state. *Macromolecules* **2011**, *44*, 2613-2625.

1
2
3 (29) Patel, G. N.; Chance, R.R.; Witt, J. D. A planar-nonplanar conformational transition in
4 conjugated polymer solutions. *J. Chem. Phys.* **1979**, *70*, 4387-4392.
5
6

7
8
9 (30) Patel, G. N. Soluble polydiacetylenes I. Synthesis and properties. *Polym. Prepr. (Am.*
10
11 *Chem. Soc., Div. Polym. Chem.)* **1978**, *19*, 154-157.
12

13
14 (31) Wegner, G. Topochemical reactions of monomers with conjugated triple bonds. IV.
15 Polymerization of 2,4-hexadiyne-1,6-diol bis(p-toluenesulfonate). *Makromol.*
16
17 *Chem.* 1971, *145*, 85-94.
18
19

20
21
22 (32) Bloor, D.; Koski, L.; Stevens, G. C.; Preston, F. H.; Ando, D. J. Solid state polymerization
23 of bis(p-toluenesulfonate) of 2,4-hexadiyne-1,6-diol. 1. X-ray diffraction and spectroscopic
24 observations. *J. Mat. Sci.* 1975, *10*, 1678-1688.
25
26
27

28
29
30 (33) McGhie, A. R.; Kalyanaraman, P. S.; Garito, A. F. Solid state polymerization of a
31 diacetylene: 2,4-Hexadiyne-1,6-diol bis(p-toluenesulfonate) (PTS). *Mol. Cryst. Liq.*
32
33 *Cryst.* 1979, *50*, 287-299.
34
35
36

37
38 (34) Patel, G. N.; Khanna, Y. P.; Ivory, D. M.; Sowa, J. M.; Chance, R. R. Polymer
39 conversions in the γ -ray polymerization of urethane-substituted diacetylenes. *J. of Polym. Sci.,*
40
41 *Polym. Phys. Ed.* 1979, *17*, 899-903.
42
43
44

45
46 (35) Enkelmann, V. The solid-state polymerization, physical properties, and crystal structures
47 of diacetylene mixed crystals. *Makromol. Chem.* 1983, *184*, 1945-1955.
48
49

50
51 (36) Schmaus, D.; Vickridge, I. Chapter 4. MeV Ion Beam Analytical Methods. In *Analytical*
52
53 *Methods for Corrosion Science and Engineering*, Marcus, P.; Mansfeld, F. Eds; Dekker, Taylor
54 and Francis, Boca Raton, 2006, pp103-132.
55
56
57
58
59
60

1
2
3 (37) Quillet, V.; Abel, F.; Schott, M. Absolute cross section measurements for hydrogen and
4 deuterium elastic recoil using 1 to 2.5 MeV helium-4 ions, and for the $^{12}\text{C}(\text{d},\text{p})^{13}\text{C}$ and $^{16}\text{O}(\text{d},\text{p}_1)$
5 ^{17}O nuclear reactions. *Nucl. Instrum. Methods Phys. Res., Sect. B* **1993**, *83*, 47-61.
6
7

8
9
10
11 (38) Weiser, G.; Horvath, A. Electroabsorption spectroscopy on p-conjugated polymers. In
12 *Primary photoexcitations in conjugated polymers: Molecular exciton versus semiconductor band*
13 *model*, Siriciftci, N.S. Ed; World Scientific: Singapore, 1997; pp318-362.
14
15


16
17
18
19 (39) Schott, M. Optical properties of single conjugated polymer chains (polydiacetylene). In
20 *Photophysics of molecular materials*, Lanzani, G. Ed; Wiley-VCH: Weinheim, 2005; pp49-151.
21
22

23
24
25 (40) Spagnoli, S.; Schott, M.; Johnson, M.; Toupet, L. Structural study of two reactive
26 diacetylenes. *Chem. Phys.* **2007**, *333*, 236-245.
27
28

29
30 (41) Lifshitz, Y.; Golan, Y.; Konovalov, O.; Berman, A. Structural Transitions in
31 Polydiacetylene Langmuir Films. *Langmuir*, **2009**, *25*, 4469-4477.
32
33

34
35
36 (42) Reichert, A.; Nagy, J. O.; Spevak, W.; Charych, D. H. Polydiacetylene Liposomes
37 Functionalized with Sialic Acid Bind and Colorimetrically Detect Influenza Virus. *J. Am. Chem.*
38 *Soc.* **1995**, *117*, 829-830.
39
40

41
42
43
44 Table of Contents Graphic
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

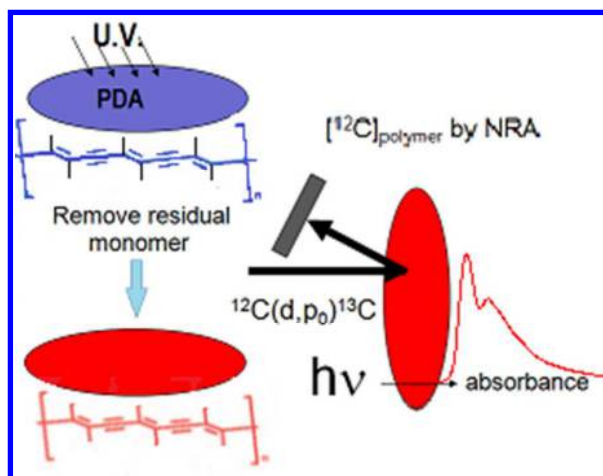

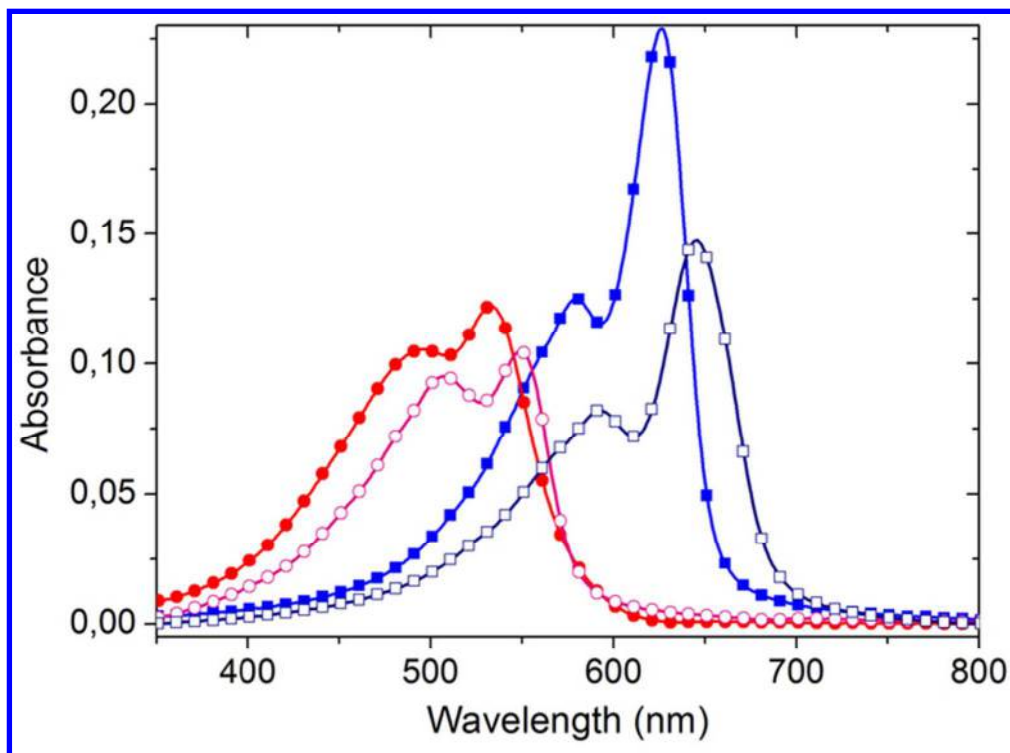


Figure 1: Absorption spectra for evaporated polycrystalline films of 4BCMU and PCDA of the blue and red polymer chain type, with $N_m(4BCMU)=14 \cdot 10^{15}$ molecules/cm² (~100nm) and $N_m(PCDA)=5.3 \cdot 10^{15}$ molecules/cm² (~35nm). Solid and open squares: blue 4BCMU and PCDA respectively; solid and open circles: red 4BCMU and PCDA respectively.

61x45mm (300 x 300 DPI)

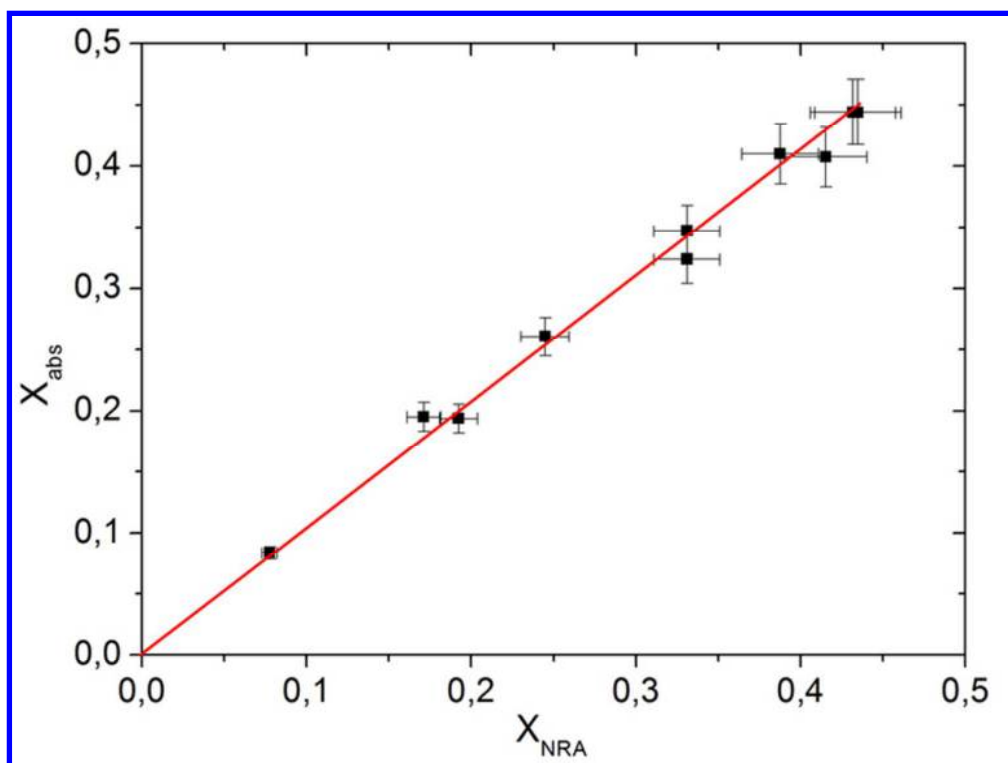


Figure 2: comparison of the polymer content determined using the absorption spectra: X_{abs} and using the NRA method: X_{NRA} in evaporated 4BCMU polycrystalline films. Data are fitted with a straight line of slope 1.01 ± 0.02 with intercept at zero.

61x46mm (300 x 300 DPI)

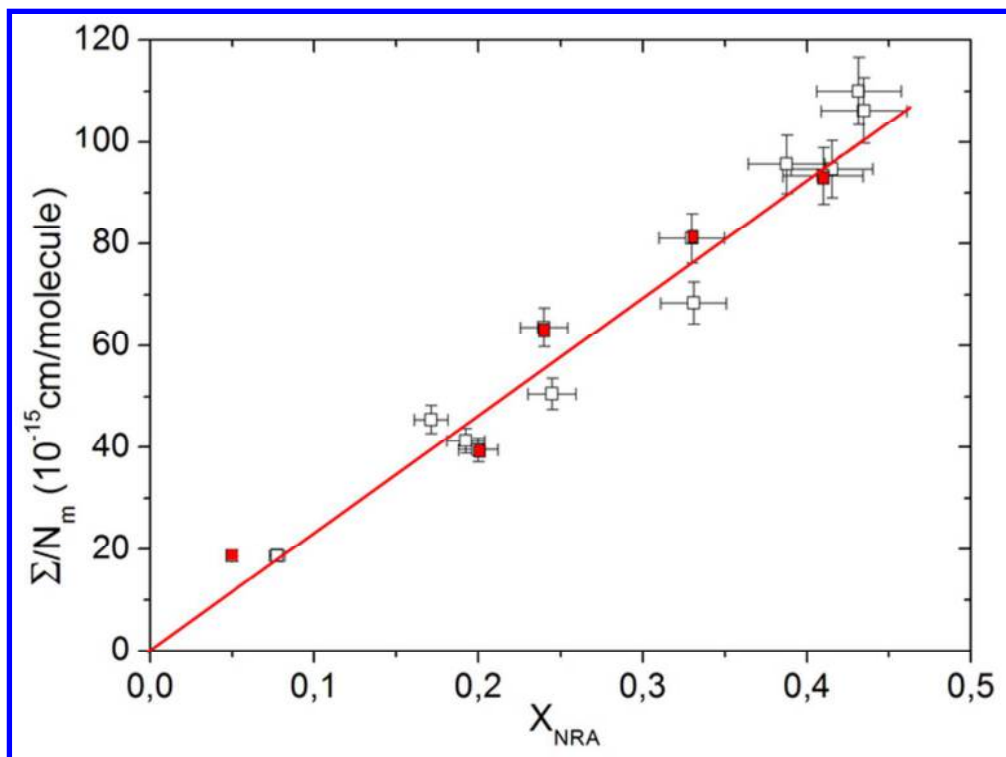


Figure 3: 4BCMU calibration curve using the NRA method: Σ/N_m as a function of X_{NRA} for the blue and red chains. When the same wavenumber range ($12500\text{--}25000\text{ cm}^{-1}$) is used to calculate Σ , similar data are obtained for blue (open squares) and red (solid squares) chains: slope $232 \pm 9\ 10^{-15}$ cm/molecule and intercept zero.

61x45mm (300 x 300 DPI)

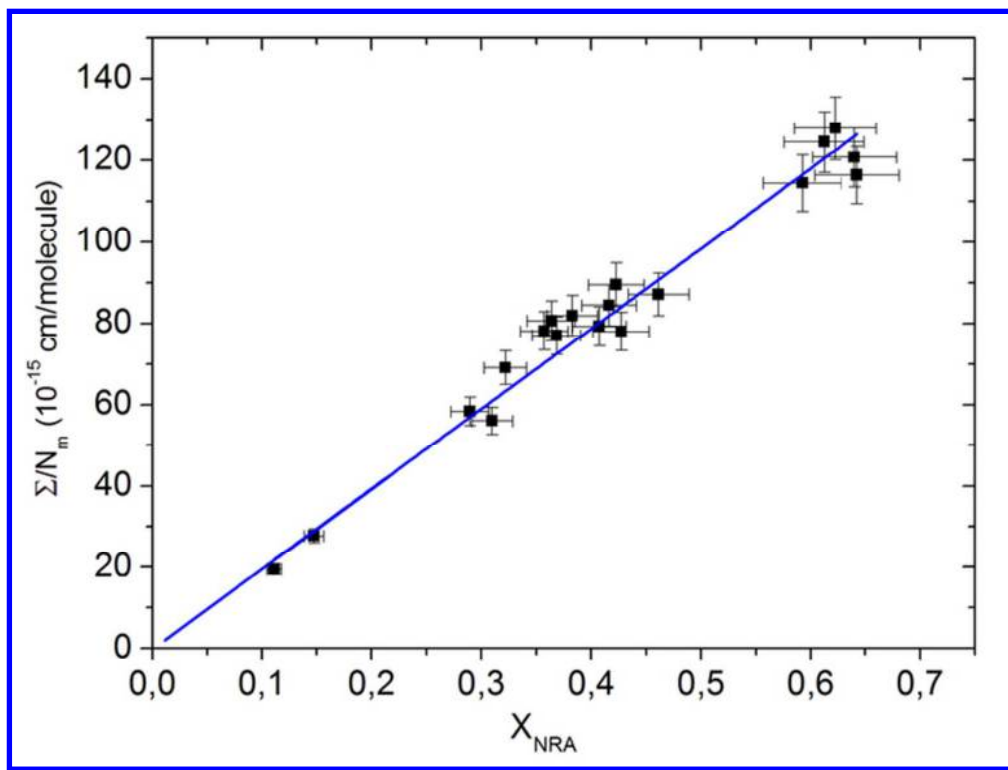


Figure 4: PCDA calibration curve using the NRA method: Σ/N_m function of X_{NRA} for the blue chains. Slope $197 \pm 3 \cdot 10^{-15}$ cm/molecule and intercept zero.

62x46mm (300 x 300 DPI)

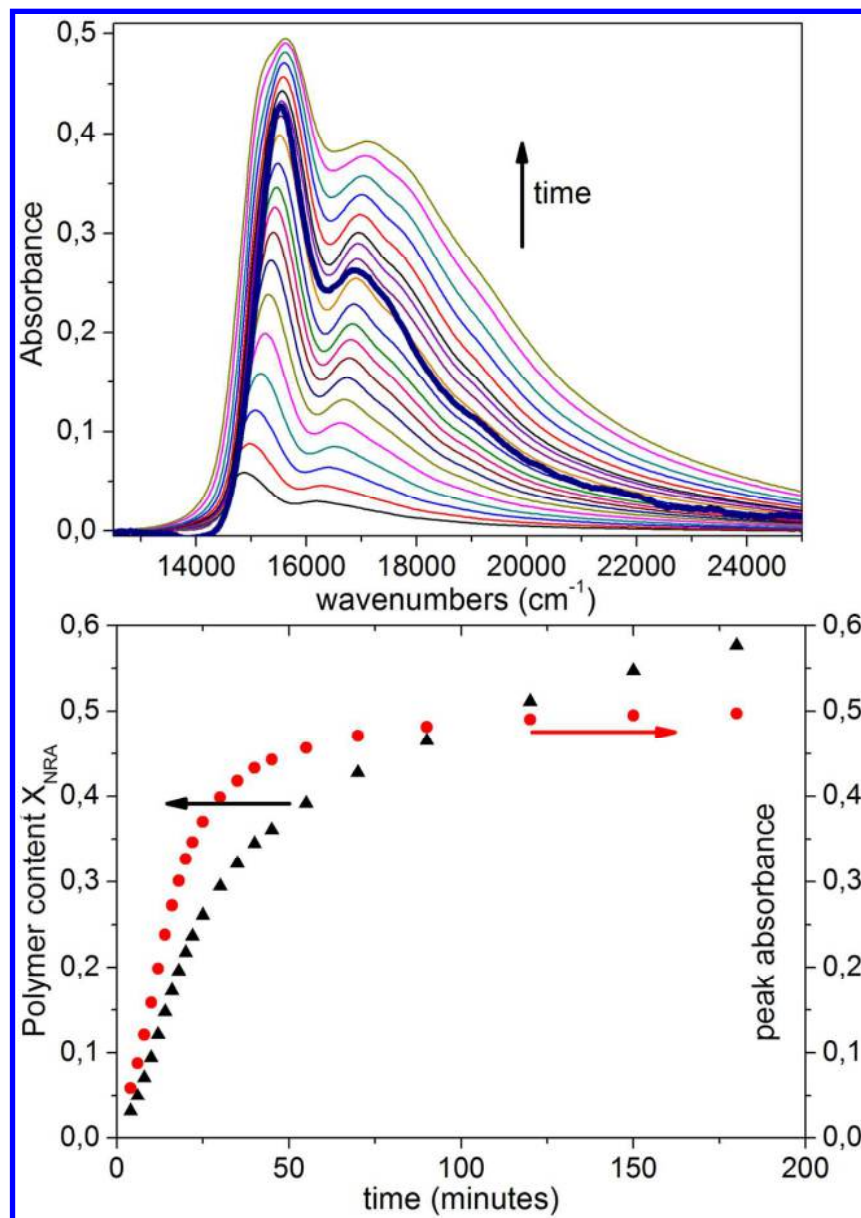


Figure 5: a) absorption spectra of microcrystalline PCDA film (150 nm) as a function of UV polymerization time. In bold the absorption spectrum of a trilayer Langmuir film of PCDA corresponding to a polymer content of 30% is added. This spectrum has been multiplied by a factor 20 b) PCDA microcrystalline film: polymerization kinetics using the peak absorption (closed circles) and the polymer content (closed triangles).

118x167mm (300 x 300 DPI)

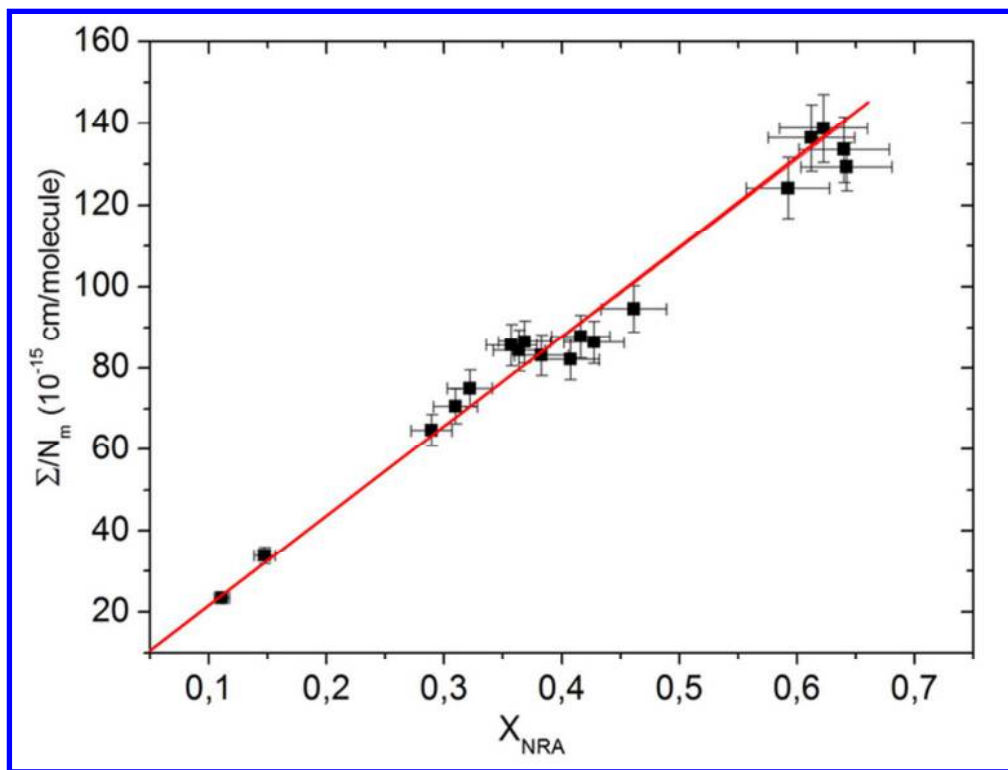


Figure 6: PCDA calibration curve using the NRA method: Σ/N_m as a function of X_{NRA} for the red chains. Slope $216 \pm 4 \cdot 10^{-15}$ cm/molecule and intercept zero.

62x46mm (300 x 300 DPI)