



X-ray absorption spectroscopy study of buried Co layers in the Co/Mo₂C multilayer mirrors

Yanyan Yuan, Karine Le Guen, Yuchun Yu, Jingtao Zhu, Zhanshan Wang, Wenbin Li, Mingwu Wen, Christian Mény, Haisheng Yu, Yuying Huang, et al.

► To cite this version:

Yanyan Yuan, Karine Le Guen, Yuchun Yu, Jingtao Zhu, Zhanshan Wang, et al.. X-ray absorption spectroscopy study of buried Co layers in the Co/Mo₂C multilayer mirrors. *Surface and Interface Analysis*, 2017, 49 (3), pp.205 - 209. 10.1002/sia.6116 . hal-01480541

HAL Id: hal-01480541

<https://hal.sorbonne-universite.fr/hal-01480541>

Submitted on 1 Mar 2017

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

X-ray absorption spectroscopy study of buried Co layers in the Co/Mo₂C multilayer mirrors

Yanyan Yuan^{1,2*}, Karine Le Guen^{1,2}, Yuchun Tu^{1,2,3}, Jingtao Zhu³, Zhanshan Wang³, Wenbin Li³, Mingwu Wen³, Christian Mény⁴, Haisheng Yu⁵, Yuying Huang⁵, Xiangjun Wei⁵, Philippe Jonnard^{1,2}

¹*Sorbonne Universités, UPMC Univ Paris 06, Laboratoire de Chimie Physique-Matière et Rayonnement,*

11 rue Pierre et Marie Curie, F-75231 Paris cedex 05, France

²*CNRS UMR 7614, Laboratoire de Chimie Physique-Matière et Rayonnement, 11 rue Pierre et Marie Curie, F-75231 Paris cedex 05, France*

³*Institute of Precision Optical Engineering, Department of Physics, Tongji University, Shanghai 200092, China*

⁴*Institut de Physique et Chimie des Matériaux de Strasbourg, UMR 7504 CNRS-Université De Strasbourg 23 rue du Loess, 67034 Strasbourg, France*

⁵*Shanghai Synchrotron Radiation Facility, Shanghai Institute of Applied Physics Chinese Academy of Sciences, Zhangheng Road 239, Pudong,*

Shanghai 201204, China

Abstract

X-ray absorption spectroscopy (XAS) at the Co K edge was applied to investigate the chemical environment of Co atoms inside Co/Mo₂C periodic multilayers. The results show a mixing between Co and Mo₂C layers prior to any annealing process whereas following annealing from 300°C pure Co layers are observed. XAS results are in agreement with previous nuclear magnetic resonance spectroscopy results. They indicate that the pure Co content increases upon annealing, while it is absent in the as-deposited samples. The comparison of the results, based on the analysis of the data obtained on the multilayer samples and some reference materials, reveals that the ordering of Co atoms inside the Co layers increases upon annealing.

Keywords: XANES; EXAFS; interface analysis; periodic multilayer; buried Co layers; annealing

* Corresponding author: e-mail: yuan.yanyan@just.edu.cn. The present address of author Yanyan Yuan is School of Materials Science and Engineering, Jiangsu University of Science and Technology, Mengxi Road 2, Zhenjiang, Jiangsu Province, 212003, China. The present address of author Yuchun Tu is Shanghai Institute of Laser Plasma, Chenjiashan Road 1129, Jiading district, Shanghai, 201800, China.

1. Introduction

Multilayer structures consisting of a periodic alternation of thin films show a variety of interesting properties and applications. They provide not only the potential applications as X-ray and neutron optical elements but also convenient tools for studying the interfaces between different materials. The accurate characterization of interfaces in multilayer structures is still a challenging task and is very important for the improvement of their application properties[1], [2].

X-ray absorption spectroscopy (XAS) is well known for probing the local atomic structure around a specific element in thin films and other structures [3]–[8]. In the case of buried interfaces, the phases are often formed in a narrow region, are highly disordered or present a short-range order. Thus the XAS technique with short-range order sensitivity provides a powerful tool for the study of interface phases, also called interphases. Examples of XAS investigation of multilayered samples can be found in [9]–[14].

The interfacial properties of the Co/Mo₂C multilayer have been studied in a previously published paper [15]. It reported that the Co and C atoms mix together during deposition and then, following annealing from 300°C, Co and C demix from their mixed regions. In order to interpret the chemical bond environment of Co layers upon annealing, XAS was measured by detecting the fluorescence radiation. Both XANES (X-ray absorption near edge spectroscopy) and EXAFS (extended X-ray absorption fine structure) spectra were used.

2. Experiment

The Co/Mo₂C multilayer samples were prepared by magnetron sputtering. Three different samples are considered: as-deposited, annealed at 300 and 600°C in a furnace for 1h with a pressure of 3.0×10^{-4} Pa, respectively. The details of sample preparation were given previously [16]. Here we recall only the structure of the samples: the thickness of Co and Mo₂C layer in one period is 2.6 and 1.5 nm, respectively; the number of period is 30; the substrates are sliced and polished Si (100) wafers. A 3.5-nm-thick B₄C capping layer is deposited onto the multilayer top to prevent oxidation. Table 1 lists the structural parameters of these samples derived from the x-ray reflectivity data measured at 0.154 nm [16]. Those values will be used in the following sections. Different

characterization methods have been carried out such as x-ray reflectometry in the hard and soft x-ray ranges, x-ray emission spectroscopy, nuclear magnetic resonance (NMR) spectroscopy whose results were given elsewhere [15], [17].

The XAS experiments were carried out at beam line BL14W1 at the Shanghai synchrotron radiation facility [18]. Two types of double crystal monochromators are used for covering photon energy range from 4.5 to 50 keV. The photon energy Resolution ($\Delta E/E$) is around 10^{-4} . The multilayers deposition onto thick substrates leads to the impossibility of absorption measurements in transmission, fluorescence detection was used in this study. The XAS experiment is made in the partial fluorescence yield mode, where the integrated intensity of the Co K α characteristic emission is measured as a function of the energy of the incident radiation scanned through the Co K edge (7709 eV). A 32-element Canberra/XIA Ge detector system was used to detect the fluorescence radiation.

For the sake of comparison, the XAS spectra of some reference samples (CoMo (1 at.%), Co₃Mo, Co₃Mo₃C and Co₆Mo₆C solid solutions and a Co foil) were also obtained. Here, the spectra of the reference samples CoMo (1 at.%), Co₃Mo, Co₃Mo₃C and Co₆Mo₆C solid solutions were obtained in fluorescence mode and that of the Co foil in transmission mode. We should keep in mind that the direct comparison of the intensity of the features of the multilayers and the reference samples is difficult as the self-absorption conditions are not the same in thin films and bulk materials.

All the XAS spectra were normalized after a background subtraction taking into account the low and high photon energy parts of the spectra far from the threshold. This was done with the IFEFFIT software [19]. The background toward the high energy side can be difficult to determine owing to the presence of the first EXAFS oscillations, leading to an uncertainty on the intensity near the threshold.

3. Results and discussion

Fig. 1(a) and (b) respectively show the EXAFS and XANES spectra in the vicinity of the Co K edge of the three Co/Mo₂C multilayer samples and the Co foil reference. All the spectra present a shoulder at about 7713 eV, whose value is determined by the minimum of the first derivative. The spectra of the annealed multilayers exhibit higher-contrasted oscillations and are close to those of the Co reference. This indicates that the local environment of the Co atoms in the annealed multilayer is

similar to that of Co atoms in the Co foil. In the case of the as-deposited sample, the oscillations are attenuated, especially above 7850 eV.

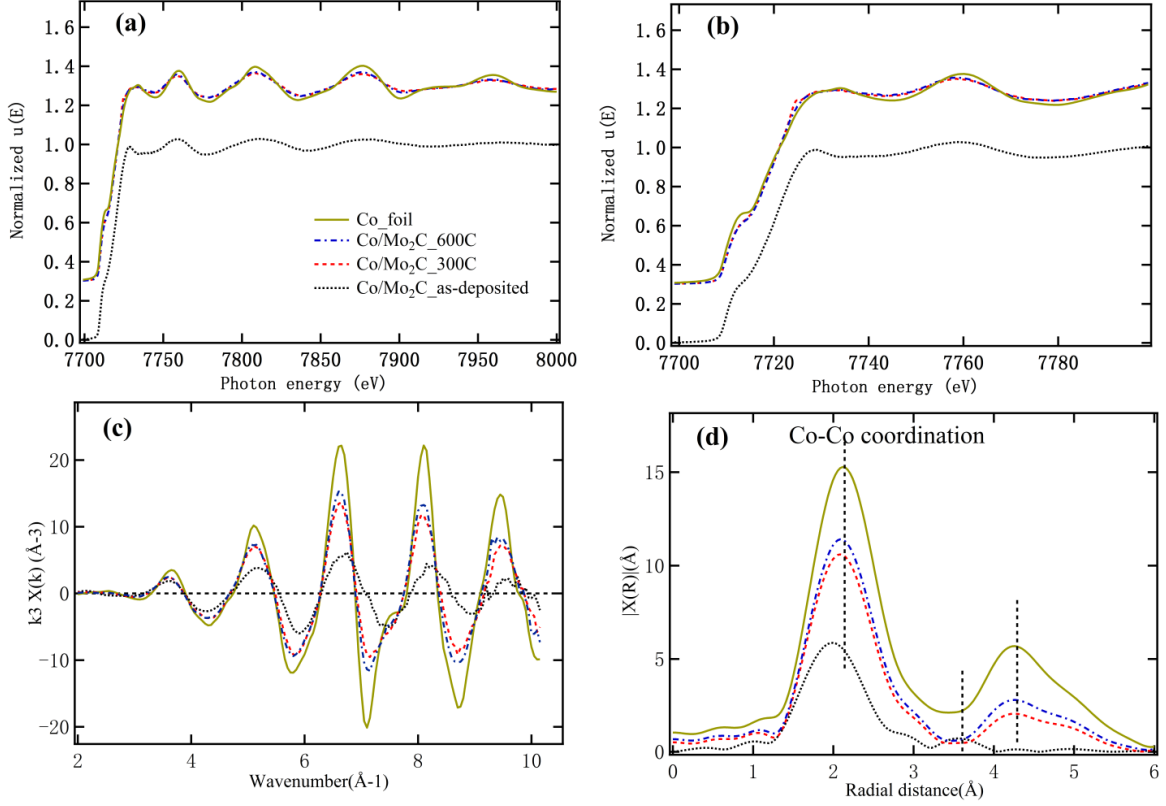


Fig. 1: Co K edge x-ray absorption measurement of the Co/Mo₂C multilayers (as-deposited, annealed at 300 and 600°C), and the Co foil reference: (a) normalized EXAFS spectra; (b) normalized XANES spectra; (c) k^3 -weighted k-space spectra and (d) Fourier transform R-space spectra of EXAFS. For the sake of clarity, curves are vertically shifted in (a) and (b).

Fig. 1(c) and (d) respectively show, for the three multilayers and the reference, the k^3 -weighted k-space spectra (data have been multiplied by k^3 to enhance the oscillations at high k) and Fourier transform R-space spectra (the Fourier transform of an EXAFS spectrum would give a similar radial distribution function) of the EXAFS data. In all spectra, the highest contrast is obtained for the Co foil. The k^3 -weighted k-space spectra of the multilayer present well-contrasted oscillations for high k values. The amplitude of the oscillations increases as a function of the annealing temperature. The same trend can be seen on the Fourier transform R-space spectra, Fig. 1(d).

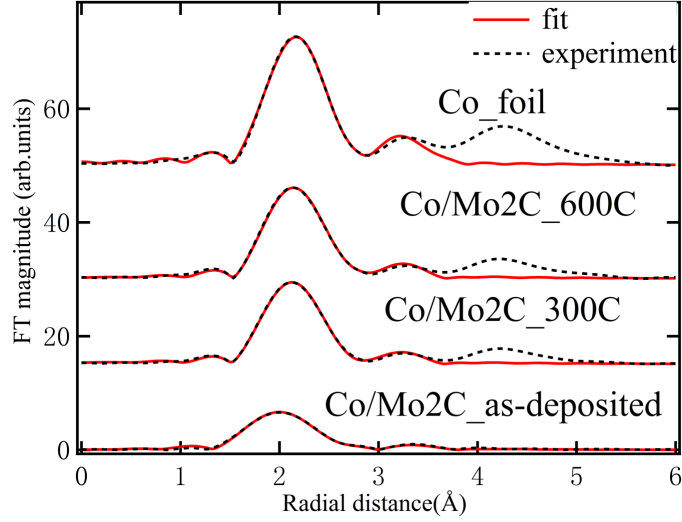


Fig. 2: The k^3 weighted Fourier transforms of the Co K-edge EXAFS spectra ($k=3$ to $10.15 \text{ \AA}^{-1}$) measured on the Co/Mo₂C multilayers (as-deposited, annealed at 300 and 600°C), and the Co foil reference. The fits were carried out in R-space in the interval of $[1.0, 5.0] \text{ \AA}$. For the sake of clarity, curves are vertically shifted.

Quantitative analysis of EXAFS spectra is performed to determine the local environment information of Co atoms: coordination number, atoms bond length. A hexagonal Co₃Mo phase (space group P63/mmc, lattice parameters $a=5.1245 \text{ nm}$, $b=5.1245 \text{ nm}$, $c=4.1125 \text{ nm}$ [20]) was used. In the fit procedure we introduced the parameters: amplitude reduction factor S_0^2 , zero energy shift ΔE_0 , atoms bond length R , Debye-Waller factors σ^2 . Four single scattering paths of Co atoms were used and yield an excellent fit for the region from 1.0 to 5.0 Å. In four single scattering paths, the amplitude reduction factor S_0^2 and zero energy shift ΔE_0 are defined to be consistent for each scattering path, the bond length R are defined independent, the Debye-Waller factors σ^2 of the first path are independent and others are be consistent.

The best fit is obtained with the hexagonal Co₃Mo phase theoretical model for the Co/Mo₂C multilayers (as-deposited, annealed at 300 and 600°C), shown in Fig. 2. A good fit is obtained in the R range of $[1.0, 5.0] \text{ \AA}$ for the Co/Mo₂C as-deposited sample and that of the other samples are in the interval of $[1.0, 3.5] \text{ \AA}$. This indicates that the local structure of Co atoms in the multilayers sample is close to that of the hexagonal Co₃Mo phase. The Co-Co coordination number of the first shell is obtained using four single scattering paths. Best fit values of the parameters are listed in Table 2 for the first shell. The results show that the coordination number of the first shell increases with the annealing temperature. The Debye-Waller factors σ^2 are decreasing, indicating the strong ordering of Co atoms upon annealing. The same results were reported by Chernov *et al.* in the Co/C

multilayer [10]. From the structural parameters of the EXAFS fit however it is not possible to determine if the Co_3Mo phase is fully formed or if only sub-scale crystallites are formed at the interfaces of the multilayer. We can only say that the local structure around the Co atoms is similar but not equal to the one in the Co_3Mo *hcp* phase.

In order to better understand the structure of the multilayer samples, the XAS spectra of the references, namely the CoMo (1 at.%), Co_3Mo , $\text{Co}_3\text{Mo}_3\text{C}$ and $\text{Co}_6\text{Mo}_6\text{C}$ solid solutions, are presented in Fig. 3 compared to the one of the Co foil. Here self-absorption correction of XAS spectra has been performed for the thick samples. In Fig. 3(a) and 3(b), the oscillations in the spectra of the solid solutions are poorly contrasted with respect to those of the pure Co foil reference, except that of the CoMo (1 at.%). The first maximum is reported at 7730 eV for the Co_3Mo , $\text{Co}_3\text{Mo}_3\text{C}$ and $\text{Co}_6\text{Mo}_6\text{C}$ solid solutions and 7734 eV for the Co foil and CoMo (1 at.%). The second and third ones are located at 7754 and 7803 eV respectively for the Co_3Mo , $\text{Co}_3\text{Mo}_3\text{C}$ and $\text{Co}_6\text{Mo}_6\text{C}$ solid solution samples while they are located at 7760 and 7808 eV respectively for bulk Co and CoMo (1 at.%). Near the edge, all spectra present a shoulder, whose intensity and positions vary depending on the sample (and on the self-absorption conditions). The shoulder position of the Co foil and CoMo (1 at.%) is located at around 7715 eV and around 7716 eV for the other samples. The shift is due to the change of Co oxidation state.

In Fig. 3(c), the spatial frequency in the k^3 -weighted k -space spectra slightly differs from one sample to another. In Fig. 3(d), the Co_3Mo , $\text{Co}_3\text{Mo}_3\text{C}$ and $\text{Co}_6\text{Mo}_6\text{C}$ show a weak coordination sphere peak corresponding to that of the Co foil. A closer examination of the R-space spectra of the $\text{Co}_3\text{Mo}_3\text{C}$ and $\text{Co}_6\text{Mo}_6\text{C}$ samples shows a shoulder toward the high radial distances, close to the first coordination sphere, which is located in between the first and second Co-Co coordination spheres of the Co foil. This indicates a local ordering trend of Co atoms inside the $\text{Co}_3\text{Mo}_3\text{C}$ and $\text{Co}_6\text{Mo}_6\text{C}$ samples.

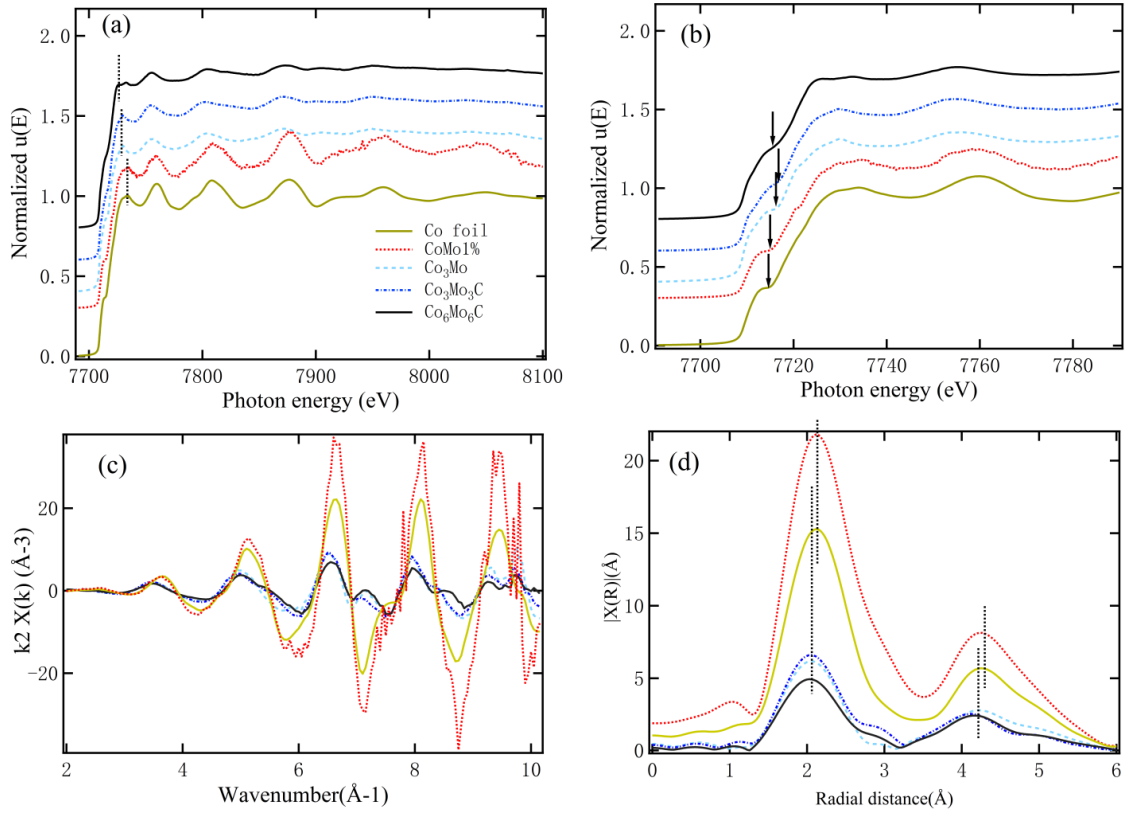


Fig. 3: Co K edge x-ray absorption measurement of the solid solution references, CoMo (1 at.%), Co_3Mo , $\text{Co}_3\text{Mo}_3\text{C}$ and $\text{Co}_6\text{Mo}_6\text{C}$, compared to the Co foil: (a) normalized EXAFS spectra; (b) normalized XANES spectra; (c) k^3 -weighted k -space spectra and (d) Fourier transform R -space spectra of EXAFS data. For the sake of clarity, curves are vertically shifted in (a) and (b).

In order to obtain further details on the chemical bond of the Co atoms within the multilayers, we compared in Fig. 4 the Co K edge XAS spectra of two references (Co foil and $\text{Co}_3\text{Mo}_3\text{C}$) and two multilayers (as-deposited and annealed at 600°C). In Fig. 4(a), the positions of the observed features for the as-deposited sample correspond to those of the Co foil but with different relative intensities. It is clear that for the as-deposited sample there is no pure Co in the stack [15]. Compared to $\text{Co}_3\text{Mo}_3\text{C}$, the as-deposited multilayer exhibits close EXAFS features, similar amplitudes but with different frequencies in the k^3 -weighted k -space spectrum, and similar low coordination numbers in the Fourier transform R -space spectra. This suggests that only the local atomic structure of the Co layer inside the as-deposited sample is similar to that of the solid solution $\text{Co}_3\text{Mo}_3\text{C}$. It can be deduced that in the as-deposited sample the Co layers are mixed with C and Mo atoms. Concerning the Co/ Mo_2C multilayer annealed at 600°C , the great similarities in the EXAFS and XANES spectra with respect to the Co foil point out a similar local environment of the Co atoms. This confirms our previous

results demonstrating that annealing leads to the ordering of the Co layer and the inherent increase of pure Co content.

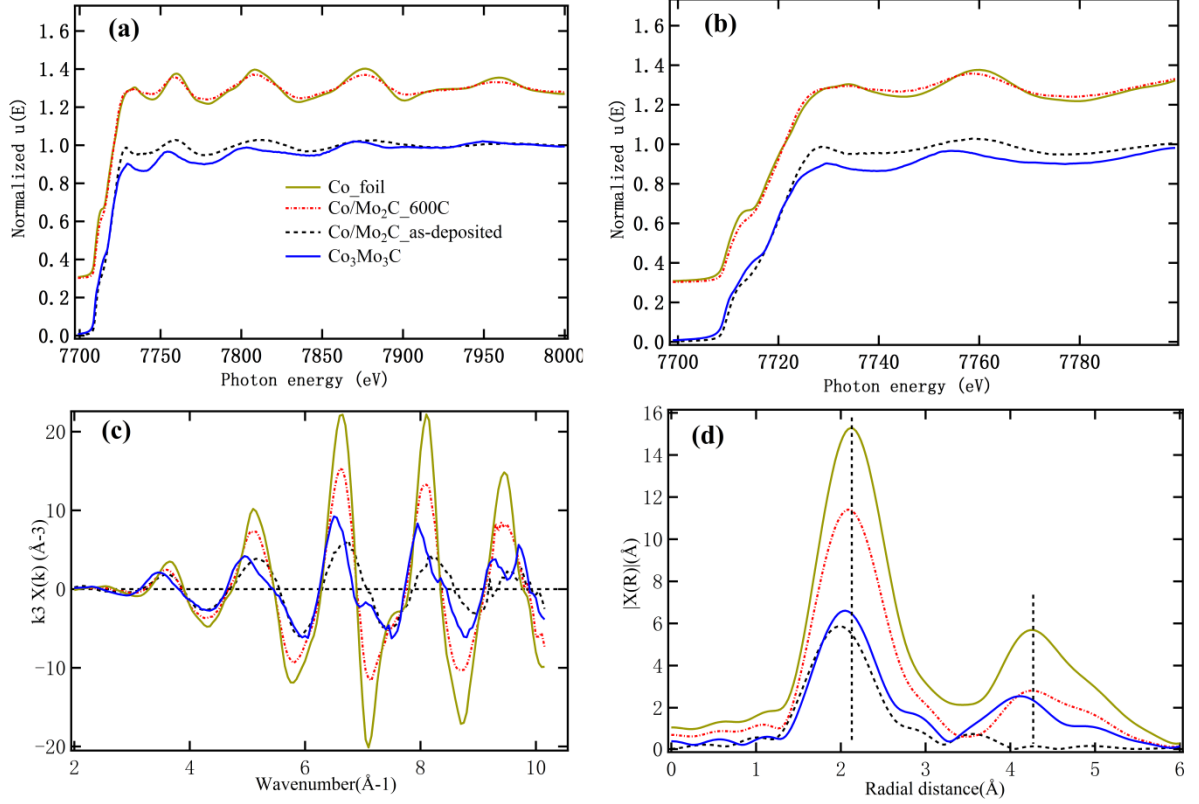


Fig. 4: Co K edge x-ray absorption measurement of two solid solution references, $\text{Co}_3\text{Mo}_3\text{C}$ and $\text{Co}_6\text{Mo}_6\text{C}$, and of two $\text{Co}/\text{Mo}_2\text{C}$ multilayers, as-deposited and annealed at 600°C : (a) normalized EXAFS spectra; (b) normalized XANES spectra; (c) k^3 -weighted k -space spectra and (d) Fourier transform R -space spectra of EXAFS data. For the sake of clarity, curves are vertically shifted in (a) and (b).

4. Conclusion

The XAS spectra of $\text{Co}/\text{Mo}_2\text{C}$ multilayer samples measured in the partial fluorescence mode were carried out at the Co K edge. The chemical environment of the Co atoms was studied by collecting the Co $K\alpha$ fluorescence signal. In light of all the above results, some significant spectra have been obtained for the differently annealed samples and for the reference materials. There is a clear distinction between the as-deposited and the annealed $\text{Co}/\text{Mo}_2\text{C}$ multilayer samples from the XAS spectra. This behavior is in agreement with the one measured through NMR experiments [15], where the mixing of the Co layers occurs for the as-deposited sample, whereas pure Co is observed upon annealing from 300°C . In addition we show that both Mo and C atoms of the Mo_2C layers are

involved in the mixing with the Co atoms. Moreover the quantitative analysis of the EXAFS data indicates a stronger local ordering of the Co layers following annealing. In conclusion, with the annealing process, demixing takes place in the Co and C mixing region and the layers become ordered, which results in the existence of pure Co region in the annealed samples.

Acknowledgments

This work is done under the framework of the international ANR-NSFC COBMUL project (ANR #10-INTB-902-01 and NSFC #11061130549) and Natural Science Foundation of China (#11061130549) and of the Cai Yuanpei Project (EGIDE PHC No. 30248NF), 973 program (No. 2011CB922203), and National Natural Science Foundation of China (Nos. 11375131 and 11305104).

References

- [1] H. Maury, P. Jonnard, J.-M. André, J. Gautier, F. Bridou, F. Delmotte and M.-F. Ravet, Interface characteristics of Mo/Si and B₄C/Mo/Si multilayers using non-destructive X-ray techniques, *Surf. Sci.*, 2007, *601*, 1, 2315–2322.
- [2] Q. Zhong, W. Li, Z. Zhang, J. Zhu, Q. Huang, H. Li, Z. Wang, P. Jonnard, K. Le Guen, J.-M. André, H. Zhou and T. Huo, Optical and structural performance of the Al(1% wtSi)/Zr reflection multilayers in the 17-19nm region, *Opt. Express*, 2012, *20*, 10, 10692–10700.
- [3] Y. Yacoby, E. A. Stern, Achievements and prospects in X-ray absorption spectroscopy, *AIP Conference Proceedings*, 1997; *389*, 535–556.
- [4] M. A. Mohiddon, K. L. Naidu, M. G. Krishna, G. Dalba, S. I. Ahmed and F. Rocca, Chromium oxide as a metal diffusion barrier layer: An x-ray absorption fine structure spectroscopy study, *J. Appl. Phys.*, 2014; *115*, 4, 044315.
- [5] R. V. Dennis, B. J. Schultz, C. Jaye, X. Wang, D. A. Fischer, A. N. Cartwright and S. Banerjee, Near-edge x-ray absorption fine structure spectroscopy study of nitrogen incorporation in chemically reduced graphene oxide, *J. Vac. Sci. Technol. B*, 2013; *31*, 4, 041204.
- [6] K. Amemiya and M. Sakamaki, NiO-like single layer formed on a Ni/Cu(001) thin film revealed by the depth-resolved x-ray absorption spectroscopy, *Appl. Phys. Lett.*, 2011; *98*, 1, 012501.
- [7] J. Jiménez-Mier, P. Olalde-Velasco, G. Carabalí-Sandoval, G. Herrera-Pérez, E. Chavira, W.-L. Yang and J. Denlinger, X-ray absorption to determine the metal oxidation state of transition metal compounds, *AIP Conference Proceedings*, 2013; *1544*, 78–85.
- [8] H. L. Bao, X. P. Sun, Z. Jiang, Y. Y. Huang and J. Q. Wang, Structural changes of Rh-Mn nanoparticles inside carbon nanotubes studied by X-ray absorption spectroscopy, *Chin. J. Catal.*, 2014; *35*, 8, 1418–1427.
- [9] M. Rovezzi, F. D'Acapito, A. Patelli, V. Rigato, G. Salmaso, E. Bontempi and I. Davoli, Characterization of thermally treated Mo/Si multilayer mirrors with standing wave-assisted EXAFS, *Nucl. Instrum. Methods Phys. Res. Sect. B Beam Interact. Mater. At.*, 2006; *246*, 1, 127–130.

- [10] A. Gupta, P. Rajput and C. Meneghini, Depth-resolved x-ray absorption fine structure study of Fe/Si interfaces using x-ray standing waves, *Phys. Rev. B*, 2007; 76, 19, 195401.
- [11] S. M. Heald and J. M. Tranquada, Standing - wave - assisted extended x-ray absorption fine-structure study of a Ni - Ti multilayer, *J. Appl. Phys.*, 1989; 65, 1, 290–293.
- [12] V. A. Chernov, N. I. Chkhalo, M. V. Fedorchenko, E. P. Kruglyakov, S. V. Mytnichenko and S. G. Nikitenko, Structural changes study of Co/C and Ni/C multilayers upon annealing, *J. X-Ray Sci. Technol.*, 1995; 5, 4, 389–395.
- [13] A. Chernov, N. I. Chkhalo, M. V. Fedorchenko, E. P. Kruglyakov, S. V. Mytnichenko and S. G. Nikitenko, Study of the inner structure of Co/C and Ni/C multilayers prepared by pulsed laser evaporation method, *J. X-Ray Sci. Technol.*, 1995; 5, 1, 65–72.
- [14] G. M. Lamble, S. M. Heald, D. E. Sayers, E. Ziegler and P. J. Viccaro, Tungsten-carbon multilayer composition and the effects of annealing: A glancing angle extended x-ray absorption fine structure study, *J. Appl. Phys.*, 1989; 65, 11, 4250–4255.
- [15] Y. Y. Yuan, K. Le Guen, J.-M. André, C. Mény, C. Ulhaq, A. Galtayries, J. T. Zhu, Z. S. Wang and P. Jonnard, Interface observation of heat-treated Co/Mo₂C multilayers, *Appl. Surf. Sci.*, 2015; 331, 8–16.
- [16] Y. Y. Yuan, K. Le Guen, J.-M. André, Z. Wang, H. C. Li, J. T. Zhu, C. Mény, A. Giglia, S. Nannarone and P. Jonnard, Co/Mo₂C multilayer as X-ray mirror: Optical and thermal performances, *Phys. Status Solidi B*, 2014; 251, 4, 803–808.
- [17] Y. Y. Yuan, Characterization of physico-chemical environment of Co-based multilayer mirrors working in the soft x-ray and EUV ranges, PhD thesis, 2014. <https://tel.archives-ouvertes.fr/tel-01080753>.
- [18] X. Gao, S. Gu, Q. Gao, Y. Zou, Z. Jiang, S. Zhang, X. Wei, H. Yu, G. Sheng, P. Duan and Y. Huang, A high-resolution X-ray fluorescence spectrometer and its application at SSRF, *X-Ray Spectrom.*, 2013; 42, 6, 502–507.
- [19] B. Ravel and M. Newville, ATHENA, ARTEMIS, HEPHAESTUS: data analysis for X-ray absorption spectroscopy using IFEFFIT, *Journal of Synchrotron Radiation*, 2005; 12, 537–541.
- [20] Refinement of the structure of the phase Co₃Mo, D'Alte da Veiga, L.M., *Acta Crystallographica* 1965; 18, 855-857.

Tab. 1: Structural parameters of the three multilayers derived from x-ray reflectivity data measured at 0.154 nm.

Sample	Period d (nm) prior annealing	Period d (nm) following annealing	Thickness/Roughness (nm) (± 0.05 nm)		
			B ₄ C	Co	Mo ₂ C
As-deposited	4.20	-	3.60/0.56	2.65/0.32	1.55/0.26
300°C	4.17	4.18	3.31/0.56	2.93/0.82	1.25/0.26
600°C	4.17	4.13	2.89/0.54	2.47/0.38	1.66/0.22

Table. 2: Parameters of the first coordination shell in Co/Mo₂C multilayers (as-deposited, annealed at 300 and 600°C) and the Co foil.

Sample	The first shell (Co-Co)		
	N	R(Å)	σ^2 (Å ²)
as-deposited	4(1)	2.41(9)	0.0125(3)
300°C	5(2)	2.46(4)	0.0084(4)
600°C	6(2)	2.49(2)	0.0089(7)
Co_foil	6(2)	2.47(4)	0.0038(2)

N: coordination number, R: neighbor atoms distance, σ^2 : Debye-Waller factor for individual shells. Uncertainty of the last digit is given in parentheses.