

Lipid-Stabilized Water–Oil Interfaces Studied by Microfocusing Small-Angle X-ray Scattering

Emanuela Di Cola, Kristian Torbensen, Ilaria Clemente, Federico Rossi,
Sandra Ristori, Ali Abou-Hassan

► **To cite this version:**

Emanuela Di Cola, Kristian Torbensen, Ilaria Clemente, Federico Rossi, Sandra Ristori, et al.. Lipid-Stabilized Water–Oil Interfaces Studied by Microfocusing Small-Angle X-ray Scattering. *Langmuir*, American Chemical Society, 2017, 10.1021/acs.langmuir.7b02076 . hal-01582631

HAL Id: hal-01582631

<https://hal.sorbonne-universite.fr/hal-01582631>

Submitted on 6 Sep 2017

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Lipid stabilized Water- Oil Interfaces Studied by Micro Focusing Small Angle X-ray Scattering

Emanuela Di Cola, Kristian Torbensen, Ilaria Clemente, Federico Rossi, Sandra Ristori, and Ali Abou-Hassan

Langmuir, **Just Accepted Manuscript** • DOI: 10.1021/acs.langmuir.7b02076 • Publication Date (Web): 17 Aug 2017

Downloaded from <http://pubs.acs.org> on August 28, 2017

Just Accepted

“Just Accepted” manuscripts have been peer-reviewed and accepted for publication. They are posted online prior to technical editing, formatting for publication and author proofing. The American Chemical Society provides “Just Accepted” as a free service to the research community to expedite the dissemination of scientific material as soon as possible after acceptance. “Just Accepted” manuscripts appear in full in PDF format accompanied by an HTML abstract. “Just Accepted” manuscripts have been fully peer reviewed, but should not be considered the official version of record. They are accessible to all readers and citable by the Digital Object Identifier (DOI®). “Just Accepted” is an optional service offered to authors. Therefore, the “Just Accepted” Web site may not include all articles that will be published in the journal. After a manuscript is technically edited and formatted, it will be removed from the “Just Accepted” Web site and published as an ASAP article. Note that technical editing may introduce minor changes to the manuscript text and/or graphics which could affect content, and all legal disclaimers and ethical guidelines that apply to the journal pertain. ACS cannot be held responsible for errors or consequences arising from the use of information contained in these “Just Accepted” manuscripts.



Lipid stabilized Water- Oil Interfaces Studied by Micro Focusing Small Angle X-ray Scattering

Emanuela Di Cola^a, *Kristian Torbensen*^b, *Ilaria Clemente*^c, *Federico Rossi*^d, *Sandra Ristori*^{c*},
and Ali Abou-Hassan^{b*}

a) Laboratoire Interdisciplinaire de Physique, Université Grenoble-Alpes, 38402 Saint-Martin-
d'Hères, France

b) Sorbonne Universités, UPMC Univ Paris 06, UMR 8234, Laboratoire Physico-chimie des
Electrolytes, Nanosystèmes Interfaciaux (PHENIX), 75252 Paris cedex 05 – France

c) Department of Chemistry and Biology, University of Salerno, Fisciano (SA), Italy

d) Department of Chemistry & CSGI, University of Florence, 50019 Sesto Fiorentino, Italy

*corresponding authors: sandra.ristori@unifi.it ; ali.abou_hassan@upmc.fr

Abstract

Water in oil (w/o) simple emulsions are dispersed micro-confined systems which find applications in many areas of advanced materials and biotechnology, such as food industry, drug delivery and cosmetics, to name but a few. In these systems, the structural and chemical

1
2
3 properties of the boundary layer at the w/o interface are of paramount importance to determine
4 functionality and stability. Recently, microfluidic methods have emerged as a valuable tool to
5 fabricate monodisperse emulsion droplets. Due to the intrinsic flexibility of microfluidics,
6 different interfaces can be obtained, and general principles governing their stability are needed to
7 guide the experimental approach. Herein, we investigate the structural characteristics of the
8 region encompassing the liquid/liquid (L/L) interface of w/o emulsions generated by a
9 microfluidic device in the presence of the phospholipid 1,2-dimyristoyl-sn-glycero-3-
10 phosphocholine (DMPC), and other intercalating amphiphiles (dopants), using microfocused
11 small angle X-rays scattering (μ -SAXS). We show that phospholipids provide a stable and
12 versatile boundary film of ~ 100 μm , whose basic units are swollen and uncorrelated DMPC
13 bilayers. The internal arrangement of this interfacial film can be tuned by adding molecules with
14 a different packing parameter, such as cholesterol, which is able to increase the stiffness of the
15 lipid membranes and trigger inter-bilayer correlation.
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38

39 KEYWORDS Liquid/liquid interface, simple emulsions, micro-SAXS, microfluidics, DMPC
40 membranes.
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Introduction

Interfaces are the boundary layers which separate different bulk regions of matter, controlling their mutual confinement and boundary properties, such as interfacial tension and partition coefficients of solvated species. With respect to bulk phases, these layers present peculiar chemical, physical and biological properties that have drawn the interest of researchers from many different fields.¹ Simple emulsions, where aqueous droplets are dispersed in an oil phase, (w/o emulsions or, *vice versa*, o/w emulsions) are typical examples of systems exhibiting high interfacial area to volume ratio. These systems are well suited to study the crossing of chemical species between liquid regions with different hydrophilic character and curved interface. Moreover, simple emulsion are the object of great practical interest, since they have found applications in many technological areas, including food industry, pharmaceuticals and cosmetics.² Generally, w/o

and o/w emulsions are thermodynamically unstable, and surfactants, such as biocompatible phospholipids,^{3,4} polymers⁵ or colloidal particles,^{6,7} can be used as stabilizing agents. In particular, phospholipids are an attractive class of compounds for biomedical applications and they have been used as emulsion stabilizers in drug delivery.^{8,9,10,11} The majority of these works report on o/w droplets, which are well suited for enhancing bioavailability of poorly water soluble drugs. However, high resolution (nm or molecular level) studies are difficult to be performed, due to the complexity and limited stability of these systems. The kinetics of droplet evolution has been thoroughly studied, since it governs the stability of the system toward coalescence.^{12,13}

As for the structural and chemical properties of droplet assemblies, it is well established that the amphiphilic layer at the liquid/liquid interface plays a key role in determining both the emulsion stability toward coalescence,

1
2
3 and the permeability of different species
4 solvated in the bulk regions. The rigidity and
5 lateral homogeneity of lipid bilayers can be
6 modified by adding sterols or other molecules
7 with a rigid core, which are able to induce the
8 formation of rafts and defects in the lipid
9 matrix. Sterols are also considered suitable
10 components of artificially made bilayers,
11 since they occur naturally in biological
12 membranes.^{14,15} In particular, cholesterol is a
13 major constituent of the plasma membranes in
14 eukaryotic micro-organisms, and its use
15 allows to build up realistic models for cell
16 membranes. Furthermore, it is interesting to
17 investigate whether cholesterol perturbs the
18 structure of the limiting layer in simple w/o
19 emulsions, since the occurrence of defects in
20 the interfacial membrane can influence the
21 permeation of species able to undergo passive
22 diffusion. The properties of the droplet
23 surface depend not only on the nature and
24 composition of the stabilizing layer, but also
25 on the method used to build-up the interfacial

film. Bulk emulsification procedures,
involving drop breakup by shear or impact
stress generated by mechanical agitation,
have been described for the preparation of
emulsions.^{16,17} However, the obtained
emulsions may present high dispersity,
resulting in poorer performance and/or lower
stability, thus limiting the extent of
applications. Recently, microfluidics has
emerged as a versatile technique to generate
monodisperse emulsions with high
throughput, and enhanced control over the
emulsion design, in particular when the
interface is constituted by a lipid-based
layer.¹⁸⁻²⁰

Here, with the aim to reach a deeper
understanding of the structural properties of
these systems, we investigated the structure
of the region surrounding the liquid/liquid
(L/L) interface of w/o emulsions generated by
a microfluidic device in the presence of
amphiphilic molecules, by using
microfocused small angle X-rays scattering

1
2
3 (μ -SAXS). Previous studies combining
4 microfluidic devices with X-ray focused
5 beams have demonstrated, that the
6 complementarity of the two techniques
7 represents a powerful tool to follow up
8 structural changes with high spatial and
9 temporal resolution.^{21,22,23} By using focused
10 X-rays, raster scanning of the sample can be
11 performed, allowing a comprehensive study
12 of a heterogeneous sample with real-space
13 resolution only limited by the beam
14 size.^{24,25,26} To the best of our knowledge this
15 is the first study probing the L/L interface of
16 a single droplet by μ -SAXS.

17
18 We show that phospholipids provide a stable
19 and versatile boundary layer, whose
20 properties can be tuned by adding dopants to
21 modify the interface stiffness and charge.

22 The lipid layer was fabricated using
23 dimyristoyl-phosphatidylcholine, with and
24 without cholesterol added as a rigidity
25 modulator. We also included a positive or a
26 negative charged lipid dopant, since ionic

lipids are known to affect the membrane
lamellarity.²⁷⁻²⁹

Experimental section

Materials.




1,2-dimyristoyl-sn-glycero-3-phosphocholine (DMPC) was purchased from Lipoids Inc. Cholesterol (CHOL), myristic acid (Myr-A), sodium tetradecylsulfate (STS) tetradecylamine (TDA), *tert*-butyltrichlorosilane and polyvinyl alcohol (PVA) were all purchased from Sigma-Aldrich. The chemical structure of these compounds is reported in Table 1

Sample preparation

Simple water-in-oil (w/o) emulsion droplets were generated in a microfluidic device consisting of an inner polyimide coated 365/75 μm (outer diameter [OD]/inner diameter [ID]) borosilicate capillary tube, inserted in an outer 1/0.5 mm (OD/ID) borosilicate capillary tube.

A coaxial flow was obtained by pumping in the outer tube a mixture of an oil phase made by chloroform/cyclohexane 1:2, v/v and 1% w/w DMPC, flow rate of 20 $\mu\text{L min}^{-1}$ (flow rate = 10 $\mu\text{L min}^{-1}$), while the inner tube, contained an aqueous 2% w/w PVA solution.

Table 1. Chemical structure the compounds used in this work

Commercial name	Chemical structure
Cholesterol	
Myristic acid	$\text{CH}_3(\text{CH}_2)_{11}\text{CH}_2\text{COOH}$
Sodium tetradecylsulfate	$\text{CH}_3(\text{CH}_2)_{12}\text{CH}_2\text{O}-\text{S}(=\text{O})_2\text{ONa}$
Tetradecylamine	$\text{CH}_3(\text{CH}_2)_{12}\text{CH}_2\text{NH}_2$
DMPC	
Polyvinyl alcohol	
<i>tert</i> -butyltrichlorosilane	$\begin{array}{c} \text{H}_3\text{C} \quad \text{Cl} \\ \quad \\ \text{H}_3\text{C}-\text{C}-\text{Si}-\text{Cl} \\ \quad \\ \text{H}_3\text{C} \quad \text{Cl} \end{array}$

This resulted in separated w/o emulsions. PVA was added to the aqueous phase, since it is a well-known viscosity modulator frequently used in microfluidics, for example

in generation of more complex emulsions such as w/o/w double emulsions. Hence, considering comparison with the broad variety of systems using this viscosity modulator, PVA was also applied here. The droplets were collected in borosilicate capillaries of 0.3 mm (ID) and 10 μm wall thickness, in order to minimize the parasitic signal from the glass background. To obtain concave w/o interfaces, the inner walls of these tubes were rendered hydrophobic by filling them with a 2% (w/w) solution of *tert*-butyltrichlorosilane in toluene. After 2h, the tubes were rinsed with toluene, and oven dried at 70 $^\circ\text{C}$ for other 2h.

Microfocus SAXS data acquisition and analysis

Scanning micro-X-ray diffraction was performed at the ID13 beamline of ESRF (Grenoble, France). A monochromatic X-ray beam ($\lambda = 0.095372$ nm) was focused down to a $1.5 \times 1.5 \mu\text{m}^2$ spot at the desired sample position, using a combination of Beryllium-

1
2
3 compound refracting lenses (Be-CRL
4 translocator). The sample to detector distance
5
6 was 0.941 m, corresponding to a q -range of
7
8 $0.2 < q < 8 \text{ nm}^{-1}$, with q being the scattering-
9
10 vector defined as $q = (4\pi/\lambda) \sin(\theta/2)$ and θ is
11
12 the scattering angle, i.e. the angle between the
13
14 scattered and incident radiation. One- or two-
15
16 dimensional beam raster scans covering the
17
18 emulsion interfaces were performed in
19
20 transmission geometry. At each raster step, a
21
22 scattering pattern was collected by the
23
24 DECTRIS EIGER 4M single photon counting
25
26 detector, providing frames of 2070×2167
27
28 pixels ($75 \times 75 \mu\text{m}^2$ pixel size) at rates up to
29
30 750 Hz. Radiation damage was observed after
31
32 about 0.2 s irradiation. Exposure times were
33
34 hence limited to 0.1 s/raster point. Microfocus
35
36 SAXS was used to investigate the the lipid
37
38 layer surrounding simple emulsion droplets.
39
40 1-dimensional raster scans, with a step size of
41
42 $2 \mu\text{m}$, were performed in a direction axial to
43
44 the capillary tube, covering a region from 0.7
45
46 mm to 0.7 mm, with the droplet center as

zero-reference point. This allowed
investigating the microemulsion across both
w/o interfaces. An on-line microscope with
focal spot coinciding with the X-ray was used
to visualize the droplets, and design the raster
scans. The 2D-diffraction patterns were
azimuthally integrated to obtain 1D scattering
intensity profiles ($I(q)$ vs q), by using the
SAXS utilities package.³⁰

Results and discussion

The boundary lipid layer of simple w/o emulsions was probed by scanning across the interface with μ -SAXS. **Figure 1** shows the image of a typical droplet confined in the capillary (top). The corresponding imaging diffraction of the droplet interface is also represented (bottom). The scattering contribution from the capillary was subtracted in order to highlight the scattering signal from the water/oil interface. At a first glimpse, the 2D scans did not evidence any preferred orientation; this allowed excluding alignment

of the sample due to shearing effects once loaded in the capillary. The integrated intensity profiles recorded in the oil phase (containing pure DMPC or DMPC/CHOL), and in the water/PVA phase did not show any excess scattering, as typically observed for correlated or uncorrelated structures (**Figure 2**), indicating that both the oil and

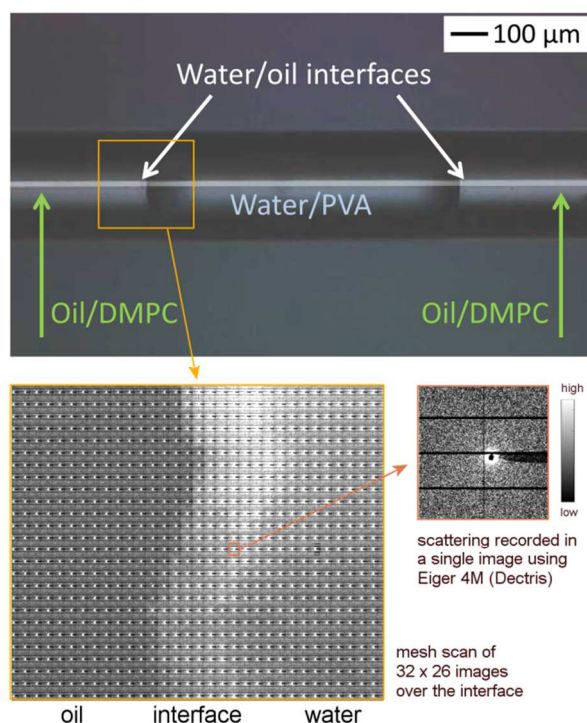


Figure 1. (top) w/o emulsion droplet of an aqueous solution of PVA (2%, w/w) in a mixture of chloroform/cyclohexane (1:2, v/v) containing 1% (w/w) DMPC, in a borosilicate capillary of 300 μm inner diameter, and wall thickness of 10 μm. (bottom) 2D reconstruction of the droplet interface by imaging diffraction.

water regions were isotropic media with no dispersed aggregates. In principle, reverse micelles could be expected in the oil phase, due to partial lipid solubility in the chloroform/cyclohexane mixture, while the aqueous phase could contain mixed micelles of lipids and cholesterol.

In sharp contrast to the inner and outer phases, the boundary layer was characterized by a diffuse scattering pattern, which extended for ~100 μm. The SAXS intensity profile along this distance had a q^{-2} decay in the intermediate q -range, a typical behavior of locally flat scattering objects. In this case, the scattering objects were localized at the interface, and were isotropically arranged over a mesoscopic scale of about 100 μm. In addition, the absence of a correlation peak in the SAXS patterns of the water/DMPC/oil system, was a clear indication that no (or very weak) correlation among these bilayers occurred in the w/o emulsions stabilized by pure DMPC. We could thus rule out the

possibility that in such a system, the basic structure was not a lamellar stacking (**Figure 2**, black filled triangles). In fact, if oligolamellar organization was present even in fractions as low as 3-5 % of the total lipid concentration, the extension of the raster beam would allow observing quasi-Bragg peaks superposed to the diffuse scattering of uncorrelated bilayers. The addition of moderate cholesterol (20% mol/mol) content to the oil/DMPC phase, resulted in the appearance of a fairly broad peak at $\sim 1 \text{ nm}^{-1}$ in the SAXS intensity profile (**Figure 2**, blue empty circles), which corresponded to a distance of 0.60–0.65 nm in the direct space. This is the characteristic repeat distance of DMPC lamellae,^{29,31} and indicated that cholesterol is able to induce marked stiffening of the bilayers, thus promoting inter-bilayer correlation within the interfacial membrane. Here, the contrast of the X-rays is at maximum, and the strong intensity indicated lipid self-assembly. For comparison, the

scattering profiles of different references are also shown in **Figure 2**.

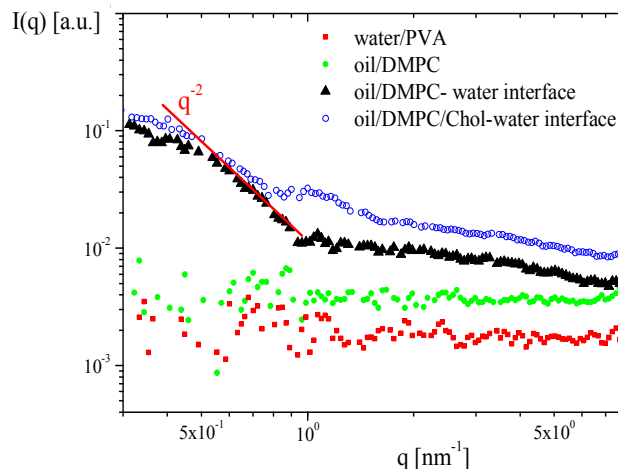


Figure 2. SAXS intensity profiles for simple w/o emulsion systems. The water/2% w/w PVA (red filled squares) and the oil/1% w/w DMPC (green filled squares) profiles represent bulk solutions far from the interface. The oil/1% w/w DMPC profile (black filled triangles) was recorded $\sim 50 \mu\text{m}$ from the w/o interface. The q^{-2} power decay is shown in the Figure. The blue empty circles represents the same scenario with 0.8/0.2 mol/mol DMPC/cholesterol (DMPC/CHOL).

The intensity recorded for each frame at the q -value of 0.5 nm^{-1} is reported in **Figure 3**, as a function of the scanned distance. The resulting profile clearly shows, that the increase in scattering intensity at this chosen q -value was extended for $\sim 100 \mu\text{m}$ into the

continuous (oil) phase. After the subtraction of the water background signal, the SAXS intensity patterns were fitted with the SasView freeware package.³² The best-fit profiles for the oil/DMPC-water (black filled triangles) and oil/DMPC/CHOL-water (blue empty circles) systems are shown in **Figure 4**, and correspond to the following best-fit parameters:

Scattering length density (SLD $\times 10^{-6} \text{ \AA}^{-2}$)

SLD heads = 10.6 ± 0.5

SLD tails = 4.0 ± 0.5

Head thickness = $4 \pm 0.2 \text{ \AA}$

Tail thickness = $40 \pm 1 \text{ \AA}$

Tail polydispersity = lognormal distribution with standard deviation $\sigma = 0.12$

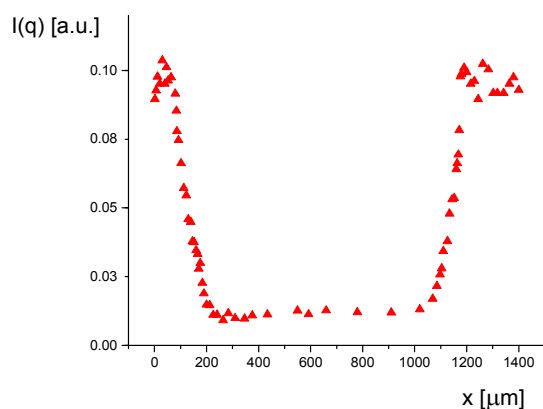


Figure 3. SAXS intensity at $q = 0.5 \text{ nm}^{-1}$, recorded at an axial line covering both the w/o interfaces of

the simple w/o emulsion system, showing an increased scattering intensity upon crossing the interfaces. The zero-reference point refers to the center of the aqueous drop.

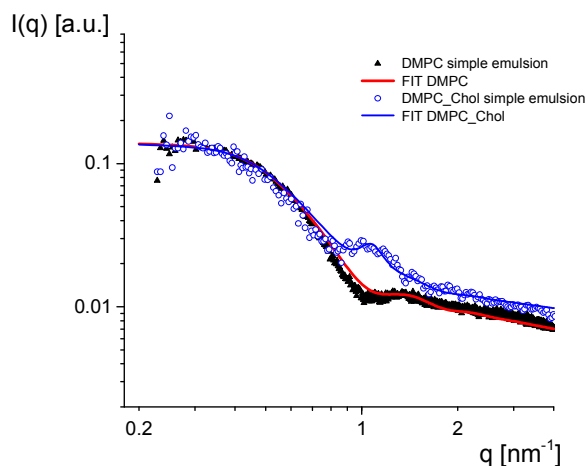


Figure 4. SAXS intensity profiles for the simple w/o emulsion system. The (black filled triangles) oil/1% w/w DMPC profile was recorded $\sim 50 \mu\text{m}$ from the w/o interface. The blue circles represent the same scenario for the system 4/1 mol/mol DMPC/cholesterol (DMPC/CHOL, blue empty circles). The best fit (solid lines) in each case was obtained with the parameters reported in the text. Water signal was subtracted from the scattering curves.

The best fit value obtained for the total bilayer thickness ($\sim 88 \text{ \AA}$) indicated extensive swelling of DMPC, since this value is almost twice as high compared to values reported in literature describing liposomes or lamellar

1
2
3 phases in aqueous media.³³⁻³⁶ This finding,
4
5 together with the low scattering length
6
7 density (SLD) of the tails, was consistent with
8
9 DMPC monolamellar membranes that
10
11 included cyclohexane in their inner
12
13 hydrophobic core. In the presence of
14
15 cholesterol at 20% mol/mol, the scattering
16
17 profile was satisfactorily reproduced by
18
19 introducing a model independent correlation
20
21 peak with a Lorentzian shape (HWHM = 0.13)
22
23 centered at 1.07 nm. As mentioned above,
24
25 this peak indicated that cholesterol induced
26
27 partial ordering in the bilayer arrangement.
28
29 We chose to perform this phenomenological
30
31 description rather than a more detailed
32
33 analysis, due to the numerous adjustable
34
35 parameters in this multicomponent system,
36
37 which might result in data over-interpretation.
38
39 Indeed, to give quantitative information on
40
41 the changes brought about by cholesterol in
42
43 the structural parameters, a range of different
44
45 molar ratios should be taken into account.
46
47 The observed effect, however, is well in

agreement with the rigidification usually
exerted by sterols in fluid lipid membranes,
such as DMPC bilayers at our working
conditions.³¹⁻³³

The scattering intensity profiles of DMPC
bilayers containing dopant amphiphiles, *i.e.*,
the curvature/surface charge modifiers Myr-
A, STS, TDA at 20% mol/mol content, are
shown in **Figure 5**. The structural features
observed do not significantly differ from the
case of pure DMPC, suggesting that the main
bilayer properties are retained after inserting
these intercalating agents in the lipid layers.
Noteworthy, still no sign of aggregation was
detected either in the external (oil) or internal
(water) micro phase of the droplets. The
overall profiles of the systems doped with
ionic surfactants were thus similar to those
reported in **Figure 3**. This proved that
changing the bilayer composition by
replacing 20% mol of DMPC with MyrA,
STS or TDA did not markedly affect the lipid

arrangement at the interface, nor the bilayer swelling.

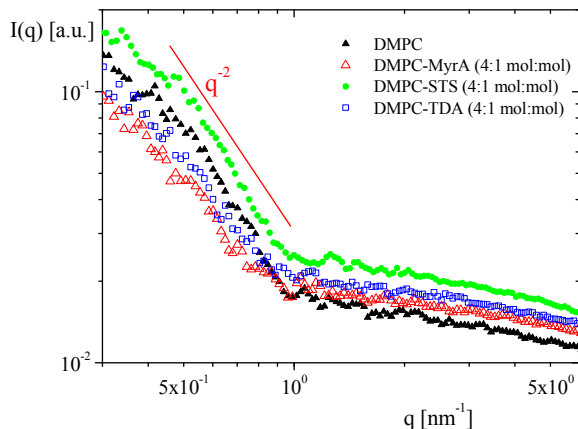


Figure 5. Scattering intensity profiles of pure DMPC and composite bilayers present at the oil/water interface. The ratios DMPC/Myr-A, DMPC/STs and DMPC/TDA are all 0.8/0.2 mol/mol.

Summary and Conclusions

Simple w/o emulsions represent a useful model for the studies of the structural properties of phospholipid membranes at the water/oil interface, and can be used to optimize emulsion systems applied in food industry, pharmaceuticals and cosmetics, and get insight on chemical communication among liposomes.^{37,38} Furthermore, they provide information on the issue of emulsion

stabilization with amphiphilic molecules and on the possibility to tune the properties of the interface. This is a relevant subject, due to the wide range of emulsion applications. Here, we studied the structural organization of DMPC-based layers surrounding aqueous droplets in an oil phase by Microfocus-SAXS measurements. In particular, we built monodisperse droplets by using a microfluidic device, and we modulated the stiffness and charge of the boundary lipid layers by adding amphiphilic dopants. The analysis of SAXS intensity profiles showed that at the oil/water interface lipids were self-assembled, and arranged into bilayer-based structures. On the contrary, no (inverse or direct) micelles were found in the bulk oil and water phases. Overall, the lipid layer had a thickness of ~ 88 Å, and was constituted by swollen DMPC. This extended layer almost lacked internal organization among bilayers. Therefore, we can speculate that phospholipids are arranged at the surface of a

1
2
3 simple emulsion droplet either as L_3 sponge
4 phase³⁹, or as polydisperse unilamellar
5 vesicles⁴⁰. We also found that the addition of
6 cholesterol increased the bilayer rigidity,
7 resulting in partial ordering and inter-bilayer
8 correlation, as it can be expected for sterols
9 intercalating a $L\alpha$ lipid phase. On the
10 contrary, the presence of amphiphilic
11 dopants, such as Myr-A, STS and TDA, did
12 not induce marked modifications to the
13 DMPC layer covering simple emulsions
14 droplets. These results will be useful for
15 future emulsion engineering by single droplet
16 manipulation. Moreover, the presence of
17 residual organic solvent in the phospholipid
18 bilayers, which is the cause of marked
19 swelling, is sure to have an effect on the

permeability of the interface, since it can
facilitate the crossing of more hydrophobic
species. The combined use of micro-focused
beam scattering techniques with
microfluidics, is undoubtedly of interest for
the community of researchers working with
w/o emulsions stabilized by lipids. We thus
believe, that this work can help advancing the
field of emulsion formulation, and contribute
to comprehend specific aspects of
communicative systems where lipid
membranes surround water confined
microdroplets.^{41,42}

20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
ACKNOWLEDGMENT The authors thank the
staff of ID13 (ESRF Grenoble) for their guidance
and keen interest throughout this work

Corresponding author

Sandra Ristori: sandra.ristori@unifi.it

Ali Abou-Hassan: ali.abou_hassan@upmc.fr

REFERENCES

(1) Eiseenthal, K.B. Liquid interfaces. *Acc. Chem. Res.* **1993**, *26*, 636-43. DOI: 10.1021/ar00036a005

(2) Israelachvili, J. The science and applications of emulsions — an overview. *Coll. Surf. A: Physicochem. Eng. Asp.* **1994**, *91*, 1-8. DOI: 10.1016/0927-7757(94)02743-9.

(3) Wiącek, A. E.; Adryńczyk, E. Interfacial Properties of Phosphatidylcholine-based Dispersed Systems. *Ind. Eng. Chem. Res.* **2015**, *54*, 6489–96. DOI: 10.1021/acs.iecr.5b01429

(4) Knoth, A.; Scherze, I.; Muschiolik, G.; Effect of lipid type on water-in-oil-emulsions stabilized by phosphatidylcholine-depleted lecithin and polyglycerol polyricinoleate. *Eur. J. Lipid Sci. Technol.* **2005**, *107*, 857–863. DOI: 10.1002/ejlt.200501205

(5) Surh, J.; Vladisavljević, G. T.; Mun, S.; McClements, D. J. Preparation and Characterization of Water/Oil and Water/Oil/Water Emulsions Containing Biopolymer-Gelled Water Droplets. *J. Agr. Food Chem.* **2007**, *55*, 175–184. DOI: 10.1021/jf061637q

(6) Ngai, T.; Bon, S.F.A. Eds. Particle-Stabilized Emulsions and Colloids: Formation and Applications, *RSC Soft Matter Series, No. 3*, Royal Society of Chemistry, Cambridge, UK, **2015**. DOI:10.1039/9781782620143

(7) Binks, B. P.; Tyowua, A. T. Particle-Stabilized Powdered Water-in-Oil Emulsions. *Langmuir*, **2016**, *32*, 3110–15. DOI:10.1021/acs.langmuir.6b00140

(8) Kawakami, S.; Yamashita, F.; Hashida, M. Disposition characteristics of emulsions and incorporated drugs after systemic or local injection. *Advanced Drug Delivery Reviews*, **2000**, *45*, 77-88. DOI:10.1016/S0169-409X(00)00102-2

(9) Lee, S.; Kim, D. H.; Needham, D. Equilibrium and dynamic interfacial tension measurements at microscopic interfaces using a micropipette technique. 1. A New Method for Determination of Interfacial Tension. *Langmuir*, **2001**, *17*, 5537–5543. DOI:10.1021/la0103259

(10) Lee, S.; Kim, D. H.; Needham, D. Equilibrium and dynamic interfacial tension measurements at microscopic interfaces using a micropipette technique. 2. Dynamics of Phospholipid Monolayer Formation and Equilibrium Tensions at the Water-Air Interface. *Langmuir*, **2001**, *17*, 5544–5550. DOI:10.1021/la0103261

(11) Grigoriev, D.O.; Miller, R. Mono- and multilayer covered drops as carriers. *Current Opinion in Colloid & Interface Science*, **2009**, *14*, 48-59. DOI:10.1016/j.cocis.2008.03.003.

(12) Baret, J. C.; Kleinschmidt, F.; El Harrak, A.; Griffiths, A. D. Kinetic Aspects of Emulsion Stabilization by Surfactants: A

Microfluidic Analysis. *Langmuir*, **2009**, *25*, 6088–6093. DOI:10.1021/la9000472

(13) Bahtz, J.; Gunes, D. Z.; Syrbe, A.; Mosca, N.; Fischer, P.; Windhab, E. J. Quantification of Spontaneous W/O Emulsification and its Impact on the Swelling Kinetics of Multiple W/O/W Emulsions *Langmuir*, **2016**, *32*, 5787–5795. DOI: 10.1021/acs.langmuir.6b00425

(14) Nes, W.R.; Role of sterols in membranes. *Lipids*, **1974**, *9*, 596-612. DOI:10.1007/BF02532509

(15) Korstanje, L.J.; van Ginkel, G.; Levine, Y.K. Effects of steroid molecules on the dynamical structure of dioleoylphosphatidylcholine and digalactosyldiacylglycerol bilayers, *Biochim Biophys Acta* **1990**, *1022*, 155-162. DOI:10.1016/0005-2736(90)90109-2

(16) Nakashima, T.; Shimizu, M.; Kukizaki, M.; Particle control of emulsion by

membrane emulsification and its applications.

Adv. Drug Delivery Rev. **2000**, *45*, 47-56.

DOI:10.1016/S0169-409X(00)00099-5

(17) Mason, T.G.; Bibette, J. Shear Rupturing of Droplets in Complex Fluids.

Langmuir, **1997**, *13*, 4600-13. DOI:

10.1021/la9700580

(18) Shah, R.K.; Shum, H.C.; Rowat, A.C.; Lee, D.; Agresti, J.J.; Utada, A.S.; Chu, L.-Y.; Kim, J.-W.; Fernandez-Nieves, A.; Martinez, C.J.; Weitz, D.A. Designer emulsions using microfluidics. *Materials Today*, **2008**, *11*, 18-

27. DOI:10.1016/S1369-7021(08)70053-1

(19) Courtois, F.; Olguin, L. F.; Whyte G.; Theberge, A. B.; Huck, W. T. S.; Hollfelder, F.; Abell, C. Controlling the Retention of Small Molecules in Emulsion Microdroplets for Use in Cell-Based Assays. *Anal. Chem.*, **2009**, *81*, 3008–16. DOI: 10.1021/ac802658n

(20) Akamatsu, K.; Kanasugi, S.; Nakao S.-I.; Weitz, D. A. Membrane-Integrated Glass

Capillary Device for Preparing Small-Sized Water-in-Oil-in-Water Emulsion Droplets.

Langmuir, **2015**, *31*, 7166–72. DOI:

10.1021/acs.langmuir.5b01514

(21) Ghazal, A.; Lafleur, J. P.; Mortensen, K.; Kutter, J. P.; Arleth, L.; Jensen, G. V.

Recent advances in X-ray compatible microfluidics for applications in soft materials and life sciences. *Lab Chip*, **2016**, *16*, 4263-4295.

DOI:10.1039/c6lc00888g

(22) Lutz-Bueno, V.; Zhao, J.; Mezzenga, R.; Pfohl, T.; Fischer, P.; Liebi, M. Scanning-SAXS of microfluidic flows: nanostructural mapping of soft matter. *Lab Chip*, **2016**, *16*, 4028-4035. DOI:10.1039/c6lc00690f

(23) Stehle, R.; Goerigk, G.; Wallacher, D.; Ballauff, M.; Seiffert, S. Small-angle X-ray scattering in droplet-based microfluidics. *Lab Chip*, **2013**, *13*, 1529-1537.

DOI:10.1039/C3LC41291A

(24) Reynolds, M.; Di Cola, E.; Sztucki, M.; Gourrier, A.; Montero, C.; Burghammer, M. Monitoring nanoparticle growth in a microreactor by combined micro-SAXS and micro-Raman techniques. Chapter 1: Nanoscale Material Characterization, In *Nanotechnology 2013*, Vol. 1, pp. 16-19, **2013**. DOI: 10.1680/bbn.11.00014

(25) Merlin, A.; Angly, J.; Daubersies, L.; Madeira, C.; Schoder, S.; Leng, J.; Salmon, J.-B. Time-resolved microfocused small-angle X-ray scattering investigation of the microfluidic concentration of charged nanoparticles. *The European Physical Journal E*, **2011**, *34*, 58. DOI:10.1140/epje/i2011-11058-y

(26) Brennich, M.; Koester, S. Tracking reactions in microflow. *Microfluidics and Nanofluidics*, **2014**, *16*, 39-45. DOI:10.1007/s10404-013-1212-y

(27) Kučerka, N.; Nieh, M.-P.; Pencer, J.; Harroun, T.; Katsaras, J., The study of

liposomes, lamellae and membranes using neutrons and X-rays. *Curr. Op. Coll. Interf. Sci.* **2007**, *12*, 17-22. DOI:10.1016/j.cocis.2006.11.006

(28) Pozo Navas, B.; Lohner, K.; Deutsch, G.; Sevcsik, E.; Riske, K.A.; Dimova, R.; Garidel, P.; Pabst, G. Composition dependence of vesicle morphology and mixing properties in a bacterial model membrane system. *Biochim. Biophys. Acta.* **2005**, *1716*, 40-48. DOI:10.1016/j.bbamem.2005.08.003

(29) Torbensen, K.; Rossi, F.; Pantani, O.L.; Ristori, S.; Abou-Hassan, A. Interaction of the Belousov-Zhabotinsky Reaction with Phospholipid Engineered Membranes. *J. Phys. Chem. B.* **2015**, *119*, 10224-30. DOI: 10.1021/acs.jpccb.5b04572

(30) <http://www.saxsutilities.eu>

(31) Hub, J. S.; Salditt, T.; Rheinstädter, M. C.; de Groot, B. L. Short-Range Order and

Collective Dynamics of DMPC Bilayers: A Comparison between Molecular Dynamics Simulations, X-Ray and Neutron Scattering Experiments. *Biophys. J.*, **2007**, *93*, 3156–68. DOI:10.1529/biophysj.107.104885

(32) SasView for Small Angle Scattering Analysis, <http://www.sasview.org/>.

(33) Pabst, G.; Katsaras, J.; Raghunathan, V.A.; Rappolt, M. Structure and interactions in the anomalous swelling regime of phospholipid bilayers. *Langmuir*, **2003**, *19*, 1716-22. DOI: 10.1021/la026052e

(34) Ristori, S.; Di Cola, E.; Lunghi, C.; Richichi, B.; Nativi, C. Structural study of liposomes loaded with a GM3 lactone analogue for the targeting of tumor epitopes. *BBA-Biomembr.* **2009**, *1788*, 2518-25. DOI:10.1016/j.bbamem.2009.10.005

(35) Kiselev, M.A.; Zemlyanaya, E.V.; Aswal, V.K. SANS study of unilamellar DMPC vesicles. The fluctuation model of a

lipid bilayer. *Crystallogr. Rep.* **2004**, *49*, S136-41. arxiv.org/abs/physics/0411047

(36) Pham, Q.D.; Topgaard, D.; Sparr, E. Cyclic and Linear Monoterpenes in Phospholipid Membranes: Phase Behavior, Bilayer Structure, and Molecular Dynamics. *Langmuir*, **2015**, *31*, 11067-77. DOI: 10.1021/acs.langmuir.5b00856

(37) Torbensen, K.; Rossi, F.; Ristori, S.; Abou-Hassan, A. Chemical Communication and Dynamics of Droplet Emulsions in Networks of Belousov–Zhabotinsky Micro-Oscillators Produced by Microfluidics. *Lab Chip* **2017**, *17*, 1179–1189. DOI: 10.1039/c6lc01583b


(38) Torbensen, K.; Ristori, S.; Rossi, F.; Abou-Hassan, A. Tuning the Chemical Communication of Oscillating Microdroplets by Means of Membrane Composition. *J. Phys. Chem. C* **2017**, *in press*. DOI: 10.1021/acs.jpcc.7b04615

1
2
3
4
5 (39) Roux, D.; Coulon, C.; Cates, M. E.
6
7
8 Sponge phases in surfactant solutions *J. Phys.*
9
10 *Chem.*, **1992**, *96*, 4174–4187. DOI:
11
12 10.1021/j100190a017
13
14

15 (40) Weiss, T. M.; Narayanan, T.; Wolf, C.;
16
17 Gradzielski, M.; Panine, P.; Finet, S.; Helsby,
18
19 W. I. Dynamics of the Self-Assembly of
20
21 Unilamellar Vesicles *Phys. Rev. Lett.*, **2005**,
22
23 *94*, 038303.
24
25
26
27 DOI:10.1103/PhysRevLett.94.038303
28
29


30 (41) Tomasi, R.; Noel, J.-M.; Zenati, A.;
31
32 Ristori, S.; Rossi, F.; Cabuil, V.; Kanoufi, F.;
33
34 Abou-Hassan, A. Chemical communication
35
36 between liposomes encapsulating a chemical
37
38 oscillatory reaction. *Chem. Sci.* **2014**, *5*, 1854-
39
40
41
42 59. DOI: 10.1039/C3SC53227E
43
44

45 (42) Rossi, F.; Zenati, A.; Ristori, S.; Noel,
46
47 J.M.; Cabuil, V.; Kanoufi, F.; Abou-Hassan,
48
49 A. Activatory Coupling Among Oscillating
50
51 Droplets Produced in Microfluidic Based
52
53
54
55 Devices. *Int. J. Unconv. Comput.* **2015**, *11*,
56
57
58 23-36. DOI:10.1039/C3SC53227E
59
60

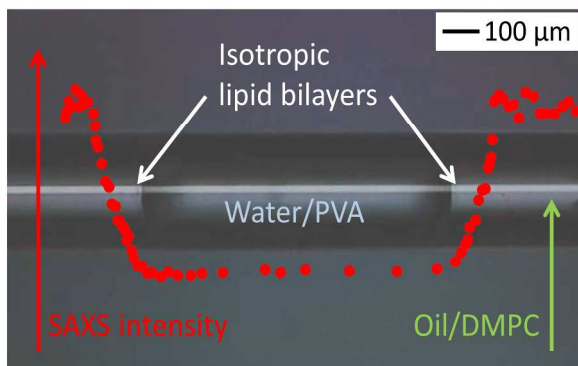

For Table of Contents Use Only

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

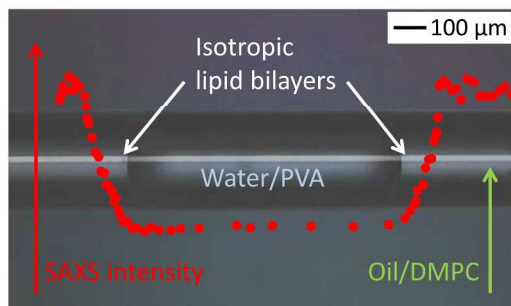

254x190mm (300 x 300 DPI)