



HAL
open science

Dependence of the interaction mechanisms between l-serine and O-phospho-l-serine with calcium hydroxyapatite and copper modified hydroxyapatite in relation with the acidity of aqueous medium

Kaia Tõnsuaadu, Michel Gruselle, Frieda Kriisa, Andres Trikkel, Patrick Gredin, Didier Villemin

► To cite this version:

Kaia Tõnsuaadu, Michel Gruselle, Frieda Kriisa, Andres Trikkel, Patrick Gredin, et al.. Dependence of the interaction mechanisms between l-serine and O-phospho-l-serine with calcium hydroxyapatite and copper modified hydroxyapatite in relation with the acidity of aqueous medium. *Journal of Biological Inorganic Chemistry*, 2018, pp.1-9. 10.1007/s00775-018-1594-0 . hal-01845481

HAL Id: hal-01845481

<https://hal.sorbonne-universite.fr/hal-01845481v1>

Submitted on 20 Jul 2018

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

1
2
3
4
5
6
7 Dependence of the interaction mechanisms between
8
9
10 L-serine and O- phospho-L-serine with calcium
11
12
13
14
15 hydroxyapatite and copper modified hydroxyapatite
16
17
18
19 in relation with the acidity of aqueous medium
20
21
22
23

24 Kaia Tõnsuaadu✉¹, Michel Gruselle^{2,3}, Frieda Kriisa¹, Andres Triikkel¹, Patrick Gredin^{3,4} and
25
26 Didier Villemin⁵
27
28
29

30 ¹ Institute of Materials and Environmental Technology, Tallinn University of Technology,
31
32 Ehitajate tee 5, 19086 Tallinn, Estonia
33
34

35 ² CNRS, UMR 8232, Institut Parisien de Chimie Moléculaire, 4 place Jussieu, F-75005 Paris,
36
37 France
38
39
40

41 ³ Sorbonne Université, UPMC Université Paris 06, 4 place Jussieu, F-75005 Paris, France
42
43

44 ⁴ Chimie Paris Tech, PSL Research Université, CNRS, Institut de Recherche de Chimie Paris, F-
45
46 75005 Paris, France
47
48
49

50 ⁵ LCTM, UMR 6507, ENSICAEN, INC3M, Fr 3038, Normandie Université, 14050 Caen,
51
52 France
53
54
55

56 ✉ kaia.tonsuaadu@ttu.ee; Fax: 372 6202801
57
58
59
60

1
2
3
4
5
6 ABBREVIATIONS
7
8
9

10 HAp, hydroxyapatite; CaHAp, calcium- hydroxyapatite; CuHAp, copper-substituted
11 hydroxyapatite; L-Ser, L-serine; O-Ph-L-Ser, O-phospho-L-serine; TA, thermal analysis.
12
13
14

15
16 ABSTRACT Motivated by the role of copper ions in biological processes the aim of this study
17 was to elucidate the impact of copper ions bound to hydroxyapatite on L-Serine (L-Ser) and O-
18 phospho-L-serine (O-Ph-L-Ser) adsorption at different acidity of aqueous solutions. The
19 adsorption phenomenon was studied by FTIR, UV, and AA spectroscopy, XRD and thermal
20 analysis methods together with the evolved gases analysis taking into consideration the ionic
21 state of the amino acids as well as the apatite surface state, which are tightly correlated with the
22 solution pH. In acidic solution, the main process involves apatite dissolution releasing calcium
23 and copper ions. At pH>5 the complexation of amino acids with Ca²⁺ or Cu²⁺ ions is more
24 important leading also to the release of cations. The ability of copper ions to form water soluble
25 complexes with L-Ser and O-Ph-L-Ser leads to an important loss of these ions, while calcium
26 release is very low at this pH. Therefore, the use of copper ions substituting calcium in the
27 apatite structure to enhance the ability of amino acids adsorption on the apatite surface seems
28 problematic even at pH>5.
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44

45
46
47 KEYWORDS Calcium hydroxyapatite; Copper modified hydroxyapatite; L-Serine; O-phospho-
48 L-serine; adsorption
49
50
51
52
53
54
55
56
57
58
59
60

1. Introduction

Hybrid organic-inorganic materials are of first importance in biological processes. Due to the role of apatites in the growth of human bones and teeth and in drug delivery, there is an increasing interest in studies related to the interactions between amino-acids and calcium apatites. Many works are devoted to the adsorption of organic and bioorganic molecules on the surface of apatites [1-5]. In general, these experiments, carried out at pH higher than 6, point out the fact that apatite surface is not fundamentally modified during the adsorption process, specifically, release of mineral ions like calcium or phosphate ions from the apatite structure are not taken into consideration in the interactions. Therefore, the role of bioorganic molecules, in particular, amino-acids (AA) as reagents to change composition of the mineral support, is neglected.

Particular interest among other AA has been paid on L-Serine (L-Ser) and O-phospho-L-serine (O-Ph-L-Ser) adsorption, which were characterized by Langmuir-type adsorption on apatite [6-10]. The studies carried out at pH 7-10 with L-Ser led to the conclusion that L-Ser adsorbs on the surface of hydroxyapatite (HAp) through electrostatic attractions exerted between one negative site of the HAp surface, i.e., phosphate or hydroxyl ion, and the positively charged protonated amino group of one Ser molecule, forming an ion pair surface complex [6,7].

O-Ph-L-Ser has higher affinity for the HAp surface compared to L-Ser molecules [7]. The enhanced adsorption capacity noted for O-Ph-L-Ser might be related to the presence of phosphate groups in the molecule, which are potential specific attachment sites. The mono-protonated negatively charged (HL^{2-}) O-Ph-L-Ser species were found adsorbed forming surface complexes with the positively charged $\equiv CaOH^{2+}$ sites on the surface of HAp at pH 7 [8]. The negatively charged deprotonated carboxyl and phosphate groups of the adsorbed HL^{2-} species

orient themselves at the maximum possible distance from the negatively charged surface of HAp because of electrostatic repulsions [9].

The only study performed in acidic O-Ph-L-Ser solutions [10] concluded that there occurs an ion-exchange between HAp and P-Ser in dilute solutions. The dissolution of apatite released phosphate and calcium ions into the solution in the amounts linearly related to the uptake of serine (<8 mM solution).

Taking into consideration that the drug delivery process is strongly influenced by the acidity of the biological medium, we decided to revisit the mechanisms of the adsorption of AA, namely L-Serine and O- Phospho-L-serine, shown in Fig. 1, with Ca-hydroxyapatite (CaHAp) and a copper modified Ca-hydroxyapatite (CuHAp) in relation with the acidity of the aqueous medium from acidic to smoothly basic one. The use of calcium apatites doped with copper ions is interesting to show the specific role that oxidation state II ions can play in sorption mechanism of AA. The question is therefore whether these ions will increase the ability of apatite to adsorb amino acids on the apatitic surface and by what mechanism. We first chose copper ions for their known role in biological and catalytic processes [11-13].

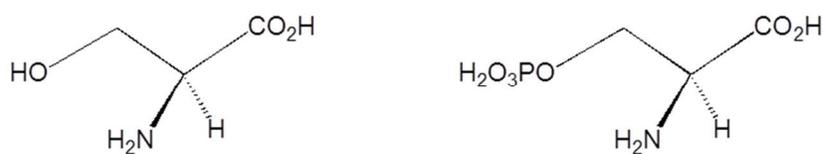


Fig. 1. L-Serine (left); O- Phospho-L-serine (right).

2. Experimental Section

2.1. Synthesis of CaHAp and CuHAp

The chemicals used for synthesis of apatites were of ACS grade, purchased from Sigma-Aldrich, Merck KGaA and Acros. The CaHAp was synthesized by precipitation in aqueous

1
2
3 solution using a PC-controlled LARA reactor system (Radleys) in deionized CO₂-free water at
4
5 25 °C in N₂ atmosphere keeping pH=9 by continuous addition of ammonia solution and keeping
6
7 Ca/P mole ratio equal to 1.67. The Ca(NO₃)₂ (0.5 M) and NH₄H₂PO₄ (0.3 M) solutions were
8
9 added simultaneously into NH₄OH aqueous solution (0.5 L). The obtained suspension was stirred
10
11 for 1 hour and matured for 24 hours at room temperature. The precipitate was filtered, washed
12
13 several times with deionized CO₂-free water and lyophilized. The Cu substituted apatite was
14
15 obtained mixing the washed CaHAp slurry in Cu-acetate solution (0.01 M) for 3 hours, after that
16
17 filtrated, washed and lyophilized.
18
19
20
21
22

23 24 2.2. Sorption experiments 25

26 L-Ser and O-Ph-L-Ser sorption experiments were performed with AA solutions in the range of
27
28 0.005 to 0.05 M in the pH interval from 2 to 8, adjusted by addition of 0.01 M KOH or 0.01 M
29
30 HNO₃ solution using automate titrator Mettler Toledo T90 with pH electrode DG-112 Pro. The
31
32 accuracy was ±0.02. The initial pH values were chosen according to the O-Ph-L-Ser solution
33
34 titration curve.
35
36

37 Apatite, 300 mg, was added to 50 ml of AA solution, mixed in centrifugal tube at overhead
38
39 mixer for 100 min and centrifuged. The experiments were performed in triplicate and the results
40
41 were averaged. After separation of the solid and liquid phases, pH and the cations content were
42
43 determined in the solution and the UV spectrum was recorded. The solid residue was dried at 60
44
45 °C and then subjected to XRD, FTIR and thermal analysis.
46
47
48
49
50

51 2.3. Analytical methods 52 53 54 55 56 57 58 59 60

1
2
3 XRD patterns were recorded with an INEL Equinox 1000 diffractometer operating in real time
4 acquisition over 2θ range $5 - 115^\circ$ in asymmetric mode. The diffractometer is equipped with a
5 cobalt anode and a primary graphite monochromator ($\lambda_{K\alpha 1} = 1.7889 \text{ \AA}$, $\lambda_{K\alpha 2} = 1.7928 \text{ \AA}$). The
6 2θ angular resolution is 0.029. The cell dimensions and average crystallite size were determined
7 by FULLPROF program [14].
8
9

10
11
12 FTIR spectra were recorded with a Bruker 55/S/NIR FTIR ATR spectrometer as an average of
13 30 scans at resolution 4 cm^{-1} .
14

15
16
17 The simultaneous TG/DTA/EGA-MS measurements were performed in an apparatus
18 consisting of a LabSys-Evo 1600 (Setaram, France) thermal analyzer and an OmniStar (Pfeiffer,
19 Germany) Quadrupole mass spectrometer. Coupling between the two components was provided
20 through a heated capillary tube kept at $T = 180 \text{ }^\circ\text{C}$. The ion currents of the selected mass/charge
21 (m/z) numbers were monitored in multiple ion detection (MID) mode (Quadera version 4.20
22 software) with the collection time of 1 s for each channel. The measurement was carried out in
23 Ar-O₂ (20%) mixture atmosphere in the temperature range of 30–1000°C using the heating rate
24 of $10 \text{ deg}\cdot\text{min}^{-1}$, the gas flow rate of $60 \text{ mL}\cdot\text{min}^{-1}$ and open Pt crucibles. The initial mass of
25 sample was 25-35 mg. The MS mass-to-charge ratios (m/z) selected for analysis were 15 for NH₃
26 to avoid the overlapping with H₂O, 18 for H₂O, 30 for NO_x (sum of NO, N₂O and NO₂) and 44
27 amu for CO₂.
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43

44
45 UV absorption spectra of the solutions in deionized water were recorded with Biochrom Libras
46 70PC UV/Visible Spectrophotometer in the wavelength interval from 190 to 400 nm with step 2
47 nm in quartz cuvettes of 10 mm path length using deionized water as reference.
48
49
50

51
52 The macro-components of the synthesis products were determined by standard analytical
53 methods. Content of Ca and Cu was determined after dissolution of sample in diluted HCl by
54
55
56
57
58
59
60

AAS (Varian SpectrAA 55B Flame AAS) and phosphorus by photo colorimetry method as phosphomolybdate yellow complex (Biochrom Libras 70PC UV/Visible Spectrophotometer).

The error in chemical analyses was under 2 %.

The specific surface area (SSA) measurements were performed by BET-method (adsorptive gas N₂, carrier gas He, heating temperature 110°C) using sorptometer EMS-53.

3. Results

3.1. Characterization of apatites

The XRD, FTIR and chemical analysis revealed that the materials obtained by precipitation were near-stoichiometric apatites, where cations/P mole ratio was 1.62 (Table 1, theory 1.67). XRD patterns and the unit cell parameters of the precipitated apatites, CaHAp and CuHAp, correspond well to a standard HAp (Diffraction standards ICDD card 00-055-0592) [14]. The unit cell parameters were $a = 9.413$ and 9.394 , $c = 6.860$ and 6.855 Å (± 0.001 Å), respectively. Decrease in unit cell parameters of CuHAp is in correlation with the smaller atomic radii of Cu in comparison with Ca. The average size of particles 110 (± 21) and 68 (± 17) nm correlates with the specific surface values 126 and 154 m²/g.

Table 1. Chemical composition and specific surface area of the apatites.

Apatite	(Ca+Cu)/P, Mole ratio	Ca, %	P, %	Cu, %	Specific surface area, m ² /g
CaHAp	1.62	38.25	18.28	0	126
CuHAp	1.62	36.10	17.54	0.91	154

1
2
3 To analyze the consequences of the interactions between the solid material and the AA
4 solutions, the changes in the solutions pH, the quantities of Ca and Cu ions released in the
5 solution during contact and the chemical and structural transformations of the apatite materials
6 were determined.
7
8
9
10
11

12 3.2. Analysis of solutions 13

14 3.2.1. Change of the AA solutions pH after contact with CaHAp and CuHAp 15

16 Due to various processes that occur at the solid surface/solution interface (preferential
17 dissolution of certain constituents of crystal lattice, ionization of surface groups, adsorption of
18 ions or formation of complex compounds between surface groups and ions from the solution),
19 the final pH values differ from the initial ones.
20
21
22
23
24
25

26 After mixing HAp – water suspension during 100 min the final pH values are found as 6.46
27 and 6.82 for CaHAp and CuHAp, respectively. The changes of pH values of the L-Ser and O-Ph-
28 L-Ser solutions as a result of the contact with apatite are presented in Suppl. mat. Fig. S1. The
29 bigger change occurs at low initial pH. The pH variation goes from the initial pH value 2 to a
30 value greater than 4. For L-Ser starting at pH 6 after mixing, the pH values increase in all the
31 studied cases by 0.5 to 1.25 pH units. When the initial pH is 8, after mixing, the change in all pH
32 values is -0.5 to -1.0. These trends show that the solution tends to return to the pH corresponding
33 to the point of zero charge (pzc). For O-Ph-L-Ser the same trends are observed. The bigger
34 change occurs at low pH, the pH variation goes from the initial pH=2 to a value greater than 4.
35
36
37
38
39
40
41
42
43
44
45
46

47 The pH value changes in correlation with the AA concentration and initial pH value. The
48 largest increase takes place at higher concentration and at initial pH <7. The pH change is almost
49 at the same level for both AA and apatites. At initial pH 8, the decrease up to -0.9 is followed,
50 which is more evident in L-Ser solutions.
51
52
53
54
55
56
57
58
59
60

3.2.2. Release of Ca^{2+} and Cu^{2+} .

The results concerning the release of Ca^{2+} and Cu^{2+} in aqueous solution when treating CaHAp and CuHAp by L-Ser or O-Ph-L-Ser are presented in Fig. S2. Ca^{2+} and Cu^{2+} release was 35 and 27 rel.%, accordingly, in L-Ser solution at pH 2. In L-Ser solution at pH 6 or 8, the Ca release is very low, especially, at pH 8, decreasing from 0.3-0.4% at pH 6 to 0.04-0.08% at pH 8. The release does not depend on L-Ser concentration. In the presence of AA the apatite solubility is a little lower than in pure water at pH>6 (0.12%) that is in agreement with the ability of AA to give complexes with calcium ions at the apatite surface [6]. In contrast with Ca^{2+} ions the release of Cu^{2+} ions is much higher, achieving 29.3% at pH 8. As a notable difference with Ca, the Cu release is independent on the initial pH of the solution.


Substantially higher Ca release occurs in O-Ph-L-Ser solutions. As expected, due to apatite dissolution, Ca content in solutions is the highest with initial pH 2. Ca relative solubility in water with HNO_3 was 10.61 and 12.74 rel.% for CaHAp and CuHAp, respectively. It increases from 12.8 to 63.1 rel.% for both apatites with the increase of AA concentration in solution from 0.01 to 0.05 M. The Ca solubility drops to 1-3 rel.% at pH 6 and 0-5 rel.% at pH 8. The Cu release has a minimum at pH 6 and the highest values at pH 2 and 8 that is more obvious for concentrations ≥ 0.02 M. Ca release is much higher than Cu release at pH 2, but above pH 6 the Cu release exceeds Ca release. Cu solubility in O-Ph-L-Ser solutions is a little lower than in L-Ser solutions.

3.2.3. UV spectroscopic analysis

Frequently, UV absorption measurements have been used for amino acid content determination in a solution [10]. Unfortunately, the shape of L-Ser and O-Ph-L-Ser absorption spectra depends not only on AA concentration but also on the content of other ions (NO_3^- , PO_4^{3-} , Cu^{2+}) and pH of

1
2
3 the solution (see Suppl. Mat. Fig. S3-S6). Therefore, the determination of amino acid
4 concentration by UV spectra is not reliable in the conditions when several variables as pH and
5 ions concentration are changing.
6
7
8
9

10 However, UV spectra revealed the formation of Cu-AA complexes in the solutions. In Fig. 2.
11 UV spectra of L-Ser containing 0.0015 mg Cu per 1 ml at different pH values (A) and the
12 intensities of the absorption peak at 246 nm depending on pH value of Cu-acetate, L-Ser + Cu-
13 ac., and O-Ph-L-Ser + Cu-ac. solutions (B) are presented. The intensity of the peak at 246 nm
14 that corresponds to Cu-AA complex, increases equally for both AA up to pH 6 and keeps this
15 value at higher pH. The peak intensity at 246 nm depends also on Cu²⁺ content in solution
16 (Suppl. Mat. Fig. S3). Therefore, Cu²⁺ release from apatite is related to its complexation with
17 AA.
18
19
20
21
22
23
24
25
26
27
28
29
30
31

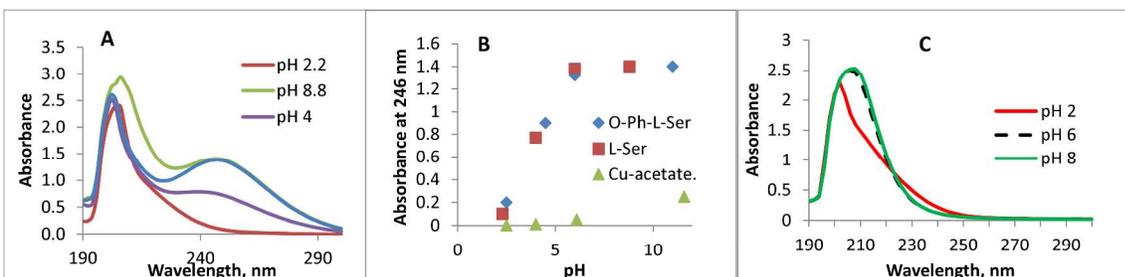

32
33
34
35
36
37
38
39
40
41
42
43 **Fig. 2.** A: UV spectra of 0.01 M L-Ser + 0.0015 mg Cu/ml at different pH. B: Absorption
44 intensity at 246 nm for Cu-acetate, L-Ser+Cu-ac., and O-Ph-L-Ser + Cu-ac. solutions depending
45 on pH. C: UV spectra of 0.02 M O-Ph-L-Ser at different pH.
46
47
48
49

50 51 3.3. Analysis of solid residue

52 53 3.3.1. XRD

1
2
3 The XRD analysis was performed for the samples treated with 0.02 M L-Ser and O-Ph-L-Ser
4 solutions. The results obtained from XRD patterns are presented in Suppl. Mat. Table S1.
5
6

7 The change of unit cell parameters as a result of interaction with L-Ser and O-Ph-L-Ser
8 solutions indicates the small changes in apatite crystal structure. Due to the reaction with L-Ser,
9 both unit cell parameters a and c increase while cell parameters of apatite remain almost
10 unchanged or decrease very slightly by interaction with O-Ph-L-Ser. Actually, these changes are
11 too small to be correctly interpreted.
12
13
14
15
16
17

18 3.3.2. FTIR spectroscopy

19 Comparison of the spectra recorded before and after amino acid sorption experiments reveals
20 very small changes in the apatite spectra. These spectra are shown in Figures 3 and 4. However,
21 some differences are found at wavelength intervals of 700-850 and 1300-1700 cm^{-1} .
22
23
24
25
26
27

28 In the spectrum of a mechanical mixture of CaHAp and L-Ser (5 %) the characteristic
29 absorptions of L-Ser and apatite are found at the same wavelength values that in the pure forms:
30 at 1586 cm^{-1} for CO_2^- (ν_{as}), at 1417 cm^{-1} for CO_2^- (ν_{s}), at 1600 cm^{-1} for COO^- (ν_{s}), at 1464 cm^{-1}
31 for NH_3^+ (ν_{s}), and at 1306 and 1342 cm^{-1} for CH groups vibrations [18]. In the spectra of the
32 material resulting from the sorption of L-Ser on apatite surface, an absorption peak at 1547 cm^{-1}
33 that could be assigned to COO^- (ν_{as}) [19] is visible. The absorption of carbonate substituted for
34 phosphate in apatite structure [20] or of NH_3^+ (ν_{s}) at 1453 cm^{-1} [7] is increased. A shoulder at
35 1630 cm^{-1} appears next to H_2O absorption at 1641 cm^{-1} in apatite structure, which has been
36 assigned to COO^- (ν_{as}) vibration shifted due to L-Ser adsorption on apatite [21] and absorption at
37 1329 cm^{-1} appears in spectra of samples treated at pH 2. These changes can be seen better for the
38 samples of CaHAp. No impact of the solution concentration is found.
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

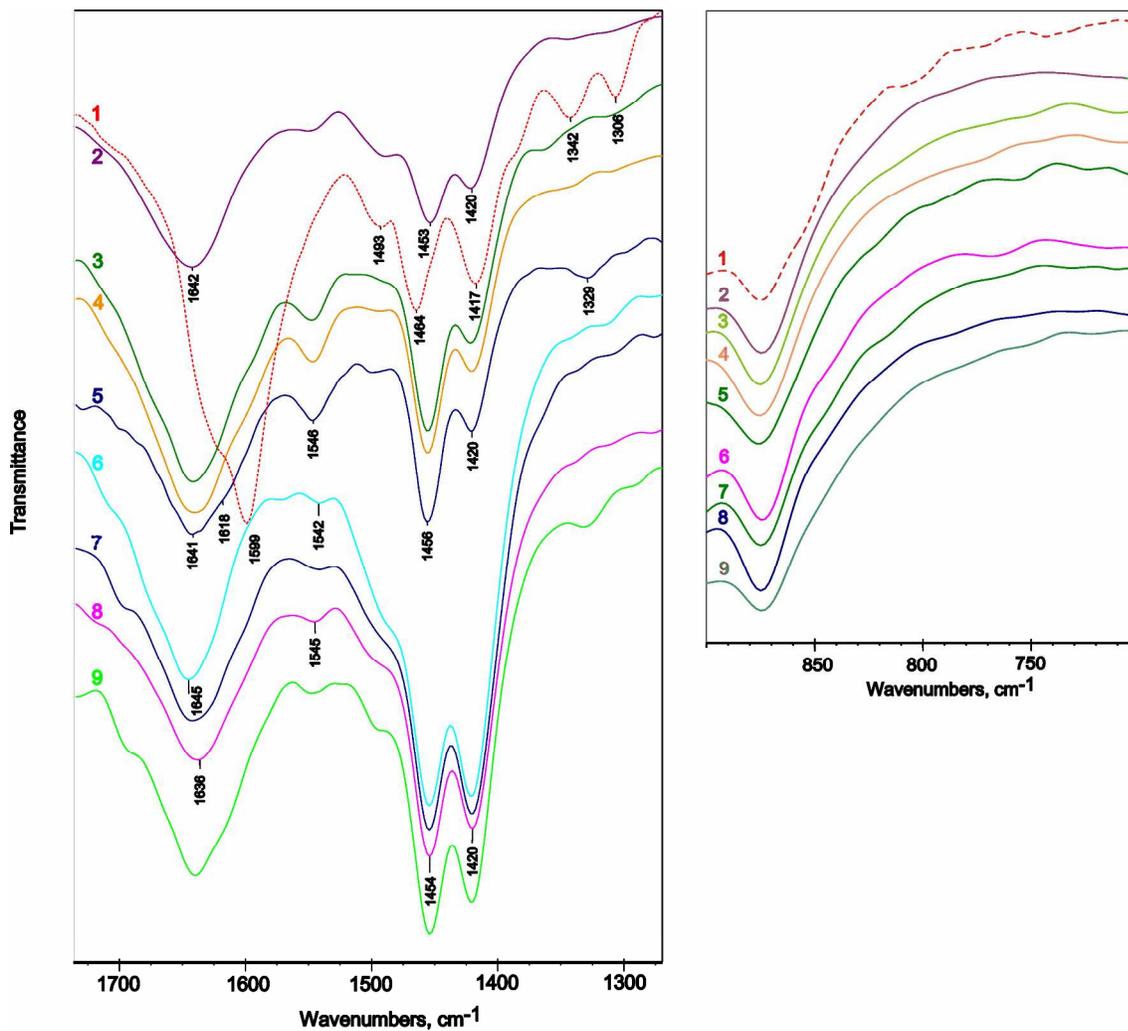


Fig. 3. FTIR spectra of CaHAp and CuHAp before and after sorption experiment in 0.02 M L-Ser solution and the mechanical mixture with 5% L-Ser. 1-CaHAp+ 5% L-Ser; 2- CaHAp; 3 - CaHAp+L-Ser pH 8; 4 - CaHAp+L-Ser pH 6; 5 - CaHAp+ L-Ser pH 2; 6 – CuHAp; 7 - CuHAp+L-Ser pH 8; 8 - CuHAp+L-Ser pH 6; 9 - CuHAp+L-Ser pH 2.

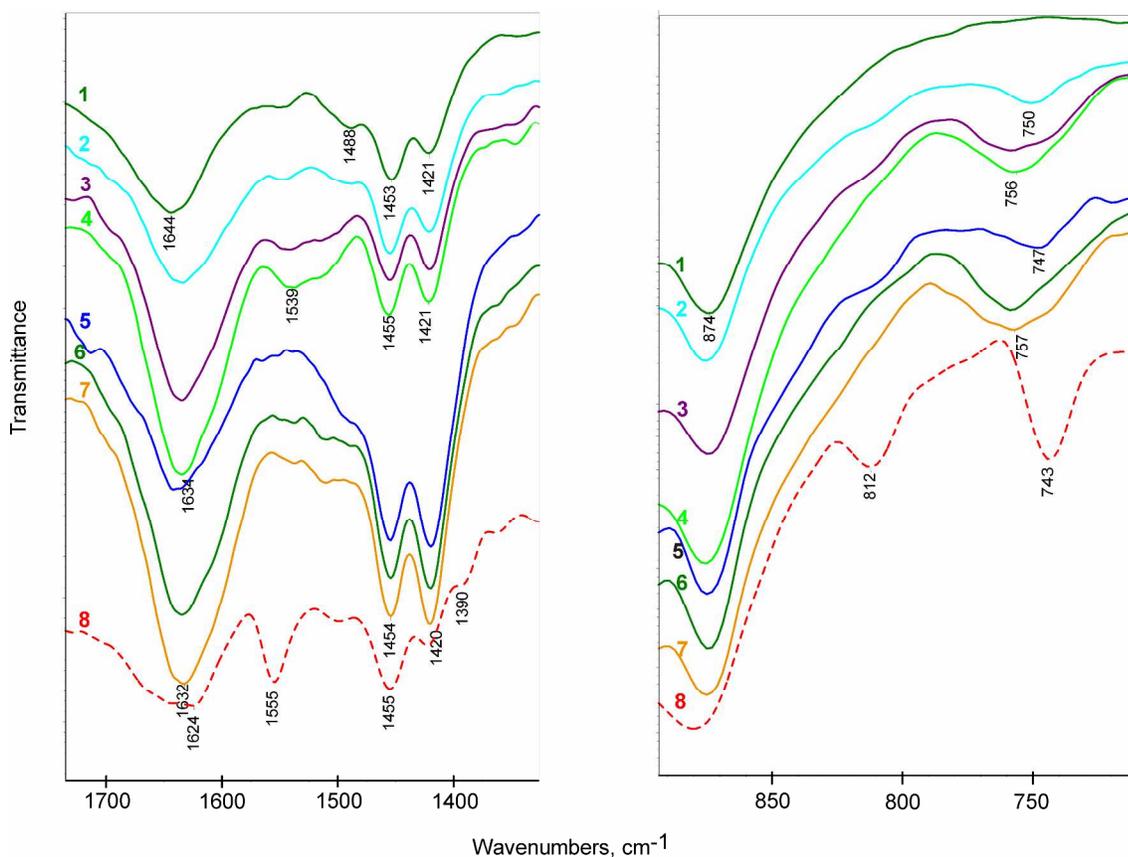


Fig. 4. FTIR spectra of CaHAp and CuHAp before and after sorption experiment in 0.02 M O-Ph-L-Ser solutions and the mechanical mixture with 5% O-Ph-L-Ser. 1 - CaHAp; 2- CaHAp+ O-Ph-L-Ser pH 8; 3 - CaHAp+ O-Ph-L-Ser pH 6; 4 - CaHAp+ O-Ph-L-Ser pH 2; 5- CuHAp+ O-Ph-L-Ser pH 8; 6 - CuHAp+ O-Ph-L-Ser pH 6; 7 - CuHAp+ O-Ph-L-Ser pH 2; 8 - CaHAp+ 5% O-Ph-L-Ser.

In the spectrum of a mechanical mixture of CaHAp and O-Ph-L-Ser (5 %) the absorption peaks of O-Ph-L-Ser, in addition to apatite peaks, are found at 1638, 1624, 1555, 1390, 1256, 812, 745 and 495 cm^{-1} . Changes in the spectra of CaHAp and CuHAp used for sorption of O-Ph-L-Ser differ from these caused by L-Ser adsorption. The new weak peaks at 1540 and 1516 cm^{-1} , particularly after reaction at pH 2, and the increase in peak intensity at 1420 cm^{-1} , related to


1
2
3 COO⁻ (ν_s) vibration [7,19], are followed in the spectra of O-Ph-L-Ser treated apatites.
4
5 Additionally, to the changes in the spectral region of 1300-1700 cm⁻¹, the peak at 745 cm⁻¹,
6
7 assigned to P-C (ν_s) [22], is shifted up to 762 cm⁻¹ depending on the final pH of the solution.
8
9 This peak intensity increases together with the O-Ph-L-Ser concentration and decrease in the
10
11 initial pH increase of the solution, similarly, to Ca release. The absorption peaks related to NH₃⁺
12
13 vibrations are less intensive but the changes related to COO⁻ vibration intensities are more
14
15 visible.
16
17

18 19 3.3.3. Thermal analysis

20
21 The thermal analysis (thermogravimetric analysis together with thermal changes and evolved
22
23 gas analyses) were performed with the aim to prove the adsorption of AA on apatite and also to
24
25 evaluate the amount of AA bound. The amount of organic matter in a solid sample was
26
27 determined from the amount of NO_x gases evolved at calcination detected by MS analysis. The
28
29 peak area under the NO_x evolution curve was measured and the normalized value was used as
30
31 an indicator of the amino acid content in the sample.
32
33

34
35 The mechanical mixtures of apatite and O-Ph-L-Ser or L-Ser with 3 and 5 mass % in it were
36
37 prepared for estimating the NO_x amount released at calcination from sorption experiment
38
39 samples. The results of TA are given in Figures 5 - 7. TA clearly exhibits the adsorption of L-Ser
40
41 and O-Ph-L-Ser on apatite by an exothermic effect with the maximum in the interval of 200-300
42
43 °C caused by the oxidation reaction of organic matter. In addition, the mass loss and the amount
44
45 of CO₂ and NO_x released, increases in comparison with the pure apatites (Fig. 5). The profile of
46
47 the curves changes together with the variation in the solution pH used (Fig. 6), indicating to
48
49 different sorption mechanism at different pH. The amount of NO_x evolved increases with the
50
51
52
53
54
55
56
57
58
59
60

1
2
3 increase in AA solution concentration and decreases with the increase in pH (Fig. 7). By TA
4
5 results the amount of AA adsorbed on CuHAp is almost the same as on CaHAp.
6
7

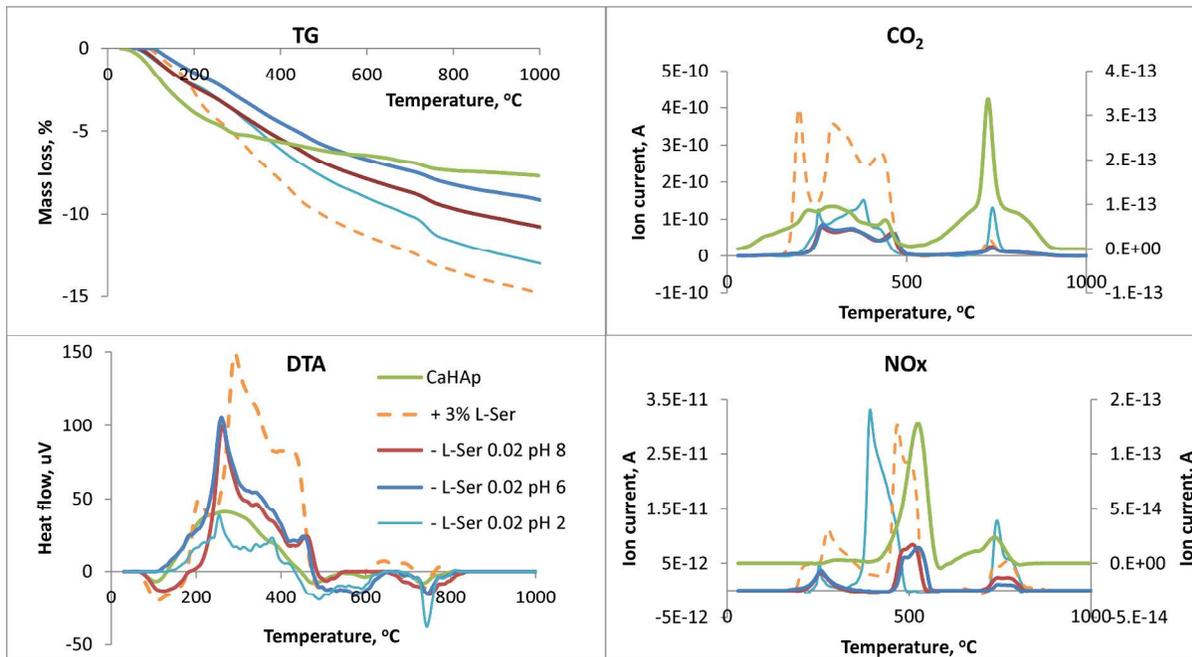

34
35 **Fig. 5.** Mass loss, DTA, CO₂ and NO_x evolution profile curves of CaHAp, mixture of
36 CaHAp+3% L-Ser and the samples after sorption experiment in 0.02 M L-Ser solutions at pH 2,
37 6 and 8.
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

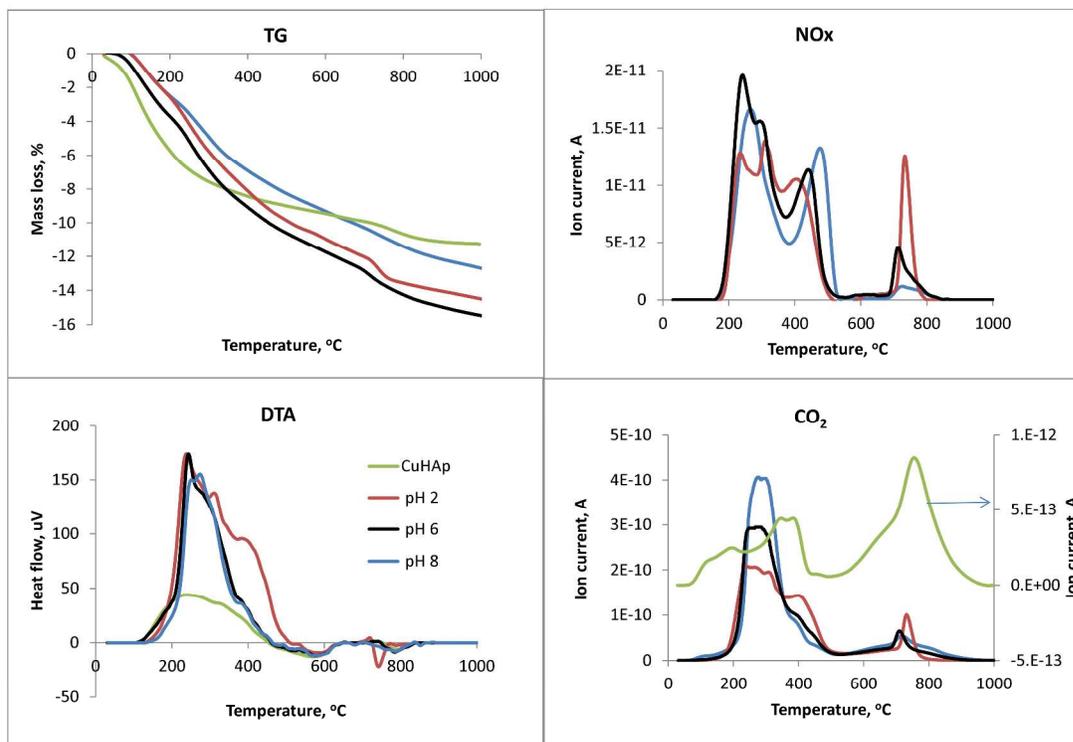


Fig. 6. DTA and mass loss curves of CuHAp and the samples after sorption experiment in 0.02 M O-Ph-L-Ser solutions at pH 2, 6 and 8.

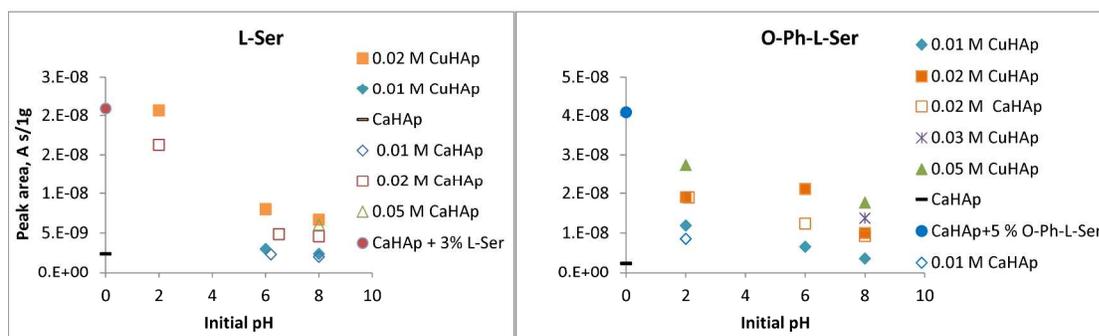


Fig. 7. The peak area of NO_x evolution from samples after L-Ser and O-Ph-L-Ser sorption experiment at calcination up to 1000 °C.

4. Discussion


To clarify phenomena at the apatite surface when opposed to AA at different pH in aqueous medium, the behaviour of both components must be taken into consideration:

1) The apatite surface properties, which depend on cations/P mole ratio and chemical composition and on the medium pH [23-25].

2) The ionization state of AA, which is strongly dependent on the medium acidity [26].

It is found that for the initial pH range 4–10, the final pH values of apatite water suspensions are close to the pH_{PZC} , which is the pH value where the surface charge is equal to zero, namely, the pH at which the charge due to the positive surface groups is equal to negative ones [27]. For the CaHAp and CuHAp used in the study pH_{PZC} were found to be 6.46 and 6.82, respectively. Above the pH_{PZC} the apatite surface is negatively charged, it is lightly positive at pH 6 and highly positive at pH 2, at which the apatite dissolves easily [28].

L-Ser appears in water solution at pH 2 partly in the form of neutral zwitterion and partly in the form of positively charged cation; at pH 6 as a neutral zwitterion and at pH 8 about 10 % of protons are neutralized and negatively charged $-COO^-$ groups are formed according to Scheme 1.

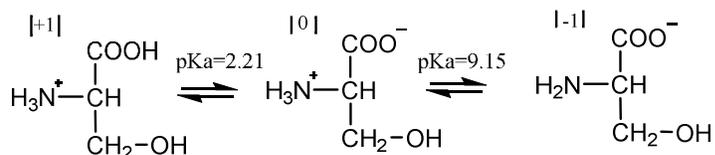

Scheme 1. Ser dissociation scheme [26].

Therefore, as a result of apatite dissolution in acidic medium the pH of L-Ser solution increases and the rest of $\text{HAp}^{[+]}$ is in equilibrium with L-Ser zwitterion, which enables complexation via COO^- groups. This explains the COO^- vibrations shifts in FTIR spectra (Fig.3).

1
2
3 Almost no electrostatic tension takes place between HAp and L-Ser in a solution at pH 6-8. L-
4 Ser can adsorb on hydroxyapatite surface only due to the complexation with surface cations. The
5 complexation constant $\log K_f$ of L-Ser is 1.43 and 7.90 for Ca^{2+} and Cu^{2+} , respectively [29]. The
6 higher $\log K_f$ of Cu^{2+} explains the much higher Cu release in comparison with Ca in sorption
7 experiments.
8
9

10
11
12 The changes in HAp IR spectra (appearance of a peak at 1546 cm^{-1} , Fig. 3), related to the
13 COO^- group complexation with Ca^{2+} sites at HAp surface, in contrast with the unchanged IR
14 spectra of CuHAp, as well as the high level of Cu^{2+} ions release, support the hypothesis of the
15 formation of soluble L-Ser-Cu complex.
16
17

18
19 The higher organic matter content in the samples after sorption experiments at lower pH values
20 (Fig. 7) can be explained by higher positive surface charge of apatite and, accordingly, higher
21 electrostatic tension in this case.
22
23

24
25 O-Ph-L-Ser does not form a typical $\text{COO}^- \text{--} \text{NH}_3^+$ zwitterion in water. Instead, one of the two
26 phosphate-bound protons dissociates upon dissolution of the crystalline O-Ph-L-Ser in water to
27 form a different $\text{HPO}_4^- \text{--} \text{NH}_3^+$ zwitterion. The three consecutive dissociation steps correspond to
28 the COOH , HPO_4^- , and NH_3^+ dissociation. Therefore, at pH 2 in O-Ph-L-Ser solution dominates
29 monobasic acidic form, at pH 6 there is a mixture of negative mono- and dibasic $\text{--OPO}_3\text{H}^-$
30 zwitterion and at pH 8 dibasic --OPO_3^{2-} zwitterion (Scheme 2).
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

5. Conclusions

The processes occurring on the apatite surface when treated by L-Ser and O-Ph-L-Ser aqueous solutions were clarified. To understand the adsorption phenomena, it is necessary to take into consideration the ionic state of the amino acid and that of the apatite surface which are tightly correlated with the pH value of the solutions. In acidic solutions the dominant process is apatite dissolution. At the same time, due to the electrostatic attraction, negatively charged ions of the amino acid are adsorbed on the apatite surface. The amino acids interaction with apatite at pH > 6 is mainly related to its complexation with cations of apatite structure. In accordance with the higher stability of soluble Cu^{2+} complexes, the relative release of Cu^{2+} ions from Cu substituted apatite is higher than that of Ca^{2+} ions in both amino acid solutions. Thereby, if the Cu release increases with the pH and O-Ph-L-Ser concentration increase, the Ca release drops remarkably at pH 8 in the case of P-Ser amount 1 mmol per 300 mg HAp. Impact of pH is less important for Cu release in L-Ser solution, the effect is more visible for Ca release in both AA solutions.

Acknowledgments

The current research was supported by the Estonian Ministry of Education and Research (Institutional research funding IUT33-19), CNRS, UPMC and TTU.

The authors thank Dr. Jamal Moussa for helpful discussions.

References

1. Šupová M (2015) Substituted hydroxyapatites for biomedical applications: A review. *Ceram Int* 41:9203-9231
2. El Rhilassi A, Mourabet M, Bennani-Ziatni M, El Hamri R, Taitai A (2016) Interaction of some essential amino acids with synthesized poorly crystalline hydroxyapatite. *J Saudi Chem Soc* 20:632-640
3. Errassifi F, Menbaoui A, Autefage H, Benaziz L, Ouizat S, Santran V, Sarda S, Lebugle A, Combes C, Barroug A, Sfihi H, Rey C (2010) In: *Advances in bioceramics and biotechnologies*. John Wiley & Sons Inc, pp 159-174
4. Ozhukil Kollath V, Van den Broeck F, Fehér K, Martins JC, Luyten J, Traina K, Mullens S, Cloots R (2015) A modular approach to study protein adsorption on surface modified hydroxyapatite. *Chem-Eur J* 21: 10497-10505
5. Errassifi F, Sarda S, Barroug A, Legrouri A, Sfihi H, Rey C (2014) Infrared, Raman and NMR investigations of risedronate adsorption on nanocrystalline apatites. *J Coll Interface Sci* 420:101-111
6. Spanos N, Klepetsanis PG, Koutsoukos PG (2001) Model Studies on the Interaction of Amino Acids with Biominerals: The Effect of L-Serine at the Hydroxyapatite-Water Interface. *J Coll Interface Sci* 236:260-265
7. Benaziz L, Barroug A, Legrouri A, Rey C, Lebugle A (2001) Adsorption of O-Phospho-L-Serine and L-Serine onto Poorly Crystalline Apatite. *J Coll Interface Sci* 238:48-53

- 1
- 2
- 3 8. Skartsila K, Spanos N (2012) Adsorption monitoring of phospho-l-serine on
- 4 hydroxyapatite. *Colloid Polym Sci* 290: 731-739
- 5
- 6
- 7
- 8 9. Spanos N, Koutsoukos PG (2001) Model Studies of the Effect of Orthophospho-L-serine on
- 9 Biological Mineralization. *Langmuir* 17:866-872
- 10
- 11
- 12
- 13 10. Misra DN (1997) Interaction of ortho-Phospho-l-serine with Hydroxyapatite: Formation of
- 14 a Surface Complex. *J Coll Interface Sci* 194:249-255
- 15
- 16
- 17
- 18 11. Festa RA, Thiele DJ (2011) Copper: An essential metal in biology. *Curr Biol* 21:877-883
- 19
- 20
- 21
- 22 12. Clavadetscher J, Hoffmann S, Lilienkamp A, Mackay L, Yusop RM, Rider SA, Mullins JJ,
- 23 Bradley M (2016) Copper Catalysis in Living Systems and In Situ Drug Synthesis. *Angew*
- 24 *Chem Int Ed Engl* 55:15662-15666
- 25
- 26
- 27
- 28 13. Chemler SR (2015) Copper catalysis in organic synthesis. *Beilstein J Org Chem* 11:2252-
- 29 2253.
- 30
- 31
- 32
- 33 14. Rodriguez-Carvajal J (2001) Recent developments of the program FULLPROF.
- 34 Commission on Powder Diffraction Newsletter 26:12-19.
- 35
- 36
- 37
- 38 15. Elliot JC (1994) Structure and chemistry of the apatites and other calcium orthophosphates.
- 39 Elsevier, Amsterdam
- 40
- 41
- 42 16. Frank-Kamenetskaya OV (2008) In: Krivovichev SV (eds) Minerals as advanced materials
- 43 I. Springer, Berlin Heidelberg, pp 241-252
- 44
- 45
- 46
- 47
- 48
- 49
- 50
- 51
- 52
- 53
- 54
- 55
- 56
- 57
- 58
- 59
- 60

- 1
2
3 17. Frank-Kamenetskaya O, Golubtsov V, Pikhur O, Zorina M, Plotkina YV (2004)
4 Nonstoichiometric apatite of the human dental hard tissues (the age alterations). Zap
5 Vseross Mineral O-va 5:120-130
6
7
8
9
10
11 18. Jarmelo S, Reva I, Carey P, Fausto R (2007) Infrared and Raman spectroscopic
12 characterization of the hydrogen-bonding network in L-serine crystal. Vib Spectrosc
13 43:395-404
14
15
16
17
18
19 19. Lee WH, Loo CY, Zavgorodniy AV, Rohanizadeh R (2013) High protein adsorptive
20 capacity of amino acid-functionalized hydroxyapatite. J Biomed Mater Res Part A 101:873-
21 883
22
23
24
25
26
27 20. Fleet ME (2014) Carbonated Hydroxyapatite: Materials, Synthesis, and Applications. Pan
28 Stanford Publishing, Singapore
29
30
31
32 21. Gonzalez-McQuire R, Chane-Ching J-Y, Vignaud E, Lebugle A, Mann S (2004) Synthesis
33 and characterization of amino acid-functionalized hydroxyapatite nanorods. J Mater Chem
34 14:2277-2281
35
36
37
38
39
40 22. Othmani M, Aissa A, Grelard A, Das RK, Oda R, Debbabi M (2016) Synthesis and
41 characterization of hydroxyapatite-based nanocomposites by the functionalization of
42 hydroxyapatite nanoparticles with phosphonic acids. Colloids Surf A 508:336-344
43
44
45
46
47
48 23. Tsuchida T, Kubo J, Yoshioka T, Sakuma S, Takeguchi T, Ueda W (2008) Reaction of
49 ethanol over hydroxyapatite affected by Ca/P ratio of catalyst. J Catal 259:183-189
50
51
52
53 24. Bengtsson Å, Sjöberg S (2009) Surface complexation and proton-promoted dissolution in
54 aqueous apatite systems. Pure Appl Chem 81:1569-1584
55
56
57
58
59
60

- 1
2
3 25. Garcia Rodenas L, Palacios J. M, Apella MC, Morando PJ, Blesa MA (2005) Surface
4 properties of various powdered hydroxyapatites. *J Coll Interface Sci* 290:145-154
5
6
7
8 26. Fleck M, Petrosyan AM (2014) Salts of amino acids: crystallization, structure and
9 properties. Springer
10
11
12
13 27. Smičiklas I, Milonjić S, Pfendt P, Raičević S (2000) The point of zero charge and sorption
14 of cadmium (II) and strontium (II) ions on synthetic hydroxyapatite. *Sep Purif Technol* 18:
15 185-194
16
17
18
19
20
21 28. Dorozhkin SV (2012) Dissolution mechanism of calcium apatites in acids: A review of
22 literature. *World journal of methodology* 2:1-17
23
24
25
26 29. In Standard Reference Database 46, NIST Critically Selected Stability Constants of Metal
27 Complexes Database Version 8.0
28
29
30
31 30. Śmiechowski M (2010) Theoretical pKa prediction of O-phosphoserine in aqueous
32 solution. *Chem Phys Lett* 501:123-129
33
34
35
36
37 31. Zachariou M, Traverso I, Spiccia L, Hearn MT (1996) Potentiometric Investigations into
38 the Acid– Base and Metal Ion Binding Properties of Immobilized Metal Ion Affinity
39 Chromatographic (IMAC) Adsorbents. *J Phys Chem* 100:12680-12690
40
41
42
43
44
45 32. Jastrzab R, Lomozik L (2009) Effectiveness of Phosphate Groups in Noncovalent
46 Interactions in Binary Adenosine Nucleotides/Phosphoserine Aqueous Systems. *J Solution*
47 *Chem* 38:35-46
48
49
50
51
52
53
54
55
56
57
58
59
60

Supplementary materials

Table S1. Unit cell parameters and particles size of apatite samples before and after sorption experiments in 0.02 M O-Ph-L-Ser and L-Ser solution.

Sample	Average apparent size, nm	Unit cell parameters, $\pm 0.001 \text{ \AA}$	
		<i>a</i>	<i>c</i>
CaHAp	110 (21)	9.413	6.860
O-Ph-L-Ser			
pH 2	104 (23)	9.398	6.856
pH 6	107 (21)	9.410	6.859
pH 8	103 (20)	9.406	6.860
L-Ser			
pH 2	108 (27)	9.444	6.885
pH 6	98 (22)	9.440	6.882
pH 8	104(25)	9.437	6.879
CuHAp	68 (17)	9.394	6.855
O-Ph-L-Ser			

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

pH 2	62(15)	9.392	6.852
pH 6	65(15)	9.396	6.859
pH 8	68(16)	9.390	6.854
L-Ser			
pH 6	70 (19)	9.420	6.871
pH 8	76 (20)	9.431	6.878

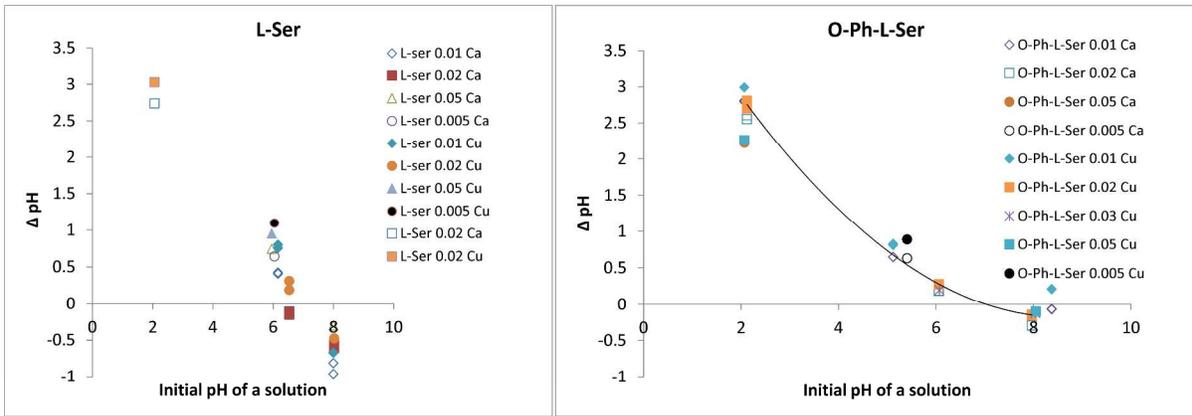


Figure S1. Change of the solution pH as a result of contact with apatite. $\Delta\text{pH} = \text{pH}_{\text{initial}} - \text{pH}_{\text{final}}$

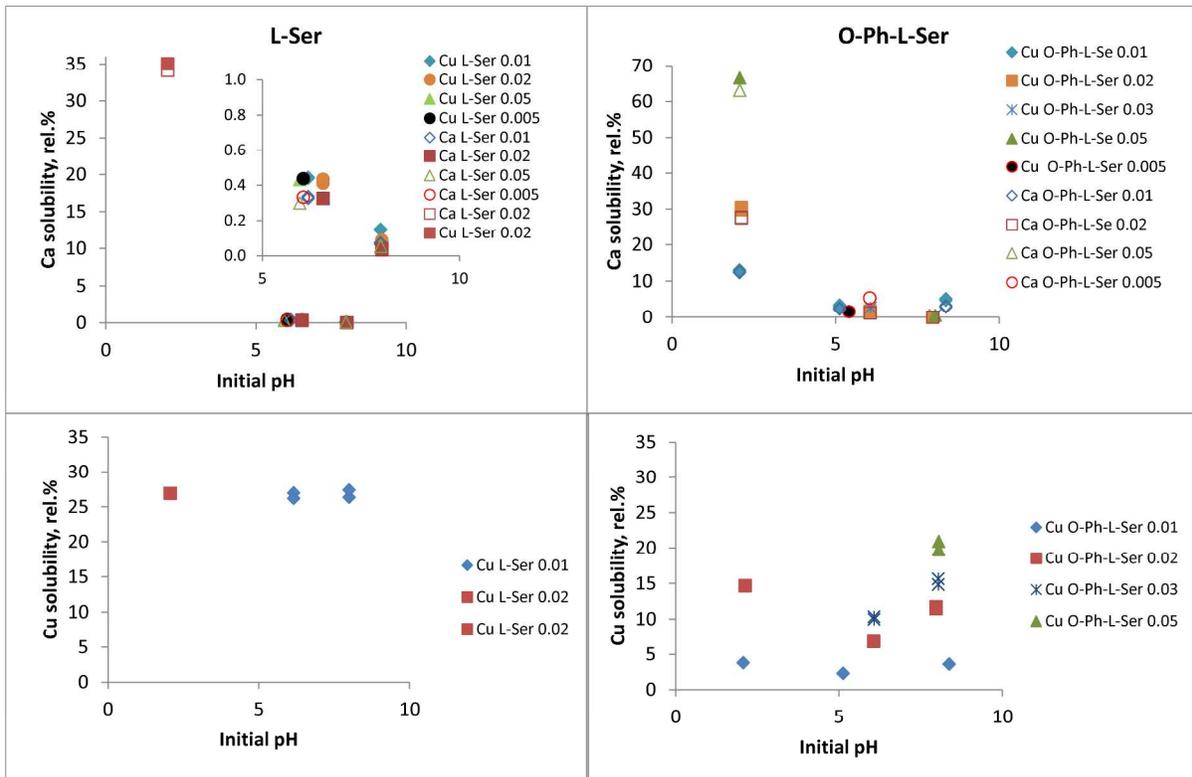


Figure S2. Ca and Cu relative solubility in L-Ser and O-Ph-L-Ser solutions depending on solution initial pH.

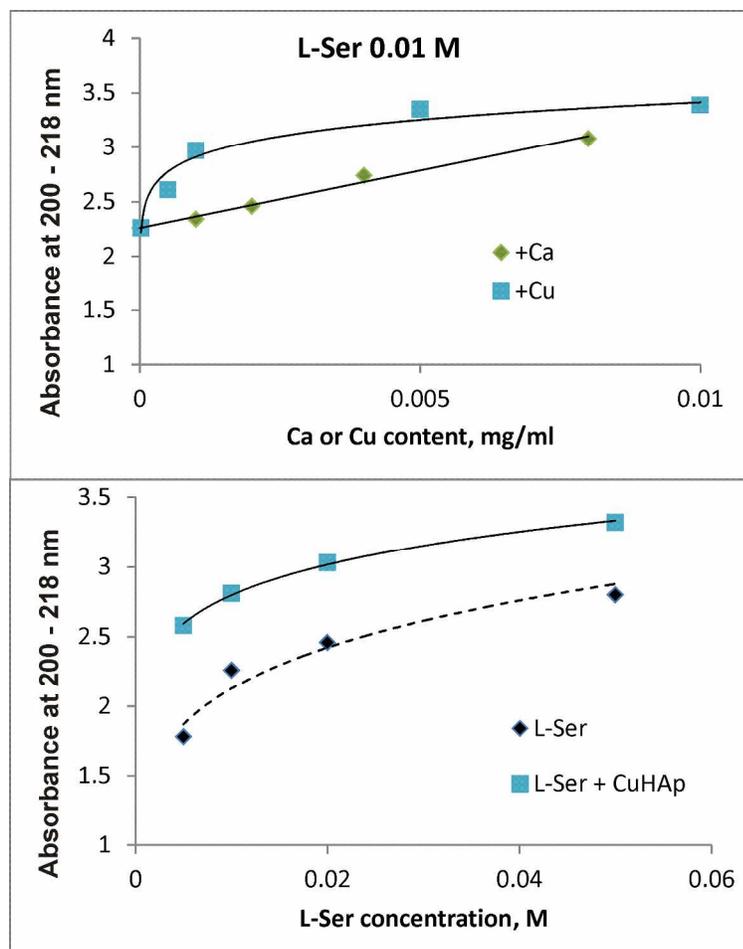


Figure S3. UV absorption intensity at 200-210 nm a) for 0.01 M L-Ser solution with different Ca or Cu content; b) depending on L-Ser concentration before and after reaction with CuHAp.

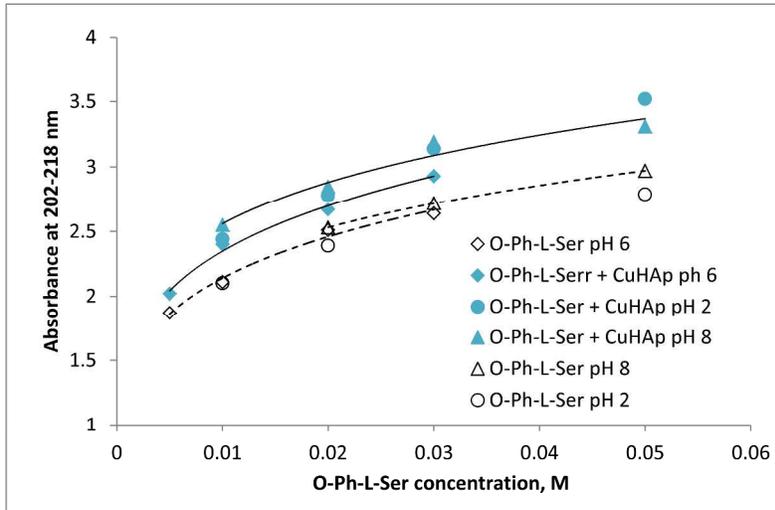


Figure S4. UV absorption intensity at 200-210 nm depending on O-Ph-L-Ser concentration and pH before and after reaction with CuHAp.

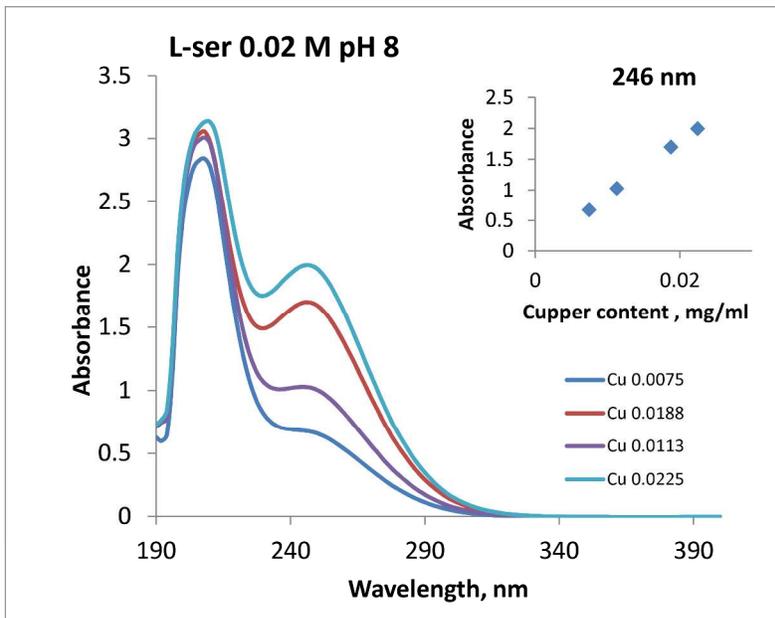


Figure S5. UV absorbance of L-Ser 0.02 M solution at pH 8 with different content of Cu^{2+} ions.

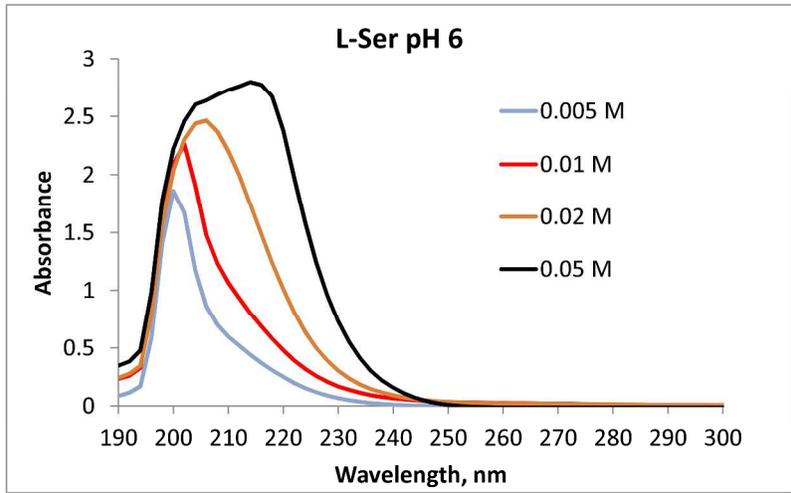


Figure S6. UV absorption spectra of L-Ser solutions at pH 6.

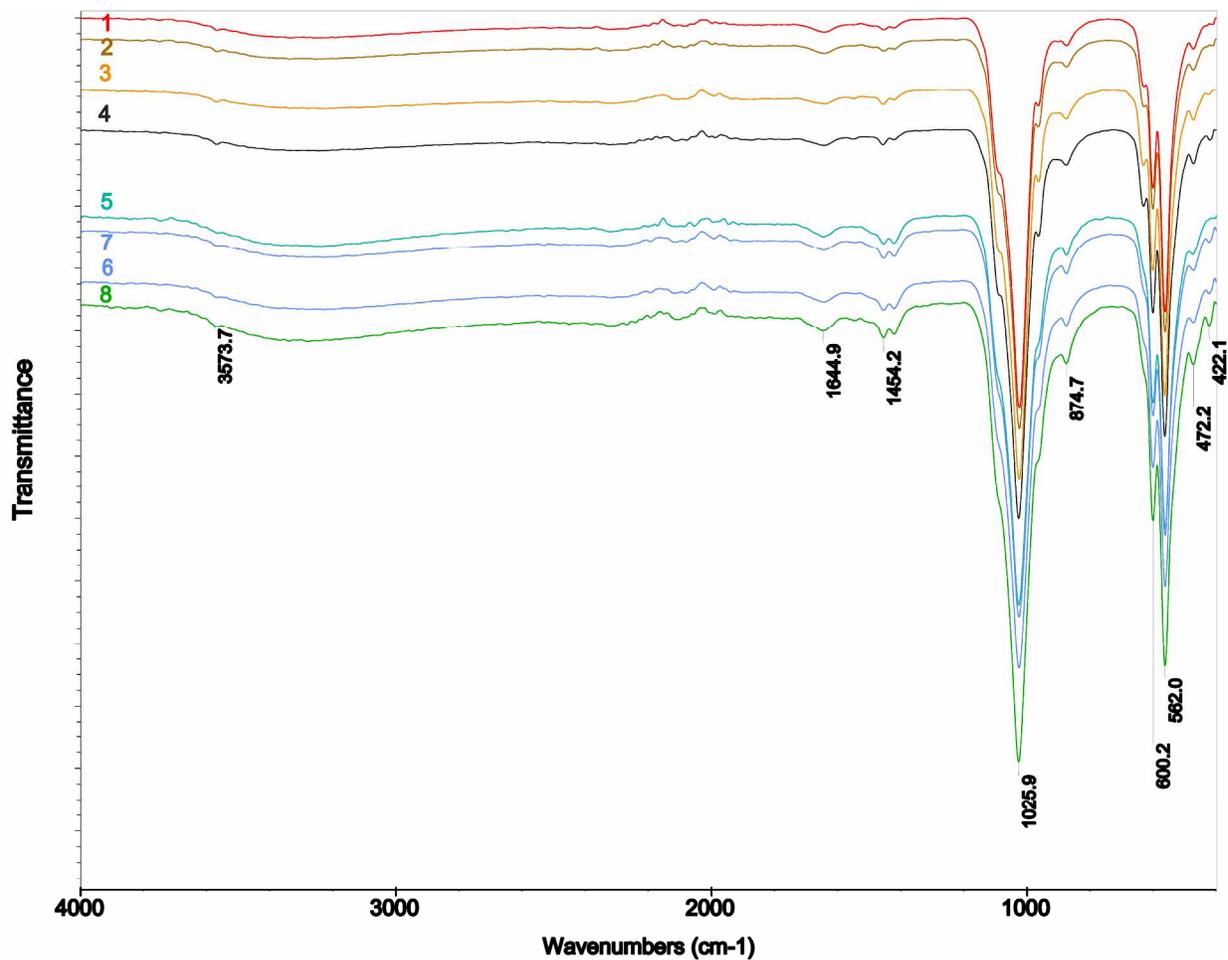


Figure S7. IR spectra of : 1 – CaHAp; 2 – CaHAp after treatment in water at pH 8, 3 - CaHAp after treatment at pH 6; 4 - CaHAp after treatment at pH 2; 5 – CuHAp; 6 – CuHAp after treatment in water at pH 8, 7 - CuHAp after treatment at pH 6; 8 - CuHAp after treatment at pH 2.