Investigation of the crystal field in rare earth titanate pyrochlores by resonant inelsatic x-ray scattering

Octave Duros, Christian Brouder, Renaud Delaunay, Hebatalla Elnaggar, Romain Jarrier, Amélie Juhin, Gheorghe S Chiuzbaian

iMAT

Investigation of the crystal field in rare earth titanate pyrochlores by resonant inelastic x-ray scattering

Octave Duros[1,2], C. Brouder[2], R. Delaunay[1], H. Elnaggar[2], R. Jarrier[1], A. Juhin[2], G. S. Chiuzbăian[1]

[1] Sorbonne Université, CNRS, Laboratoire de Chimie Physique – Matière et Rayonnement, LCPMR, F-75005 Paris, France
[2] Sorbonne Université, Muséum National d'Histoire Naturelle, CNRS, Institut de Minéralogie, de Physique des Matériaux et de Cosmochimie, IMPMC, F-75005 Paris, France

Context

• Rare earth titanate pyrochlores $R_2Ti_2O_7$ (R = Sm, Tb, Dy, Er, Yb) possess **fascinating magnetic states** [1–2] depending on the rare earth element R.

• The **structural argument** (e.g. different lattice parameters) **cannot solely explain** the variety of observed states: quantum spin liquids, spin ices or spin glasses.

• Characterization of the **crystal electric field** (CEF) acting on the R sites is a key ingredient for the understanding of those states.

• The **large variety** of CEF **parametrizations** that came over time led to many misconceptions in the litterature, thus needing a **clear definition** for further work.

1. CEF potential expansion

• CEF potential H_{CEF} pertubates the spherical symmetry of the free ion Hamiltonian H_F :

$$H = H_F + H_{CEF}$$

• One can express H_{CEF} as the sum of the potential V felt by every single electron i at a position r_i of the R metal:

$$H_{CEF} = -e \sum_{i=1}^{n} V(\boldsymbol{r}_i)$$

with V expressed with a time dependent charge distribution $\rho(\boldsymbol{R})$

$$V(\boldsymbol{r}_i) = \int \frac{\rho(\boldsymbol{R})}{|\boldsymbol{R} - \boldsymbol{r}_i|} d\tau$$

$$H_{CEF} = -e \sum_{i=1}^{n} \int \rho(\boldsymbol{R}) \sum_{k=0}^{\infty} \frac{r_i^k}{R^{k+1}} P_k(\cos\omega) d\tau$$

where $P_k(\cos\omega)$ are the *Legendre polynomials* [3]:

$$P_k(\cos\omega) = \frac{4\pi}{2k+1} \sum_{q=-k}^{k} Y_k^{q*}(\theta,\varphi) Y_k^q(\theta_i,\varphi_i)$$

expansion coefficients $Y_k^{q*}(\theta,\varphi) = (-1)^q Y_k^{-q}$	operators $Y_k^q(\theta_i,\varphi_i) = Y_k^q(i)$

2. CEF as a sum of parameters

$$P_k(\cos\omega) = \frac{4\pi}{2k+1} \left[Y_k^0 Y_k^0(i) + \sum_{q=-k}^{k} (-1)^q \left(Y_k^{-q} Y_k^q(i) + Y_k^q Y_k^{-q}(i) \right) \right]$$

We introduce the **tesseral harmonics** Z_{kq} to get rid of complex quantities:

$$Z_{k0}^c = Y_k^0, \quad Z_{kq}^c = \frac{1}{\sqrt{2}} \left(Y_k^{-q} + (-1)^q Y_k^q \right), \quad Z_{kq}^s = \frac{i}{\sqrt{2}} \left(Y_k^{-q} - (-1)^q Y_k^q \right)$$

as well as **tensor operators** which have the same transformation properties as Y_k^q:

$$\mathbf{C}_q^k = \sqrt{\frac{4\pi}{2k+1}} Y_k^q(i)$$

It comes:

$$H_{CEF} = \sum_{k=0}^{\infty} \sqrt{\frac{4\pi}{2k+1}} \left[Z_{k0}^c \mathbf{C}_0^k + \sum_{q=-k}^{k} \left(Z_{kq}^c \frac{1}{\sqrt{2}} \left(\mathbf{C}_{-q}^k + (-1)^q \mathbf{C}_q^k \right) \right. \right.$$
$$\left. \left. + Z_{kq}^s \frac{i}{\sqrt{2}} \left(\mathbf{C}_{-q}^k - (-1)^q \mathbf{C}_q^k \right) \right) \right] \times \int \rho(\boldsymbol{R}) \frac{r_i^k}{R^{k+1}} d\tau$$

We eventually introduce **CEF parameters** B_q^k to simplify the former expression:
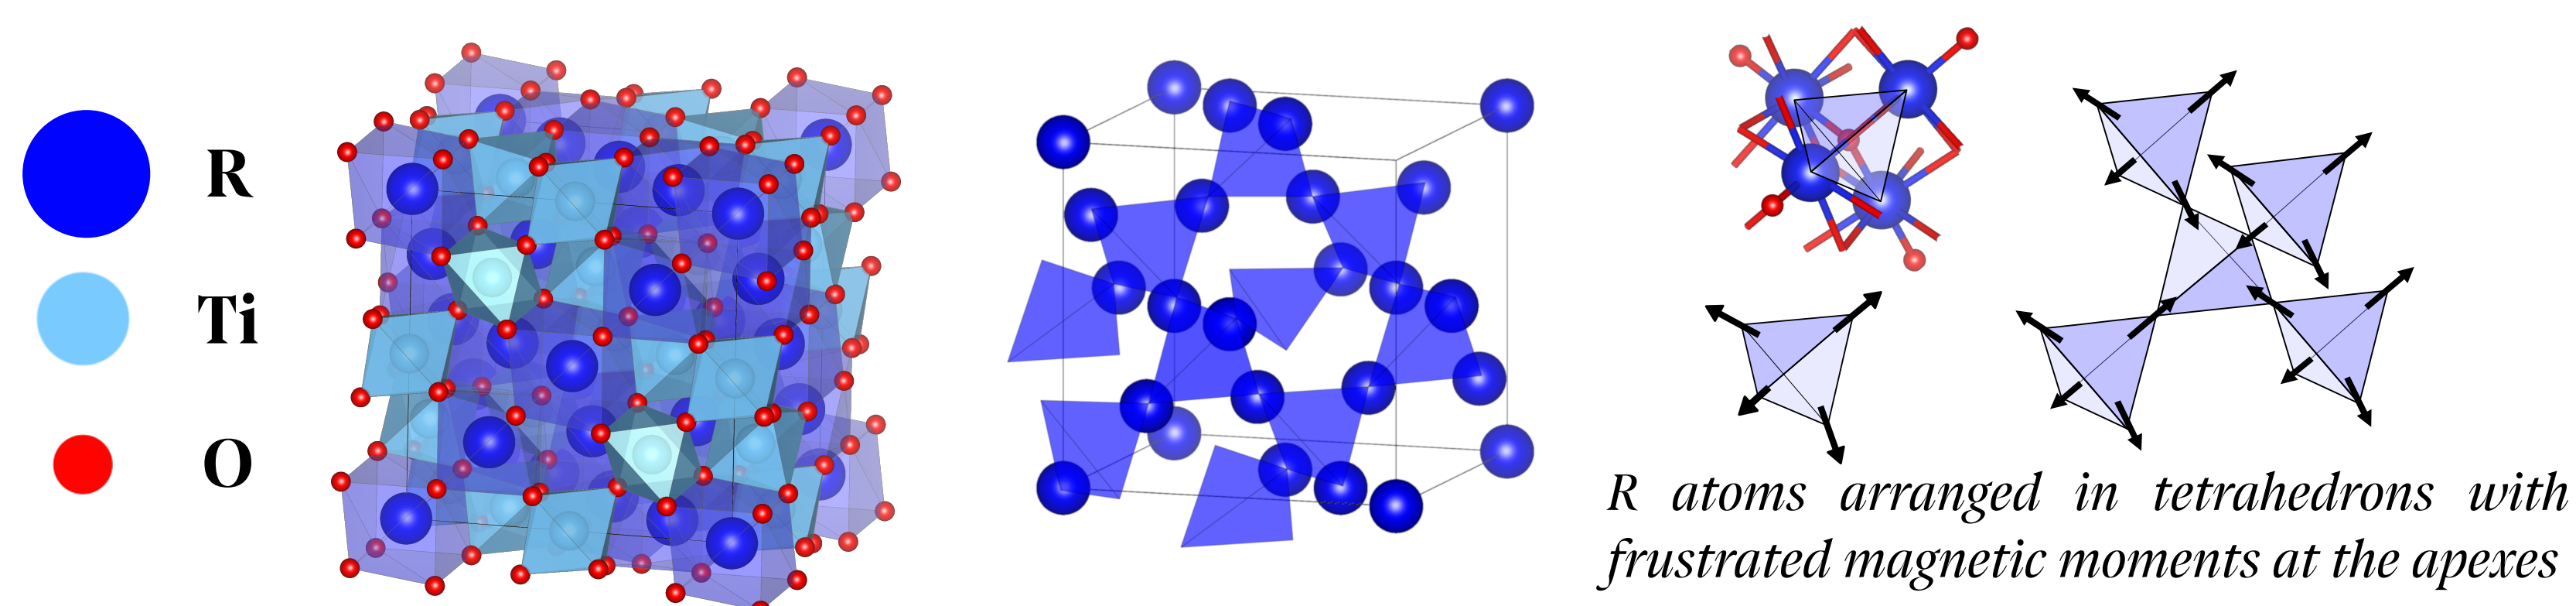
$$B_0^k = \sqrt{\frac{4\pi}{2k+1}} Z_{k0}^c \int \rho(\boldsymbol{R}) \frac{r_i^k}{R^{k+1}} d\tau$$

$$B_q^k = \sqrt{\frac{4\pi}{2k+1}} \frac{Z_{kq}^c}{\sqrt{2}} \int \rho(\boldsymbol{R}) \frac{r^k}{R^{k+1}} d\tau \qquad B_q'^k = \sqrt{\frac{4\pi}{2k+1}} \frac{Z_{kq}^s}{\sqrt{2}} \int \rho(\boldsymbol{R}) \frac{r^k}{R^{k+1}} d\tau$$

$$H_{CEF} = \sum_{k=0}^{\infty} \left[B_0^k \mathbf{C}_0^k + \sum_{q=-k}^{k} \left(B_q^k \left(\mathbf{C}_{-q}^k + (-1)^q \mathbf{C}_q^k \right) + B_q'^k \left(\mathbf{C}_{-q}^k - (-1)^q \mathbf{C}_q^k \right) \right) \right]$$

3. The $R_2Ti_2O_7$ case

- **R** (dark blue)
- **Ti** (light blue)
- **O** (red)

R atoms arranged in tetrahedrons with frustrated magnetic moments at the apexes

• **R** atoms and **Ti** atoms are situated in two different **apexes-sharing tetrahedrons sub-lattices** that interpenetrate into one another;
• **Magnetic moments** are geometrically **frustrated** (**3D kagomé lattices**);
• D_{3d} **point symmetry group**, k and q are limited and CEF in $R_2Ti_2O_7$ compounds can be described by:

$$H_{CEF} = B_0^2 \mathbf{C}_0^2 + B_0^4 \mathbf{C}_0^4 + B_3^4 (\mathbf{C}_{-3}^4 - \mathbf{C}_3^4) + B_0^6 \mathbf{C}_0^6 + B_3^6 (\mathbf{C}_{-3}^6 - \mathbf{C}_3^6) + B_6^6 (\mathbf{C}_{-6}^6 + \mathbf{C}_6^6)$$

4. How to characterize the CEF
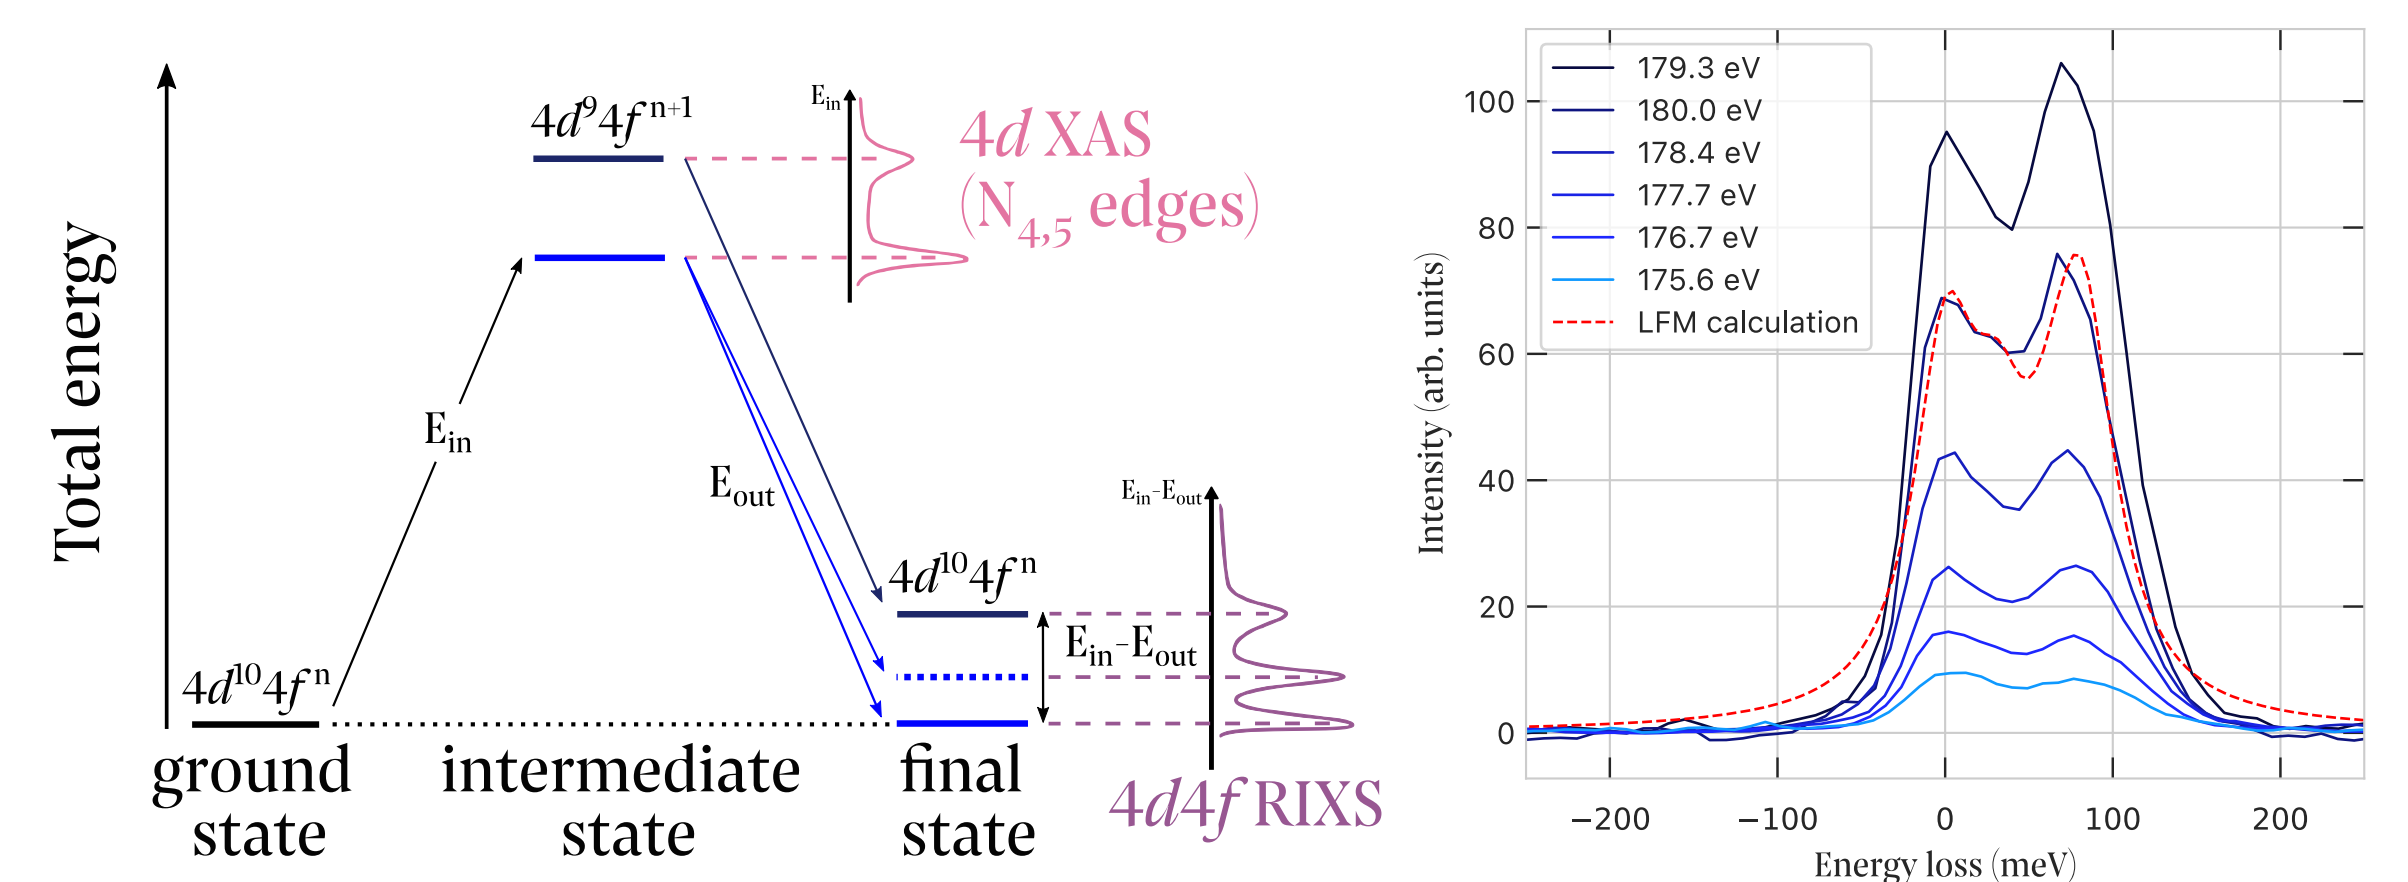
RIXS process representation and RIXS spectra of the CEF effect in $Yb_2Ti_2O_7$ measured on SEXTANTS beamline in SOLEIL, at the Yb $N_{4,5}$ edge.

• **High-resolution RIXS** allows probing the CEF;
• AERHA spectrometer [4] on SEXTANTS is **worldwide** the only instrument offering the required **energy resolution**
• Simulations run through **Quanty** software package [5]: **Ligand Multiplet Theory** calculations with CEF contribution, expanded on **spherical tensors**.

5. Conclusion and outlook

• Choice of a clear definition based on spherical tensors, that can directly be used in Quanty code.
• First observation of the CEF effect in pyrochlore crystals at the R $N_{4,5}$ edges with RIXS.
• Precise extraction of CEF parameters in $R_2Ti_2O_7$ ongoing, with new experiments and machine learning.

more:
[1] S.T. Bramwell, Nat. Comm. **8**, 2088 (2017)
[2] S.R. Giblin *et al.*, Phys. Rev. Lett. **121**, 067202 (2018)
[3] Griffith, J.S., Cambridge University Press, London (1961)
[4] G. S. Chiuzbăian *et al.*, Rev. Sci. Instrum. **85**, 043108 (2014)
[5] M.W. Haverkort *et al.*, Phys. Rev. B **85**, 165113 (2012)

LCPMR · IM2 · SCIENCES SORBONNE UNIVERSITÉ · cnrs · MUSÉUM NATIONAL D'HIST NATURELLE · IRD Institut de Recherche pour le Développement FRANCE · Institut de science des matériaux ALLIANCE SORBONNE UNIVERSITÉ