



**HAL**  
open science

## Highly Reactive Diazenyl Radical Species Evidenced during Aryldiazonium Electroreduction

Laure Pichereau, Laure Fillaud, Nikolaos Kostopoulos, Emmanuel Maisonhaute, Thomas Cauchy, Magali Allain, Jean-Marc Noël, Christelle Gautier, Tony Breton

► **To cite this version:**

Laure Pichereau, Laure Fillaud, Nikolaos Kostopoulos, Emmanuel Maisonhaute, Thomas Cauchy, et al.. Highly Reactive Diazenyl Radical Species Evidenced during Aryldiazonium Electroreduction. *Journal of Physical Chemistry Letters*, 2022, 13 (51), pp.11866-11871. 10.1021/acs.jpcllett.2c03089 . hal-04303155v1

**HAL Id: hal-04303155**

**<https://hal.sorbonne-universite.fr/hal-04303155v1>**

Submitted on 13 Nov 2023 (v1), last revised 23 Nov 2023 (v2)

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Highly Reactive Diazenyl Radical Species Evidenced during Aryldiazonium Electroreduction

*Laure Pichereau,<sup>a</sup> Laure Fillaud,<sup>b</sup> Nikolaos Kostopoulos,<sup>c</sup> Emmanuel Maisonhaute,<sup>b</sup> Thomas Cauchy,<sup>a</sup> Magali Allain,<sup>a</sup> Jean-Marc Noël,<sup>c</sup> Christelle Gautier\*<sup>a</sup> and Tony Breton\*<sup>a</sup>*

<sup>a</sup> Univ Angers, CNRS, MOLTECH-Anjou, SFR MATRIX, F-49000 Angers, France.

<sup>b</sup> Sorbonne Université, CNRS, Laboratoire Interfaces et Systèmes Electrochimiques, 4 Place Jussieu, 75005 Paris, France.

<sup>c</sup> Université Paris Cité, ITODYS, CNRS, F-75013, Paris, France.

AUTHOR INFORMATION

## Corresponding Authors


[tony.breton@univ-anger.fr](mailto:tony.breton@univ-anger.fr)

[christelle.gautier@univ-angers.fr](mailto:christelle.gautier@univ-angers.fr)

We report the experimental reassessment of the commonly admitted concerted reduction mechanism for the diazonium electroreduction. Ultrafast cyclic voltammetry was exploited to demonstrate the existence of a stepwise pathway and real-time spectroelectrochemistry experiments allowed to visualize the spectral signature of an evolution product of the phenyldiazenyl radical intermediate. Unambiguous identification of the diazenyl species was achieved by radical trapping followed by X-ray structure resolution. The electrochemical generation of this transient under intermediate energetic conditions calls into question our

comprehension of the layer structuration when surface modification is achieved *via* the diazonium electrografting technique as this azo-containing intermediate could be responsible for the systematic presence of azo bridges in the nanometric films.

## TOC GRAPHICS

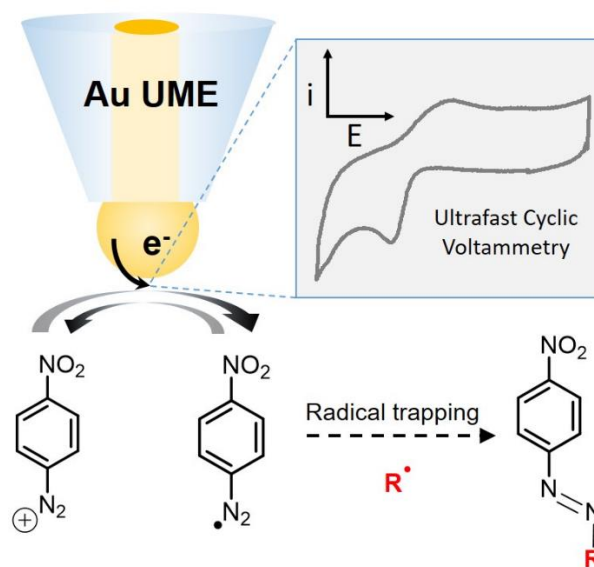


**KEYWORDS.** Diazonium, Stepwise mechanism, Concerted mechanism, Spectroelectrochemistry, Radical trapping, Grafting.

In 1992, J. Pinson et coll. reported the very first example of carbon modification exploiting the aryldiazonium electroreduction.<sup>1</sup> This new grafting approach, based on the production, and subsequent grafting of reactive aryl radicals, was to become one of the most popular methods to functionalize a broad range of substrates in a very simple way.<sup>2-8</sup> However, the fine description of the layer structuration remains to be developed. Indeed, even if the carbon-substrate bond is now evidenced, nitrogen is systematically detected in the nanometric films in a non-negligible proportion.<sup>9-13</sup> XPS, Raman and TOF-SIMS investigations all converged towards the presence of azo bridges,<sup>14,15</sup> but our scientific community has not yet proposed any alternative mechanistic

explanation for their formation.<sup>5,14,16-18</sup> This led us to take a step back and reconsider the sequence that served as a basis for the electrografting technique understanding. Electrochemical reduction of the diazonium compounds has been extensively investigated since the 50's.<sup>19-21</sup> The main objective was to determine whether the electron transfer was coupled to the decomposition into aryl radical and dinitrogen (concerted), or involved an aryldiazenyl radical intermediate (stepwise) (Scheme 1). Several electrochemical investigations on series of para-substituted diazonium have tilted the balance in favour of a stepwise mechanism versus a concerted one by establishing a strong dependence between their reduction potential and the hammet's constant of the substituents.<sup>20,22</sup> Following those first steps, studies were carried out by thermo- and photolysis of azo compounds in the early 70's but did not succeed in discriminating between concerted and non-concerted decomposition mechanisms.<sup>23-25</sup> The existence of the diazenyl radical transient remained a subject of debate because of conflicting CIDNP (Chemically Induced Dynamic Nuclear Polarization) and ESR (Electron Spin Resonance) interpretations until 1978,<sup>25-28</sup> date on which important evidence of the radical trapping was obtained from the photolysis decomposition of a series of unsymmetric diazene compounds.<sup>29</sup> The development of pulsed radiolysis/photolysis and time-resolved ESR techniques in the 80's definitively confirmed the relative persistence of the aryldiazenyl radical and gave access to decay constants ranging from  $10^5$  to  $10^6$  s<sup>-1</sup>.<sup>30-34</sup> However, first, this intermediate has never been trapped from a diazonium decomposition and second, the highly energetic conditions used to evidence the stepwise decomposition are not transposable to the low driving force exploited for the diazonium electroreduction. Indeed, the driving force typically applied for electrochemical reduction at the peak potential is about 0.07 eV while it is on the order of 3.20 eV when solvated electrons are the reducing species (corresponding to -3.10 V/SCE). In this context, Savéant has worked on the energetic aspect of the bond

breaking/formation associated to electron transfers in the early 2000's and stated that the mechanism of a bond cleavage passes from stepwise to concerted as the driving force becomes lower and lower.<sup>35,36</sup> Since this work, the scientific community considered the existence of the sole concerted mechanism in the diazonium electroreduction process.<sup>14,37</sup> Therefore, the grafting technique has been developed and improved with the idea that only aryl radicals can be grafted. In a work published in 2010 focused on the chemical reduction of the nitrobenzene diazonium in homogeneous medium, the trapping of the aryl radical by a ESR active scavenger has strengthened the consensus within the scientific community regarding the reduction of the diazonium salts *via* the sole concerted mechanism.<sup>38</sup>

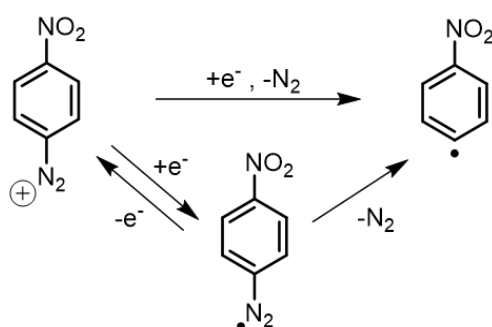


**Scheme 1.** Concerted (top) *vs* stepwise (bottom) mechanism for the diazonium electroreduction.

Herein, we experimentally reconsider the mechanistic approach of the diazonium electroreduction to collect evidences of the existence of a stepwise pathway, without rejecting a competing concerted route. The objective is to bridge the gap between polarographic studies that suggest a stepwise mechanism without, however, evidencing the diazenyl radical intermediate, and high energy experimental conditions that evidenced its formation. The 4-nitrobenzene diazonium cation (4-NBD), which widely served as a benchmark for the scientific community to develop the surface functionalization *via* the diazonium reduction, was used in the present work.<sup>18,39,40</sup> The

first step consisted to evidence *in-situ* the mechanistic pathway involved in the reduction of the 4-NBD under usual electrografting conditions. Examination of the cyclic voltammetric response is a convenient means to distinguish the stepwise mechanism from a concerted one.<sup>36</sup> The simplest case is when the cyclic voltammogram becomes chemically reversible upon raising the scan rate. Indeed, as shown in Figure S1, the simulated CVs performed in similar experimental conditions to those previously reported<sup>37</sup> do not allow to discriminate between the two mechanisms unless the dissociation rate of the diazenyl radical formed in a stepwise mechanism is lower than the values already reported for similar species.<sup>36</sup> Then, for a reduction, the presence of a reverse anodic trace at high scan rate is the signature of the radical or radical anion. Using ultramicroelectrodes (UME), very high scan rate can be reached, corresponding to lifetimes in the submicrosecond range for the reduced intermediate.<sup>41-43</sup> A voltammetric study was carried out on a gold ball UME with increasing scan rate in the presence of 4-NBD (Figure 1a and Figure S2). For low scan rate, no reversibility of the signal was observed. The rise of an anodic reversible voltammetric process was evidenced at a scan rate of 8080 V.s<sup>-1</sup> (Figure 1b), unambiguously demonstrating the existence of a stepwise pathway. To circumvent the electrode passivation issue possibly occurring at low scan rate and accurately estimate the diazenyl radical lifetime, the ultrafast cyclic voltammetric experiment was simulated in 1D using COMSOL Multiphysics software (V 5.5) (Table S1, Figure S3 and S4). The simulated curves for various dissociation rate constants of the species issued from the diazonium reduction at the very same scan rate are presented in the inset of Figure 1b. From the ratio of the peak intensity  $i_{ox}/i_{red}$  with  $i_{ox}$  and  $i_{red}$  corresponding to the intensity of the anodic and the cathodic peak respectively, we estimated a dissociation rate constant  $k_d$  of  $0.9 \times 10^4 \pm 0.5 \times 10^4 \text{ s}^{-1}$  for the species probed experimentally (Figure S4).<sup>36</sup> Compared to the values reported

in the literature from radio- and photolysis experiments, ranging from  $4 \times 10^4$  to  $10^7 \text{ s}^{-1}$ , this value is in the low range (*vide supra*).<sup>34,44</sup>

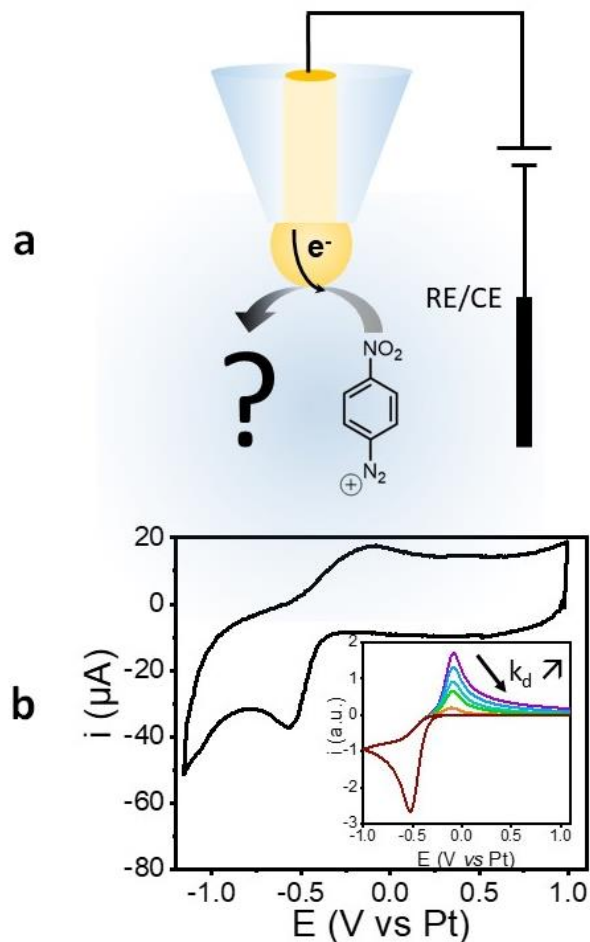


**Figure 1.** a) Cyclic voltammetry of the 4-NBD at gold ball UME. b) Experimental and simulated (inset) cyclic voltammograms recorded at  $8080 \text{ V}\cdot\text{s}^{-1}$  in a  $0.3 \text{ M nBu}_4\text{NPF}_6$  acetonitrile solution containing  $5 \text{ mM}$  of 4-NBD.

In a second step, we attempted to identify the aryldiazenyl radical. However, obtaining a sufficient concentration and a continuous production of the diazenyl radical allowing its characterization is challenging because the grafting process usually leads to the electrode passivation within few seconds due to the formation of multilayers.<sup>45</sup> To circumvent this issue and

minimize the radical polymerization, a grafting control technique recently reported was exploited. This approach involves the use of a redox reducer activated at an electrode to induce the diazonium reduction in the diffusion layer of the electrode, as illustrated in Figure 2a.<sup>46,47</sup> Employing this strategy, the mediated diazonium electroreduction was monitored in real-time using an ultra-sensitive spectroelectrochemical bench recently developed by our group to probe electrochemically generated species in the visible range.<sup>48</sup> In this work, the dissolved atmospheric dioxygen was exploited as a redox mediator since its reduced form (superoxide anion  $O_2^{\cdot-}$ ) does not absorb in the wavelength range of interest. The chronoamperometric reduction of 4-NBD was monitored by absorption spectroelectrochemistry using the following potential program: 30 s at +0.5 V, followed by a 15 min electroreduction step at -0.9 V, and a 5 min final step at +0.5 V (details in the Supporting Information).



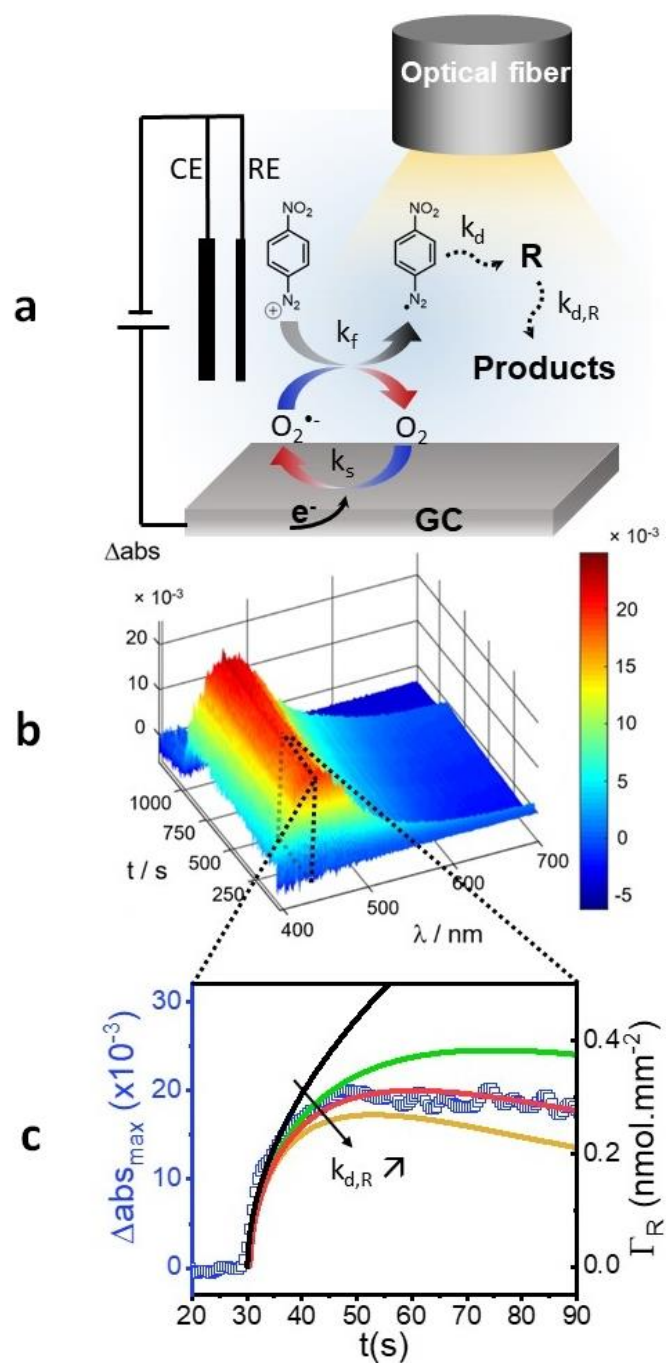

**Figure 2.** a) Mediated 4-NBD electroreduction under spectroelectrochemical monitoring, b) dynamic chronoabsorptogram recorded on GC electrode in the presence of 1 mM 4-NBD in acetonitrile  $nBu_4NPF_6$  0.1 M. c) Experimental  $\Delta Abs_{max}$  over time (blue circles) and simulated


concentration evolution of the secondary product for a dissociation constant  $k_{d,R}$  of 0 (black), 0.02 (green), 0.03 (red) and  $0.04 \text{ s}^{-1}$  (yellow) obtained from 1D simulations considering a first order reaction.

The chronoabsorptogram presented on Figure 2b shows the appearance of an absorption band  $\Delta\text{Abs}$  with a maximum located at  $\lambda_{\text{max}} \sim 450 \text{ nm}$  for the whole reductive step duration (*i.e.* -0.9 V). The  $\Delta\text{Abs}$  value returns close to its original value when the potential is shifted to +0.5 V. The absence of absorption signal after the positive potential shift confirms that the visualized absorption signal corresponds to the spectral signature of a dissolved species and not to any grafted moieties. This point was confirmed by the current-time curve presented in Figure S5, which exhibits an absence of electrode passivation. To further understand the origin of this species, the whole mechanism of the reduction process shown in Figure 2a was simulated versus time in 1D (Table S2 and Figure S6). Firstly, the theoretical concentration profile of the nitrophenyldiazenyl radical under our spectroelectrochemical analysis conditions was simulated. Using the dissociation rate constant of the diazenyl radical species  $k_d$  determined above, the simulation drives to a rapid decrease of its apparent concentration profile over time, that is in contradiction with the quasi-constant  $\Delta\text{Abs}_{\text{max}}$  value observed in Figure 2b. While being in fair agreement with the simulated spectra obtained by TD-DFT calculation ( $\lambda_{\text{max}} \sim 500 \text{ nm}$ , see Figure S7), the observed absorption spectrum is thus unlikely the signature of the diazenyl radical moiety. This spectrum can neither be attributed to the nitrophenyl anion nor radical, characterized by an absorption signal in the UV domain (Figure S7). Additionally, the experimental absorption band cannot be associated to the diazenyl radical attack on the superoxide anion or the acetonitrile molecules as the very same experimental spectra were obtained in DMSO or exploiting ferrocene as reducer instead of  $\text{O}_2^-$  (Figure S8).

Among the considered structures expected under electroreduction conditions, TD-DFT calculations showed that absorption bands in the visible range are likely attributable to delocalized dimer radicals such as those produced from nitrophenyl and/or nitrophenyldiazenyl radical attacks (Figure S7). A close examination of the non-accumulating process observed for this species (*i.e.* quasi-constant  $\Delta\text{Abs}$  value for the reduction step) agrees with its progressive disappearance with time as shown from the simulations of its concentration (Figures S9 and S10), considering, as a first approach, a first order dissociation rate constant  $k_{d,R}$  (Figure 2c). Noteworthy,  $k_{d,R}$  value extracted here ( $k_{d,R} = 0.03 \pm 0.01 \text{ s}^{-1}$ ) that reflects the decomposition rate of the species is also in good agreement with the decay rate of  $\Delta\text{abs}_{\text{max}}$  once the potential is shifted to +0.5 V as shown in Figure S11. This result, coupled to the large FWHM observed experimentally, suggests that spectroelectrochemical spectra might be attributed to several coupling intermediate species. Even if at that point our measurement cannot fully establish the species detected, it reveals that mediated electroreduction is an interesting pathway to continuously produce intermediate species in solution while preserving the integrity of the electrode surface.

To confirm the existence of the reactive diazenyl radical, we speculated that it should be possible to form and isolate a stable compound by radical trapping. To this end, N-terbutyl-alpha-phenylnitron (PBN), that is widely used as a radical scavenger in chemical and biological studies, was employed.<sup>49</sup> Typically, in the presence of free radicals, PBN undergoes a coupling on the benzylic  $\text{sp}^2$  carbon, giving rise to a stable nitroxyl radical derivative. PBN adducts can also lead to a spontaneous decomposition to form 2-methyl-2-nitrosopropane (MNP), also known as an efficient radical scavenger.<sup>50</sup> In order to obtain a sufficient amount of coupling product, the sustainable production of radicals was ensured by exploiting the mediated diazonium electroreduction strategy described in Figure 2a on a large area glassy carbon electrode. In a cell

containing 2 mM of 4-NBD and 10 mM of PBN, a potential of -0.9 V was imposed to a 1 cm<sup>2</sup> glassy carbon electrode for 20 minutes. After electrolysis, numerous products, likely formed by multiple radical reactions, were evidenced by UV absorption on thin layer chromatography. Colored products, likely coming from the diazenyl coupling, were separated from the bulk, leading to the detection of two main products, one of which was isolated (details in the Supporting Information). The structure of compound 1 was deduced from a mass spectrometry analysis (Figure S12) and corresponds to the expected coupling product between the nitrophenyldiazenyl radical and the radical scavenger PBN (Figure 3).

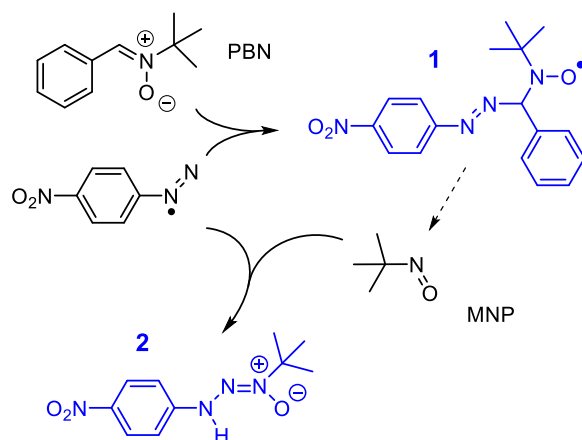

**Figure 3.** Radical trapping of the nitrophenyldiazenyl radical by the PBN scavenger, followed by the decomposition of the PBN adduct **1** into MNP scavenger, leading to the MNP adduct **2**. Structure of **1** was deduced from mass spectrometry and structure of **2** was resolved by X-ray diffraction.

The structure of the second product (compound 2, Figure 3), isolated as orange crystals, was resolved by X-ray diffraction (Supporting Information). The zwitterionic structure corresponds to the coupling of the 4-nitrophenyldiazenyl radical with the 2-methyl-2-nitrosopropane (MNP). The existence of compounds 1 and 2 unambiguously demonstrates that a diazenyl radical intermediate

is produced subsequently to the 4-NBD reduction as suggested from the cyclic voltammetry experiments.

The results presented in this work shed new light on the diazonium electroreduction mechanism. The strategy based on the combination of UFCV, spectroelectrochemistry and radical trapping, allowed evidencing the formation of the diazenyl radical and thus the existence of a stepwise mechanism pathway. The strategy illustrated herein in the case of the mediated 4-NBD reduction could be further deployed to decipher the reduction mechanism of other aryldiazonium compounds. Besides, in the context of surface modification by diazonium electrografting, the existence of the diazenyl radical could have a direct impact on the film structuration. Indeed, the direct coupling of this intermediate on the surface, if demonstrated, could be responsible for the presence of azo bridges usually identified in the nanometric films and play a major role in the structure/properties relationships understanding.

## ASSOCIATED CONTENT

**Supporting Information.** Experimental details for electrode treatment, ultrafast cyclic voltammetry, spectroelectrochemistry, radical scavenging and X-ray diffraction ; Cyclic voltammetry simulations ; Spectroelectrochemistry current-time curves ; Spectroelectrochemistry simulations ; DFT calculations and TD-DFT simulated spectra; Spectroelectrochemistry control experiments ; LDI mass spectra. Crystallographic data for the compound 2 have been deposited with the Cambridge Crystallographic Data Centre with the deposition number CCDC 2151044. These data can be obtained free of charge from CCDC, [www.ccdc.cam.ac.uk](http://www.ccdc.cam.ac.uk).

## AUTHOR INFORMATION

The authors declare no competing financial interests.

#### ACKNOWLEDGMENT

The authors thank MATRIX SFR of the University of Angers and more precisely the ASTRAL and CRISTAL platforms for the characterization of organic compounds and X-ray diffraction analysis. This work was supported by the “Centre National de la Recherche Scientifique” (CNRS France) and the “Agence Nationale de la Recherche” (ANR France).

#### REFERENCES

- (1) Delamar, M.; Hitmi, R.; Pinson, J.; Saveant, J. M. Covalent Modification of Carbon Surfaces by Grafting of Functionalized Aryl Radicals Produced from Electrochemical Reduction of Diazonium Salts. *J. Am. Chem. Soc.* **1992**, *114* (14), 5883–5884. <https://doi.org/10.1021/ja00040a074>.
- (2) Allongue, P.; Delamar, M.; Desbat, B.; Fagebaume, O.; Hitmi, R.; Pinson, J.; Savéant, J.-M. Covalent Modification of Carbon Surfaces by Aryl Radicals Generated from the Electrochemical Reduction of Diazonium Salts. *J. Am. Chem. Soc.* **1997**, *119* (1), 201–207. <https://doi.org/10.1021/ja963354s>.
- (3) Pinson, J.; Podvorica, F. Attachment of Organic Layers to Conductive or Semiconductive Surfaces by Reduction of Diazonium Salts. *Chem. Soc. Rev.* **2005**, *34* (5), 429–439. <https://doi.org/10.1039/b406228k>.
- (4) Belanger, D.; Pinson, J. Electrografting: A Powerful Method for Surface Modification. *Chem. Soc. Rev.* **2011**, *40* (7), 3995–4048.

- (5) Mesnage, A.; Lefèvre, X.; Jégou, P.; Deniau, G.; Palacin, S. Spontaneous Grafting of Diazonium Salts: Chemical Mechanism on Metallic Surfaces. *Langmuir* **2012**, *28* (32), 11767–11778. <https://doi.org/10.1021/la3011103>.
- (6) Wu, T.; Fitchett, C. M.; Brooksby, P. A.; Downard, A. J. Building Tailored Interfaces through Covalent Coupling Reactions at Layers Grafted from Aryldiazonium Salts. *ACS Appl. Mater. Interfaces* **2021**, *13* (10), 11545–11570. <https://doi.org/10.1021/acsami.0c22387>.
- (7) Greenwood, J.; Phan, T. H.; Fujita, Y.; Li, Z.; Ivasenko, O.; Vanderlinden, W.; Van Gorp, H.; Frederickx, W.; Lu, G.; Tahara, K.; Tobe, Y.; Uji-i, H.; Mertens, S. F. L.; De Feyter, S. Covalent Modification of Graphene and Graphite Using Diazonium Chemistry: Tunable Grafting and Nanomanipulation. *ACS Nano* **2015**, *9* (5), 5520–5535. <https://doi.org/10.1021/acsnano.5b01580>.
- (8) Gautier, C.; López, I.; Breton, T. A Post-Functionalization Toolbox for Diazonium (Electro)-Grafted Surfaces: Review of the Coupling Methods. *Mater. Adv.* **2021**, *2* (9), 2773–2810. [10.1039.D1MA00077B](https://doi.org/10.1039/D1MA00077B). <https://doi.org/10.1039/D1MA00077B>.
- (9) Baranton, S.; Bélanger, D. Electrochemical Derivatization of Carbon Surface by Reduction of in Situ Generated Diazonium Cations. *J. Phys. Chem. B* **2005**, *109* (51), 24401–24410. <https://doi.org/10.1021/jp054513+>.
- (10) Yu, S. S. C.; Tan, E. S. Q.; Jane, R. T.; Downard, A. J. An Electrochemical and XPS Study of Reduction of Nitrophenyl Films Covalently Grafted to Planar Carbon Surfaces. *Langmuir* **2007**, *23* (22), 11074–11082. <https://doi.org/10.1021/la701655w>.

- (11) Menanteau, T.; Levillain, E.; Downard, A. J.; Breton, T. Evidence of Monolayer Formation via Diazonium Grafting with a Radical Scavenger: Electrochemical, AFM and XPS Monitoring. *Phys. Chem. Chem. Phys.* **2015**, *17* (19), 13137–13142. <https://doi.org/10.1039/C5CP01401H>.
- (12) Ghorbal, A.; Grisotto, F.; Laudé, M.; Charlier, J.; Palacin, S. The in Situ Characterization and Structuring of Electrografted Polyphenylene Films on Silicon Surfaces. An AFM and XPS Study. *J. Colloid Interface Sci.* **2008**, *328* (2), 308–313. <https://doi.org/10.1016/j.jcis.2008.09.033>.
- (13) Adenier, A.; Cabet-Deliry, E.; Chaussé, A.; Griveau, S.; Mercier, F.; Pinson, J.; Vautrin-Ul, C. Grafting of Nitrophenyl Groups on Carbon and Metallic Surfaces without Electrochemical Induction. *Chem. Mater.* **2005**, *17* (3), 491–501. <https://doi.org/10.1021/cm0490625>.
- (14) Doppelt, P.; Hallais, G.; Pinson, J.; Podvorica, F.; Verneyre, S. Surface Modification of Conducting Substrates. Existence of Azo Bonds in the Structure of Organic Layers Obtained from Diazonium Salts. *Chem. Mater.* **2007**, *19* (18), 4570–4575. <https://doi.org/10.1021/cm0700551>.
- (15) Betelu, S.; Tijunelyte, I.; Boubekour-Lecaque, L.; Ignatiadis, I.; Ibrahim, J.; Gaboreau, S.; Berho, C.; Toury, T.; Guenin, E.; Lidgi-Guigui, N.; Félidj, N.; Rinnert, E.; Chapelle, M. L. de la. Evidence of the Grafting Mechanisms of Diazonium Salts on Gold Nanostructures. *J. Phys. Chem. C* **2016**, *120* (32), 18158–18166. <https://doi.org/10.1021/acs.jpcc.6b06486>.
- (16) Usrey, M. L.; Lippmann, E. S.; Strano, M. S. Evidence for a Two-Step Mechanism in Electronically Selective Single-Walled Carbon Nanotube Reactions. *J. Am. Chem. Soc.* **2005**, *127* (46), 16129–16135. <https://doi.org/10.1021/ja0537530>.



- (17) Lehr, J.; Williamson, B. E.; Downard, A. J. Spontaneous Grafting of Nitrophenyl Groups to Planar Glassy Carbon Substrates: Evidence for Two Mechanisms. *J. Phys. Chem. C* **2011**, *115* (14), 6629–6634. <https://doi.org/10.1021/jp111838r>.
- (18) Menanteau, T.; Dias, M.; Levillain, E.; Downard, A. J.; Breton, T. Electrografting via Diazonium Chemistry: The Key Role of the Aryl Substituent in the Layer Growth Mechanism. *J. Phys. Chem. C* **2016**, *120* (8), 4423–4429. <https://doi.org/10.1021/acs.jpcc.5b12565>.
- (19) Atkinson, E.; Warren, H.; Abell, P.; Wing, R. A Polarographic Examination of Diazotized Amines. *J. Am. Chem. Soc.* 1950.
- (20) Kochi, J. K. Polarography of Aromatic Diazonium Salts. *J. Am. Chem. Soc.* **1955**, *77* (12), 3208–3211. <https://doi.org/10.1021/ja01617a013>.
- (21) Elofson, R. M. The Polarographic Reduction of Diazotized Aromatic Amines. *Can. J. Chem.* **1958**, *36* (8), 1207–1210. <https://doi.org/10.1139/v58-174>.
- (22) Elofson, R. M.; Gadallah, F. F. Substituent Effects in the Polarography of Aromatic Diazonium Salts. *J. Org. Chem.* **1969**, *34* (4), 854–857. <https://doi.org/10.1021/jo01256a016>.
- (23) Porter, N. A.; Landis, M. E.; Marnett, L. J. Photolysis of Unsymmetric Azo Compounds. *J. Am. Chem. Soc.* **1971**, *93* (3), 795–796. <https://doi.org/10.1021/ja00732a051>.
- (24) Crawford, R. J.; Takagi, K. Mechanism of Azoalkane Thermolysis. Concerted or Nonconcerted. *J. Am. Chem. Soc.* **1972**, *94* (21), 7406–7416. <https://doi.org/10.1021/ja00776a024>.
- (25) Porter, N. A.; Marnett, L. J.; Lochmueller, C. H.; Closs, G. L.; Shobataki, M. Application of Chemically Induced Dynamic Nuclear Polarization to a Study of the Decomposition of

Unsymmetric Azo Compounds. *J. Am. Chem. Soc.* **1972**, *94* (10), 3664–3665.  
<https://doi.org/10.1021/ja00765a087>.

(26) Marnett, L. J.; Smith, P.; Porter, N. A. An EPR Investigation of Hydrazyl Radicals Formed in Azo Compound Protolyses. *Tetrahedron Lett.* **1973**, *14* (13), 1081–1084.  
[https://doi.org/10.1016/S0040-4039\(01\)95909-X](https://doi.org/10.1016/S0040-4039(01)95909-X).

(27) Bargon, J.; Seifert, K.-G. The Azobenzene Radical Cation, an Intermediate during Diazonium Reactions. *Tetrahedron Lett.* **1974**, *15* (26), 2265–2268.  
[https://doi.org/10.1016/S0040-4039\(01\)92229-4](https://doi.org/10.1016/S0040-4039(01)92229-4).

(28) Porter, N. A.; Green, J. G. <sup>15</sup>N Study of the Phenyldiazenyl Radical: A Search for Phenyl Migration. *Tetrahedron Lett.* **1975**, *16* (31), 2667–2670. [https://doi.org/10.1016/S0040-4039\(00\)75209-9](https://doi.org/10.1016/S0040-4039(00)75209-9).

(29) Porter, N. A.; Dubay, G. R.; Green, J. G. Diazenyl Radicals: A Nitrogen-15 CIDNP and Radical Trapping Study of Unsymmetric Diazenes. *J. Am. Chem. Soc.* **1978**, *100* (3), 920–925.  
<https://doi.org/10.1021/ja00471a044>.

(30) Brede, O.; Mehnert, R.; Naumann, W.; Becker, H. G. O. Pulse Radiolysis of Arenediazonium Salts in Water/Tert.-Butanol. *Berichte der Bunsengesellschaft für physikalische Chemie* **1980**, *84* (7), 666–672. <https://doi.org/10.1002/bbpc.19800840711>.

(31) Suehiro, T.; Masuda, S.; Tashiro, T.; Nakauza, R.; Tagushi, M.; Koike, A.; Rieker, A. Formation and Identification of Aryldiazenyl Radicals Using the ESR Technique. *J. Am. Chem. Soc.* **1986**, *59* (6), 1877–1886. <https://doi.org/10.1246/bcsj.59.1877>.

- (32) Adams, J. Stephen.; Burton, K. A.; Andrews, B. Kim.; Weisman, R. Bruce.; Engel, P. S. Time-Resolved Observation of Sequential Bond Cleavage in a Gas-Phase Azoalkane. *J. Am. Chem. Soc.* **1986**, *108* (25), 7935–7938. <https://doi.org/10.1021/ja00285a009>.
- (33) Suehiro, T.; Masuda, S.; Nakausa, T.; Taguchi, M.; Mori, A.; Koike, A.; Date, M. Decay Reactions of Aryldiazenyl Radicals in Solution. *Bull. Chem. Soc. Jpn.* **1987**, *60* (9), 3321-3330. <https://doi.org/10.1246/bcsj.60.3321>.
- (34) Galli, C. Radical Reactions of Arenediazonium Ions: An Easy Entry into the Chemistry of the Aryl Radical. *Chem. Rev.* **1988**, *88* (5), 765–792. <https://doi.org/10.1021/cr00087a004>.
- (35) Pause, L.; Robert, M.; Savéant, J.-M. Can Single-Electron Transfer Break an Aromatic Carbon–Heteroatom Bond in One Step? A Novel Example of Transition between Stepwise and Concerted Mechanisms in the Reduction of Aromatic Iodides. *J. Am. Chem. Soc.* **1999**, *121* (30), 7158–7159. <https://doi.org/10.1021/ja991365q>.
- (36) Savéant, J.-M. Electron Transfer, Bond Breaking and Bond Formation; Advances in Physical Organic Chemistry; Academic Press, **2000**; Vol. 35, pp 117–192. [https://doi.org/10.1016/S0065-3160\(00\)35013-4](https://doi.org/10.1016/S0065-3160(00)35013-4).
- (37) Andrieux, C. P.; Pinson, J. The Standard Redox Potential of the Phenyl Radical/Anion Couple. *J. Am. Chem. Soc.* **2003**, *125* (48), 14801–14806. <https://doi.org/10.1021/ja0374574>.
- (38) Mesnage, A.; Esnouf, S.; Jégou, P.; Deniau, G.; Palacin, S. Understanding the Redox-Induced Polymer Grafting Process: A Dual Surface-Solution Analysis. *Chem. Mater.* **2010**, *22* (23), 6229–6239. <https://doi.org/10.1021/cm1014702>.

(39) Ortiz, B.; Saby, C.; Champagne, G. Y.; Bélanger, D. Electrochemical Modification of a Carbon Electrode Using Aromatic Diazonium Salts. 2. Electrochemistry of 4-Nitrophenyl Modified Glassy Carbon Electrodes in Aqueous Media. *J. Electroanal. Chem.* **1998**, *455* (1–2), 75–81. [https://doi.org/10.1016/S0022-0728\(98\)00252-6](https://doi.org/10.1016/S0022-0728(98)00252-6).

(40) Ceccato, M.; Nielsen, L. T.; Iruthayaraj, J.; Hinge, M.; Pedersen, S. U.; Daasbjerg, K. Nitrophenyl Groups in Diazonium-Generated Multilayered Films: Which Are Electrochemically Responsive? *Langmuir* **2010**, *26* (13), 10812–10821.

(41) Amatore, C.; Maisonhaute, E.; Schöllhorn, B.; Wadhawan, J. Ultrafast Voltammetry for Probing Interfacial Electron Transfer in Molecular Wires. *ChemPhysChem* **2007**, *8* (9), 1321–1329. <https://doi.org/10.1002/cphc.200600774>.

(42) Zhou, X.-S.; Mao, B.-W.; Amatore, C.; Compton, R. G.; Marignier, J.-L.; Mostafavi, M.; Nierengarten, J.-F.; Maisonhaute, E. Transient Electrochemistry: Beyond Simply Temporal Resolution. *Chem. Commun.* **2016**, *52* (2), 251–263. <https://doi.org/10.1039/C5CC07953E>.

(43) Amatore, C.; Maisonhaute, E.; Simonneau, G. Ohmic Drop Compensation in Cyclic Voltammetry at Scan Rates in the Megavolt per Second Range: Access to Nanometric Diffusion Layers via Transient Electrochemistry. *J. Electroanal. Chem.* **2000**, *486* (2), 141–155. [https://doi.org/10.1016/S0022-0728\(00\)00131-5](https://doi.org/10.1016/S0022-0728(00)00131-5).

(44) Daasbjerg, K.; Sehested, K. Reduction of Substituted Benzenediazonium Salts by Solvated Electrons in Aqueous Neutral Solution Studied by Pulse Radiolysis. *J. Phys. Chem. A* **2002**, *106* (46), 11098–11106. <https://doi.org/10.1021/jp025900b>.

(45) Adenier, A.; Combellas, C.; Kanoufi, F.; Pinson, J.; Podvorica, F. I. Formation of Polyphenylene Films on Metal Electrodes by Electrochemical Reduction of Benzenediazonium Salts. *Chem. Mater.* **2006**, *18* (8), 2021–2029. <https://doi.org/10.1021/cm052065c>.

(46) Pichereau, L.; López, I.; Cesbron, M.; Dabos-Seignon, S.; Gautier, C.; Breton, T. Controlled Diazonium Electrografting Driven by Overpotential Reduction: A General Strategy to Prepare Ultrathin Layers. *Chem. Commun.* **2019**, *55* (4), 455–457. <https://doi.org/10.1039/C8CC08331B>.

(47) López, I.; Dabos-Seignon, S.; Breton, T. Use of Selective Redox Cross-Inhibitors for the Control of Organic Layer Formation Obtained via Diazonium Salt Reduction. *Langmuir* **2019**, *35* (34), 11048–11055. <https://doi.org/10.1021/acs.langmuir.9b01397>.

(48) Alévêque, O.; Gautier, C.; Levillain, E. Real-Time Absorption Spectroelectrochemistry: From Solution to Monolayer. *Curr. Opin. Electrochem.* **2019**, *15*, 34–41. <https://doi.org/10.1016/j.coelec.2019.03.015>.

(49) Polovyanenko, D. N.; Plyusnin, V. F.; Reznikov, V. A.; Khramtsov, V. V.; Bagryanskaya, E. G. Mechanistic Studies of the Reactions of Nitron Spin Trap PBN with Glutathionyl Radical. *J. Phys. Chem. B* **2008**, *112* (15), 4841–4847. <https://doi.org/10.1021/jp711548x>.

(50) Merckx, D. W. H.; Plankensteiner, L.; Yu, Y.; Wierenga, P. A.; Hennebelle, M.; Van Duynhoven, J. P. M. Evaluation of PBN Spin-Trapped Radicals as Early Markers of Lipid Oxidation in Mayonnaise. *Food Chemistry* **2021**, *334*, 127578. <https://doi.org/10.1016/j.foodchem.2020.127578>.